



# **18650 Cell Bottom Vent: Preliminary Evaluation into its Merits for Preventing Side Wall Rupture**

By

**Natalie Anderson, Minh Tran, and Eric Darcy  
NASA-JSC**

**S&T Meeting  
San Diego, CA  
7 Dec 2016**



# Outline

- 5 Design Guidelines
- Trading thermal isolation vs heat dissipation
  - Full thermal isolation
  - Drawing heat from cell bottoms
  - Full can length interstitial heat sink approach
- Risk of side wall rupture during thermal runaway
- New cell designs with cell bottom vent from Sony and LG
  - Vent & burst pressure
  - Thermal runaway performance
- Summary of findings to date
- Future work



# High Power/Energy 18650 Cell Designs

- Specific Energy Range 259-276 Wh/kg
- Energy Density Range 704-735 Wh/L



Panasonic NCR18650GA

LG INR18650 MJ1



Samsung INR18650-35E




Sony US18650VC7



<b>C/10 at RT</b>	<b>Panasonic NCR GA</b>	<b>Samsung 3.5E</b>	<b>Sony VC7</b>	<b>LG MJ1</b>
Discharge Capacity (Ah)	3.34	3.49	3.5	3.41
Discharge Energy (Wh)	12.16	12.7	12.72	12.46
DC Internal Resistance (mohm)	38	35	31	33
Average Mass (g)	47	46	47.4	46.9
Average Volume (L)	0.0173	0.0173	0.0173	0.0173
Specific Energy (Wh/kg)	259	276	269	266
Energy Density (Wh/L)	704	733	735	720




# C/10 Capacity Performance Comparison

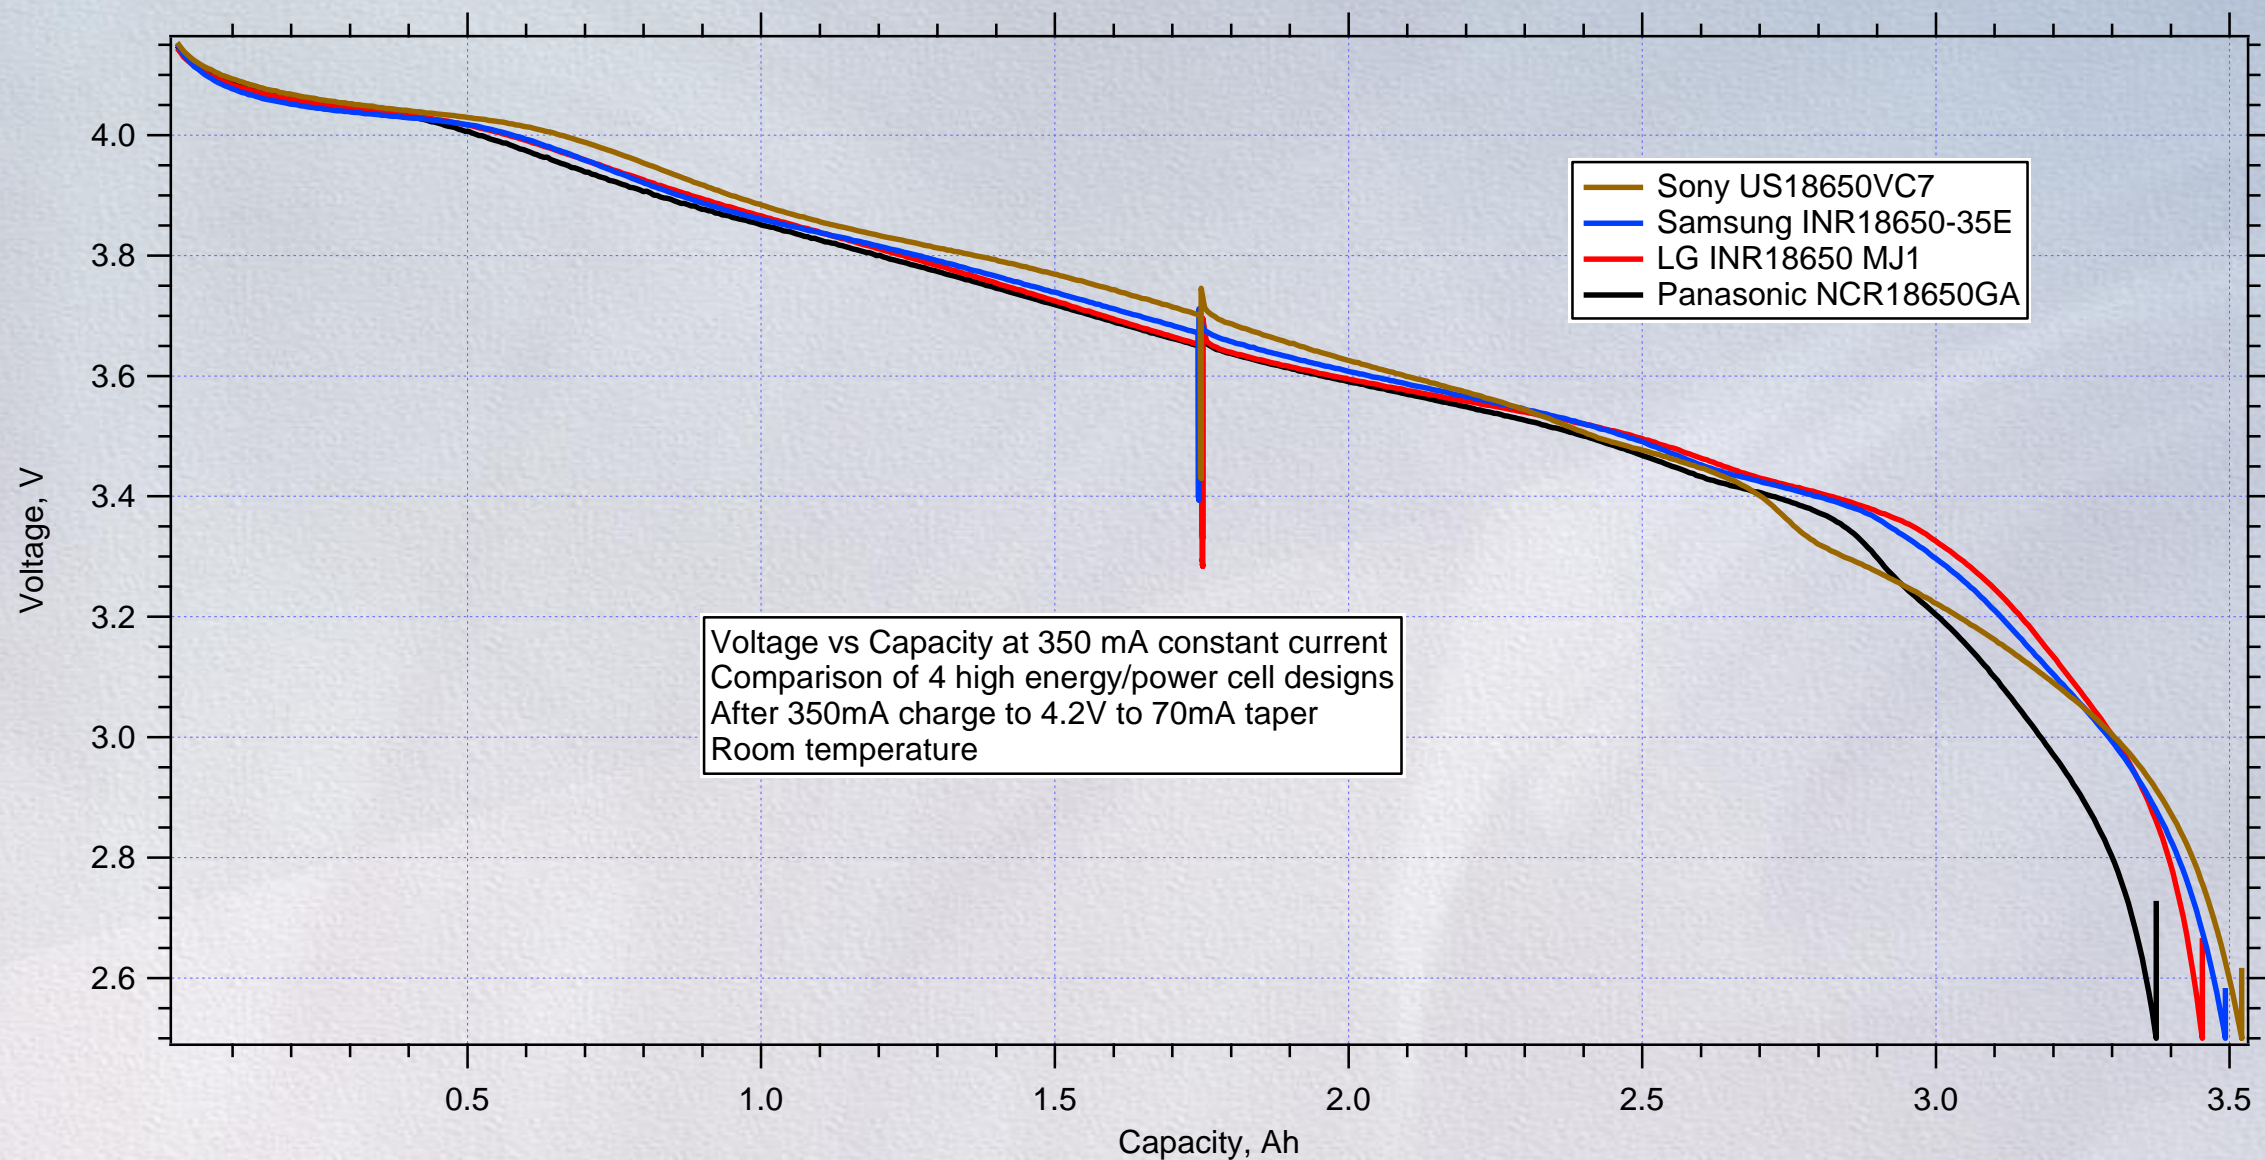



# Specific Energy (Wh/kg) Trends

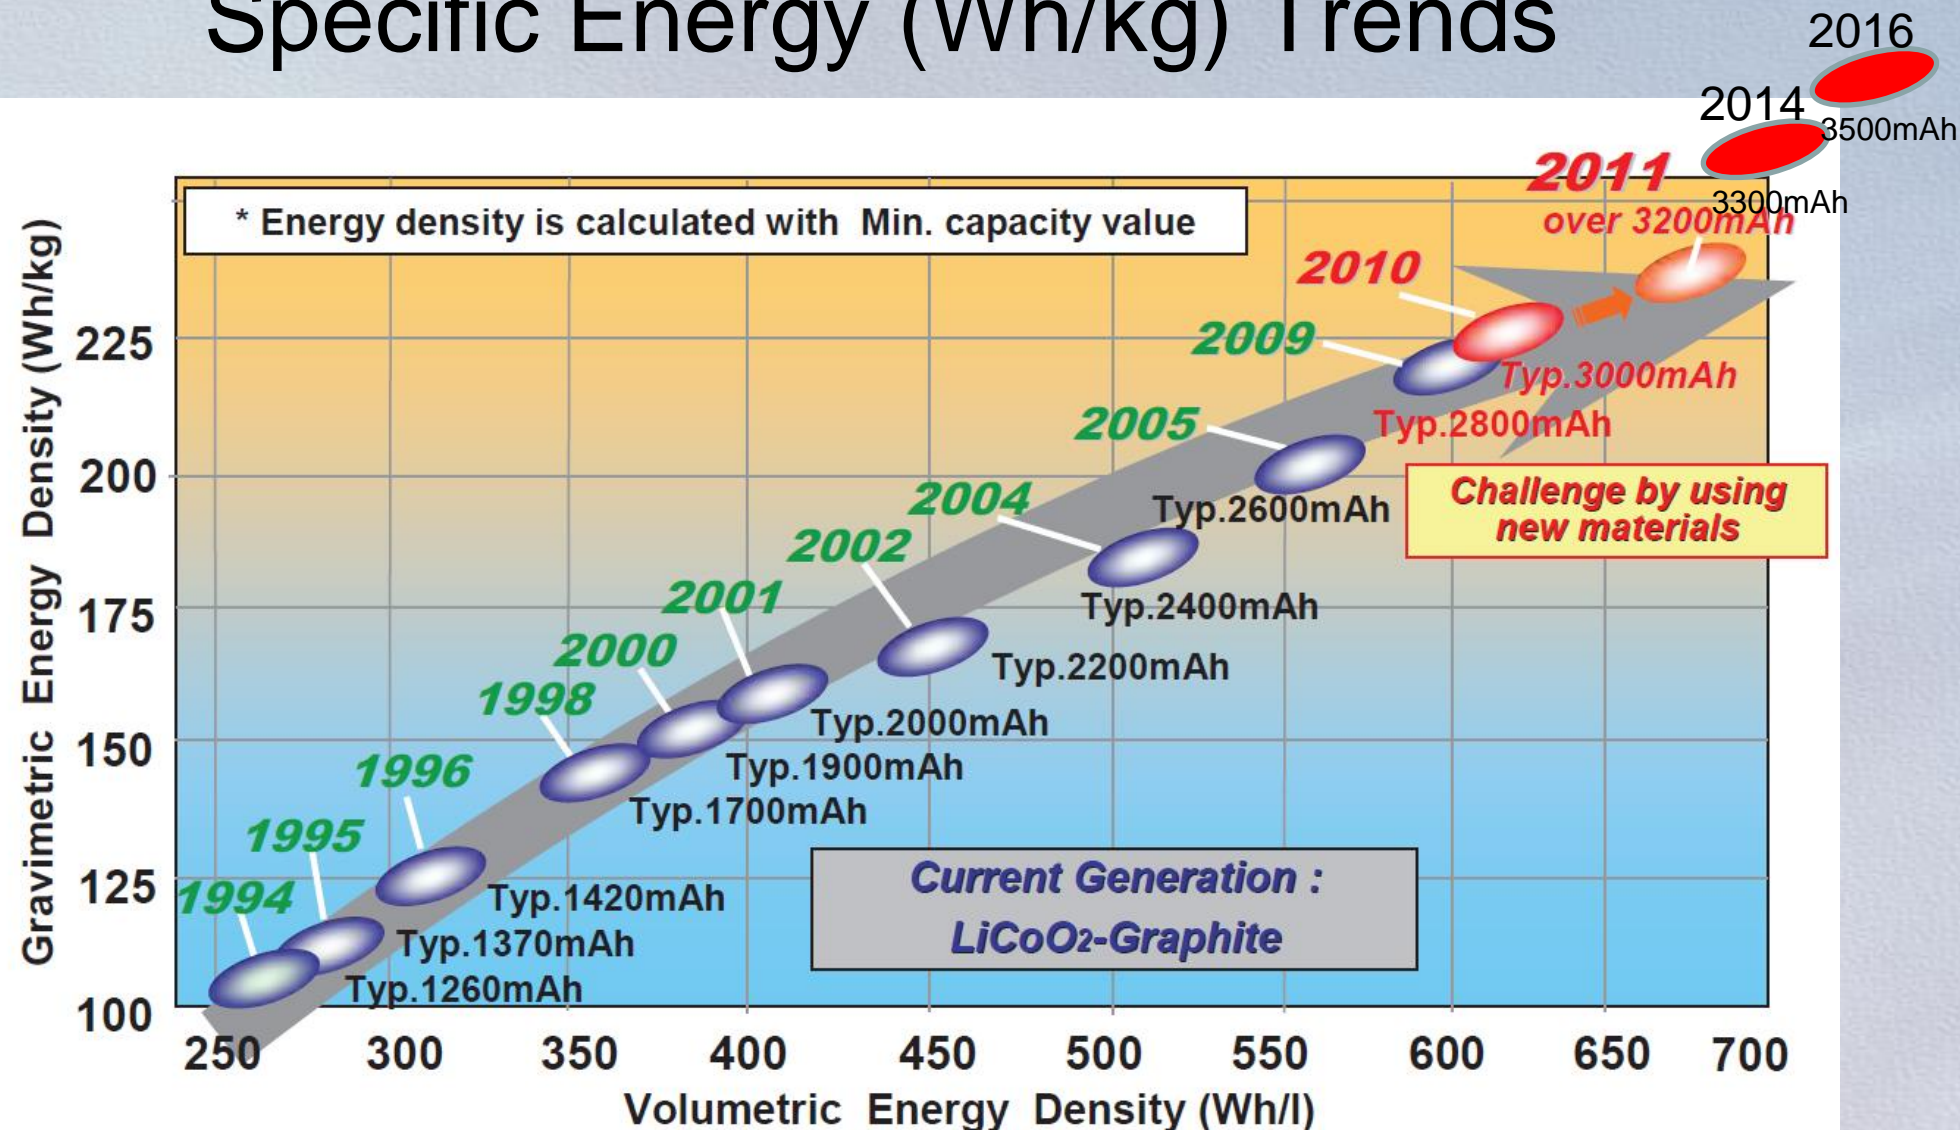


Source: Sanyo/Panasonic 2010

A high production rate design that achieves > 240 Wh/kg and > 660 Wh/L exists since 2012

Specify energy improvements are trending at 7-10% per year....should get to 300 Wh/kg by 2017



# Cell Can Wall Cross Sections

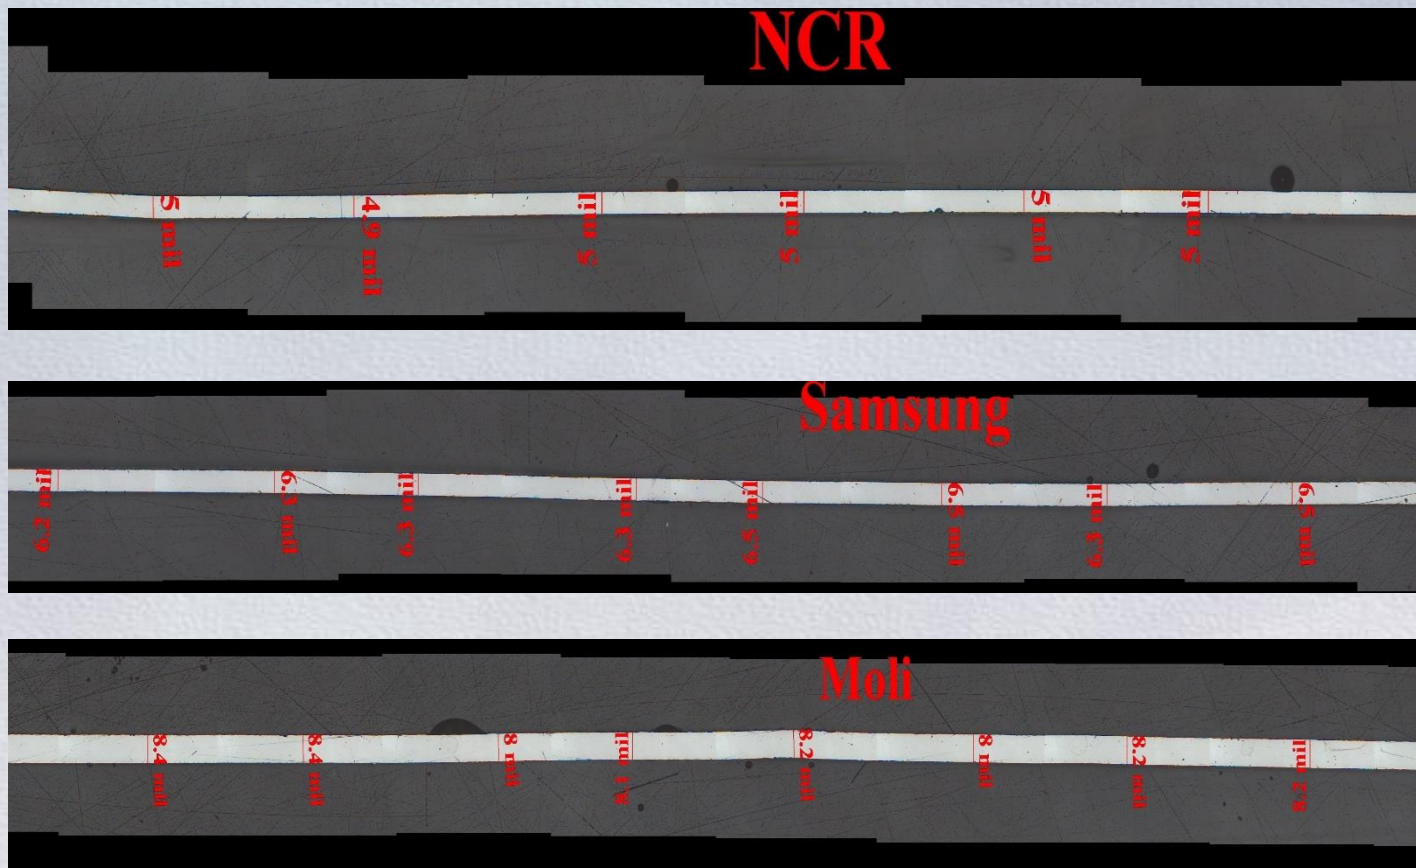

NCR18650B COTS design averages 127  $\mu\text{m}$

ICR18650-26F (2.6Ah Samsung) averages 160  $\mu\text{m}$

ICR18650J (2.4Ah Moli) averages 208  $\mu\text{m}$

**Thin can wall with  $>660 \text{ Wh/L}$   $\rightarrow$  high propensity to side wall ruptures/breaching**  
**Other factors include high reaction kinetics and high header crimp burst pressure**



# Axial View – Header of NCR18650B Cell

Double crimp header design

Header button

Button vent

Can crimp

Gasket seal

Internal crimp

Internal seal

Spin groove

0.005" (125 micron)  
Can wall thickness

Scored burst disc


CID mechanism

(+) tag

Center  
Mandrel

PTC annulus  
switch

Insulator

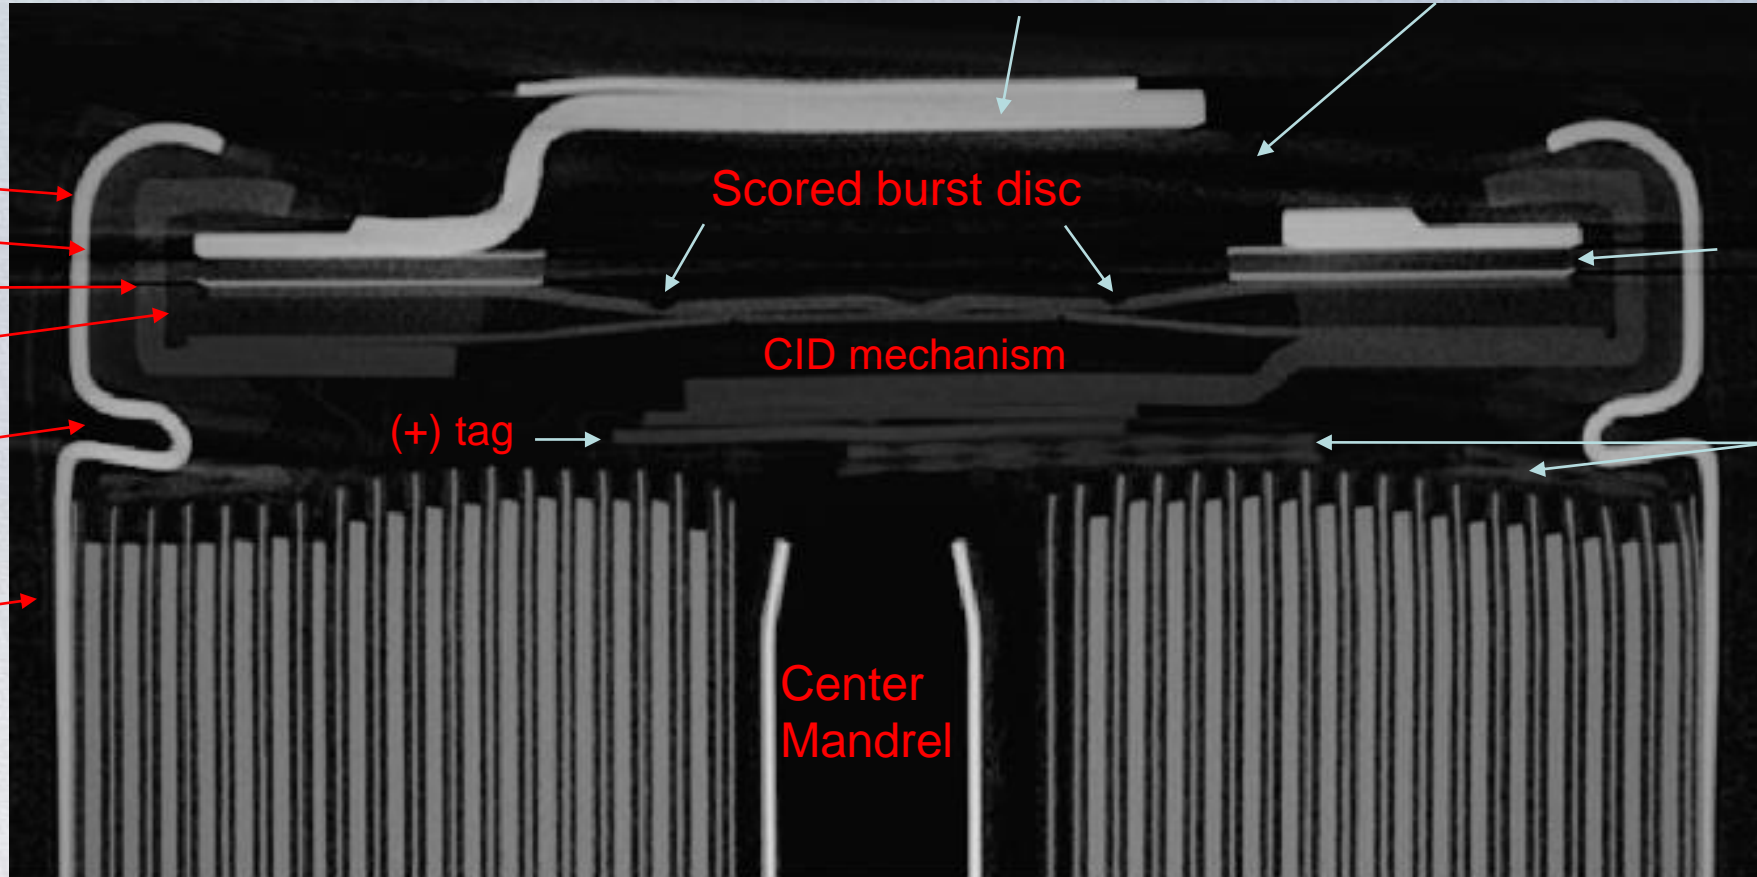

Note the double crimped header design

Burst Pressure of Crimped Header ~1000psia (68 atm)

3 of 30 cells experienced side wall ruptures during oven heating to TR



# Axial View – Header of Panasonic NCR18650GA

Features indicate a Sanyo heritage design

Header button

Button vent


Scored burst disc

(+) tag

Can crimp

Gasket seal

Spin groove

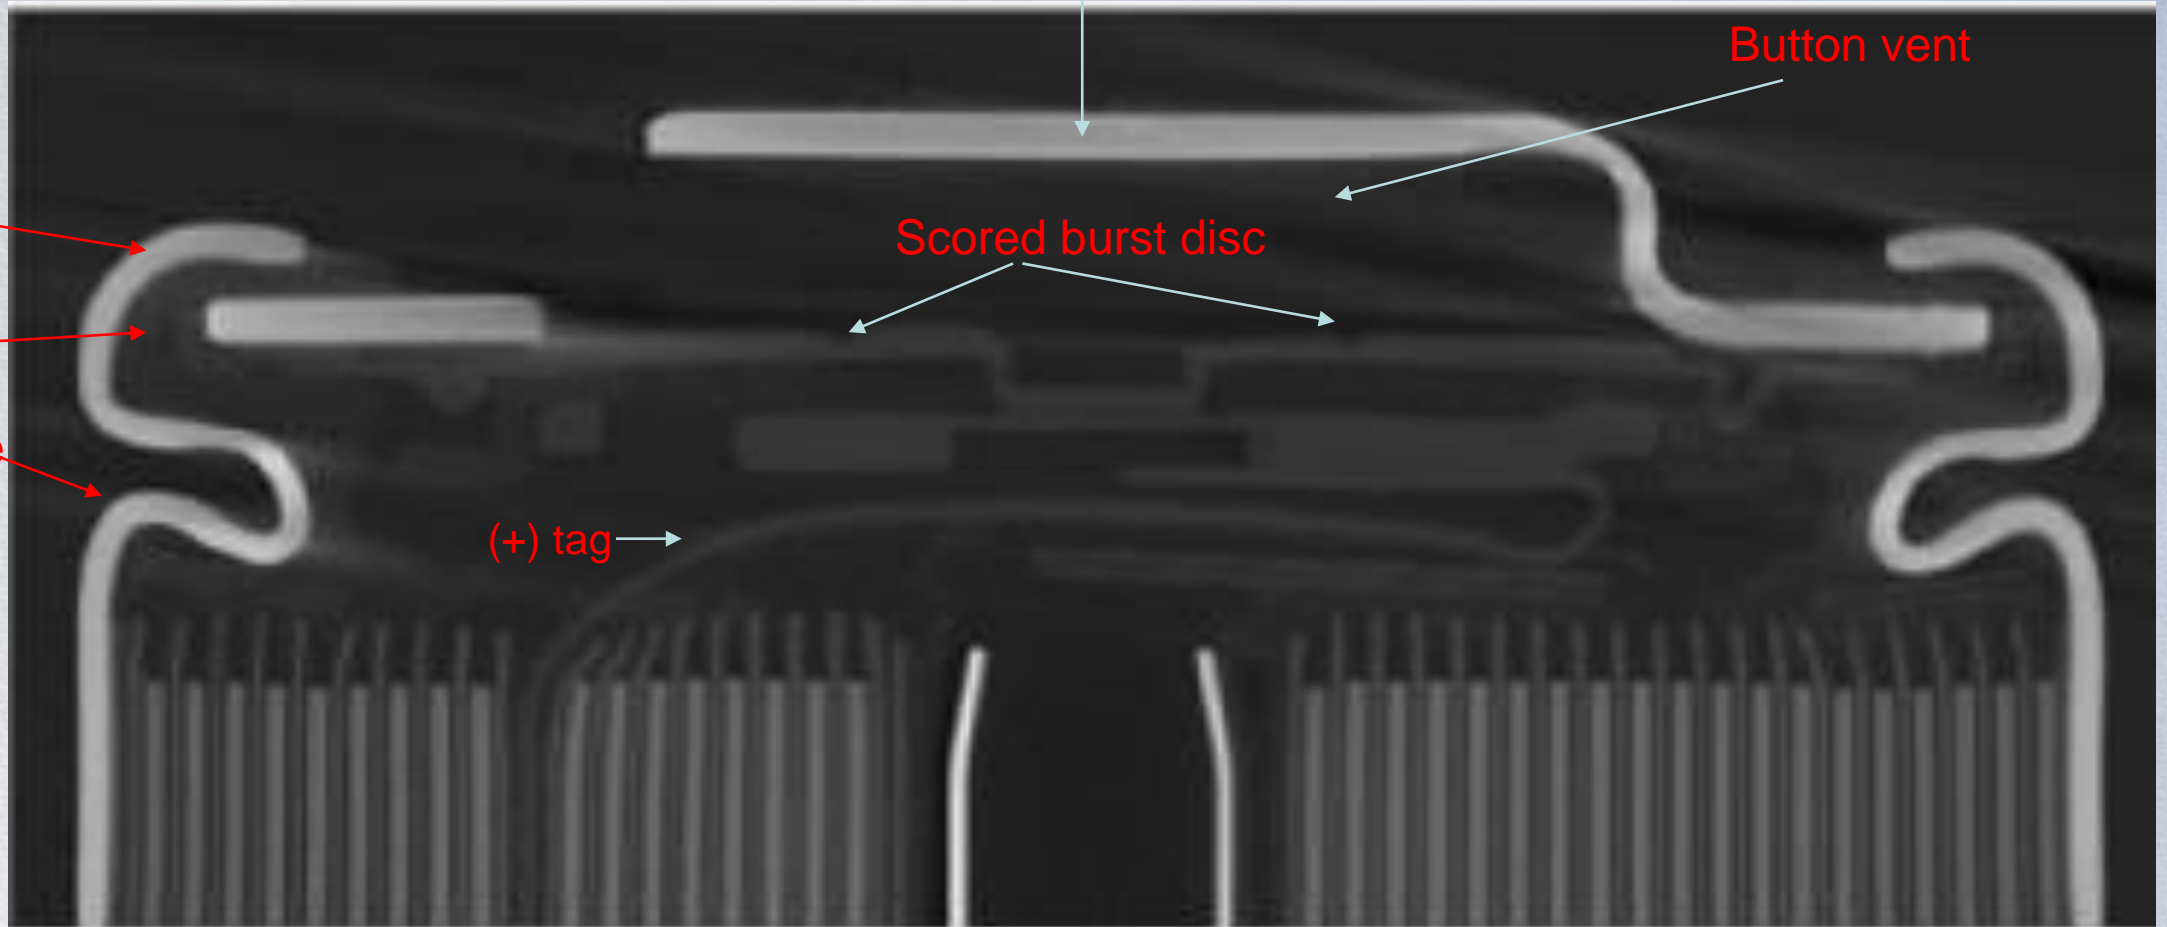


6.19 mil

6.06 mil

Can wall thickness  
0.0061" (155  $\mu\text{m}$ )



# LG INR18650 MJ1 - Axial View - Header - Cell

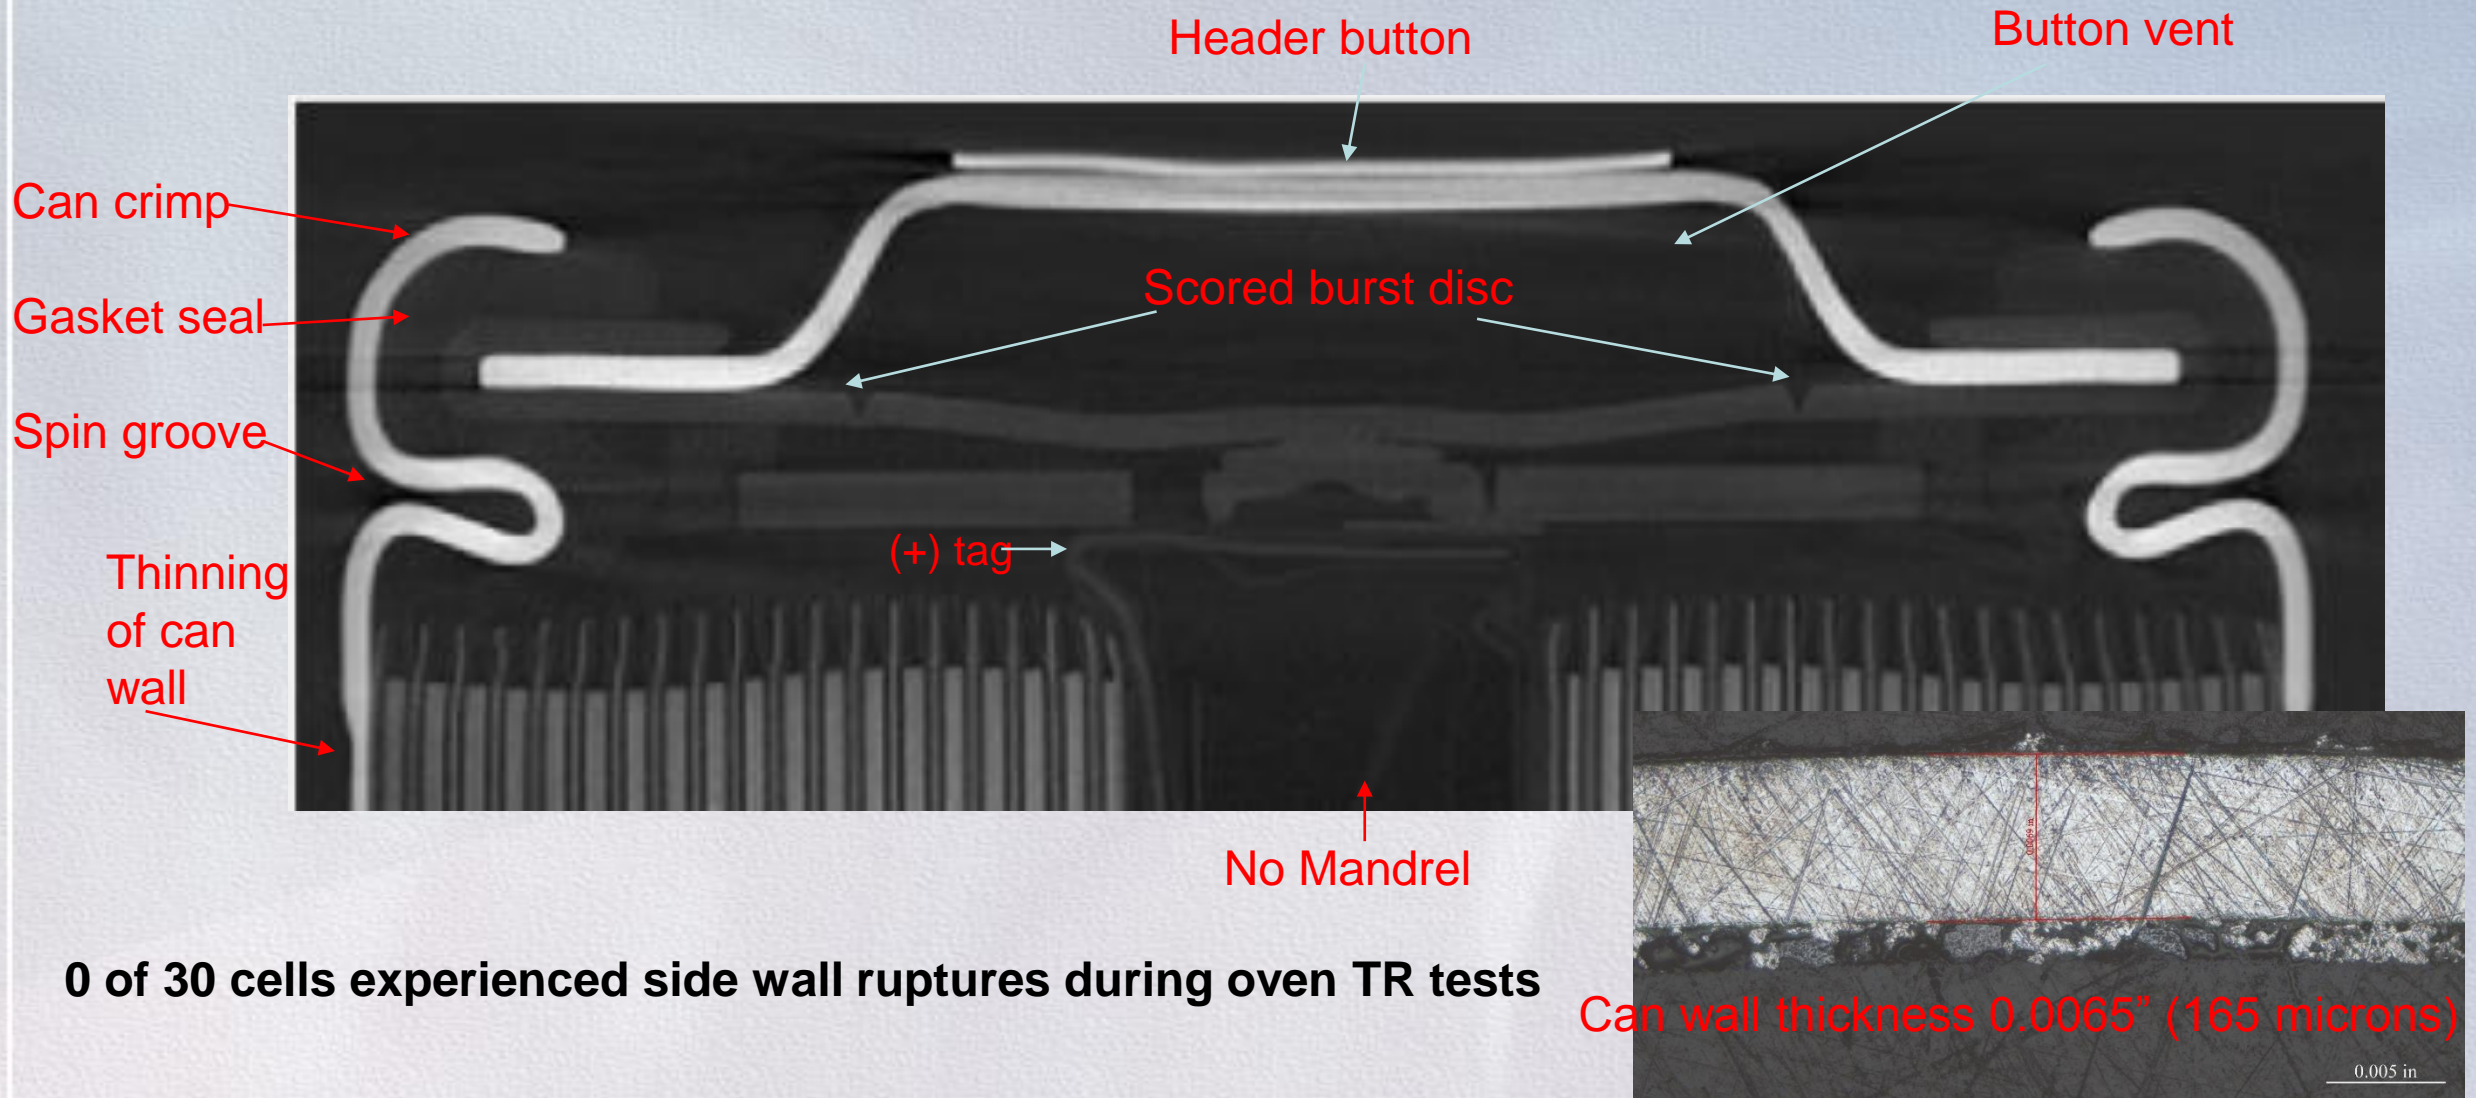


0 of 30 cells experienced side wall ruptures during oven TR tests

Note the single crimped header design with burst pressure ~800 psia (~54 atm)




# Samsung INR18650-35E - Axial View - Header - Cell 1

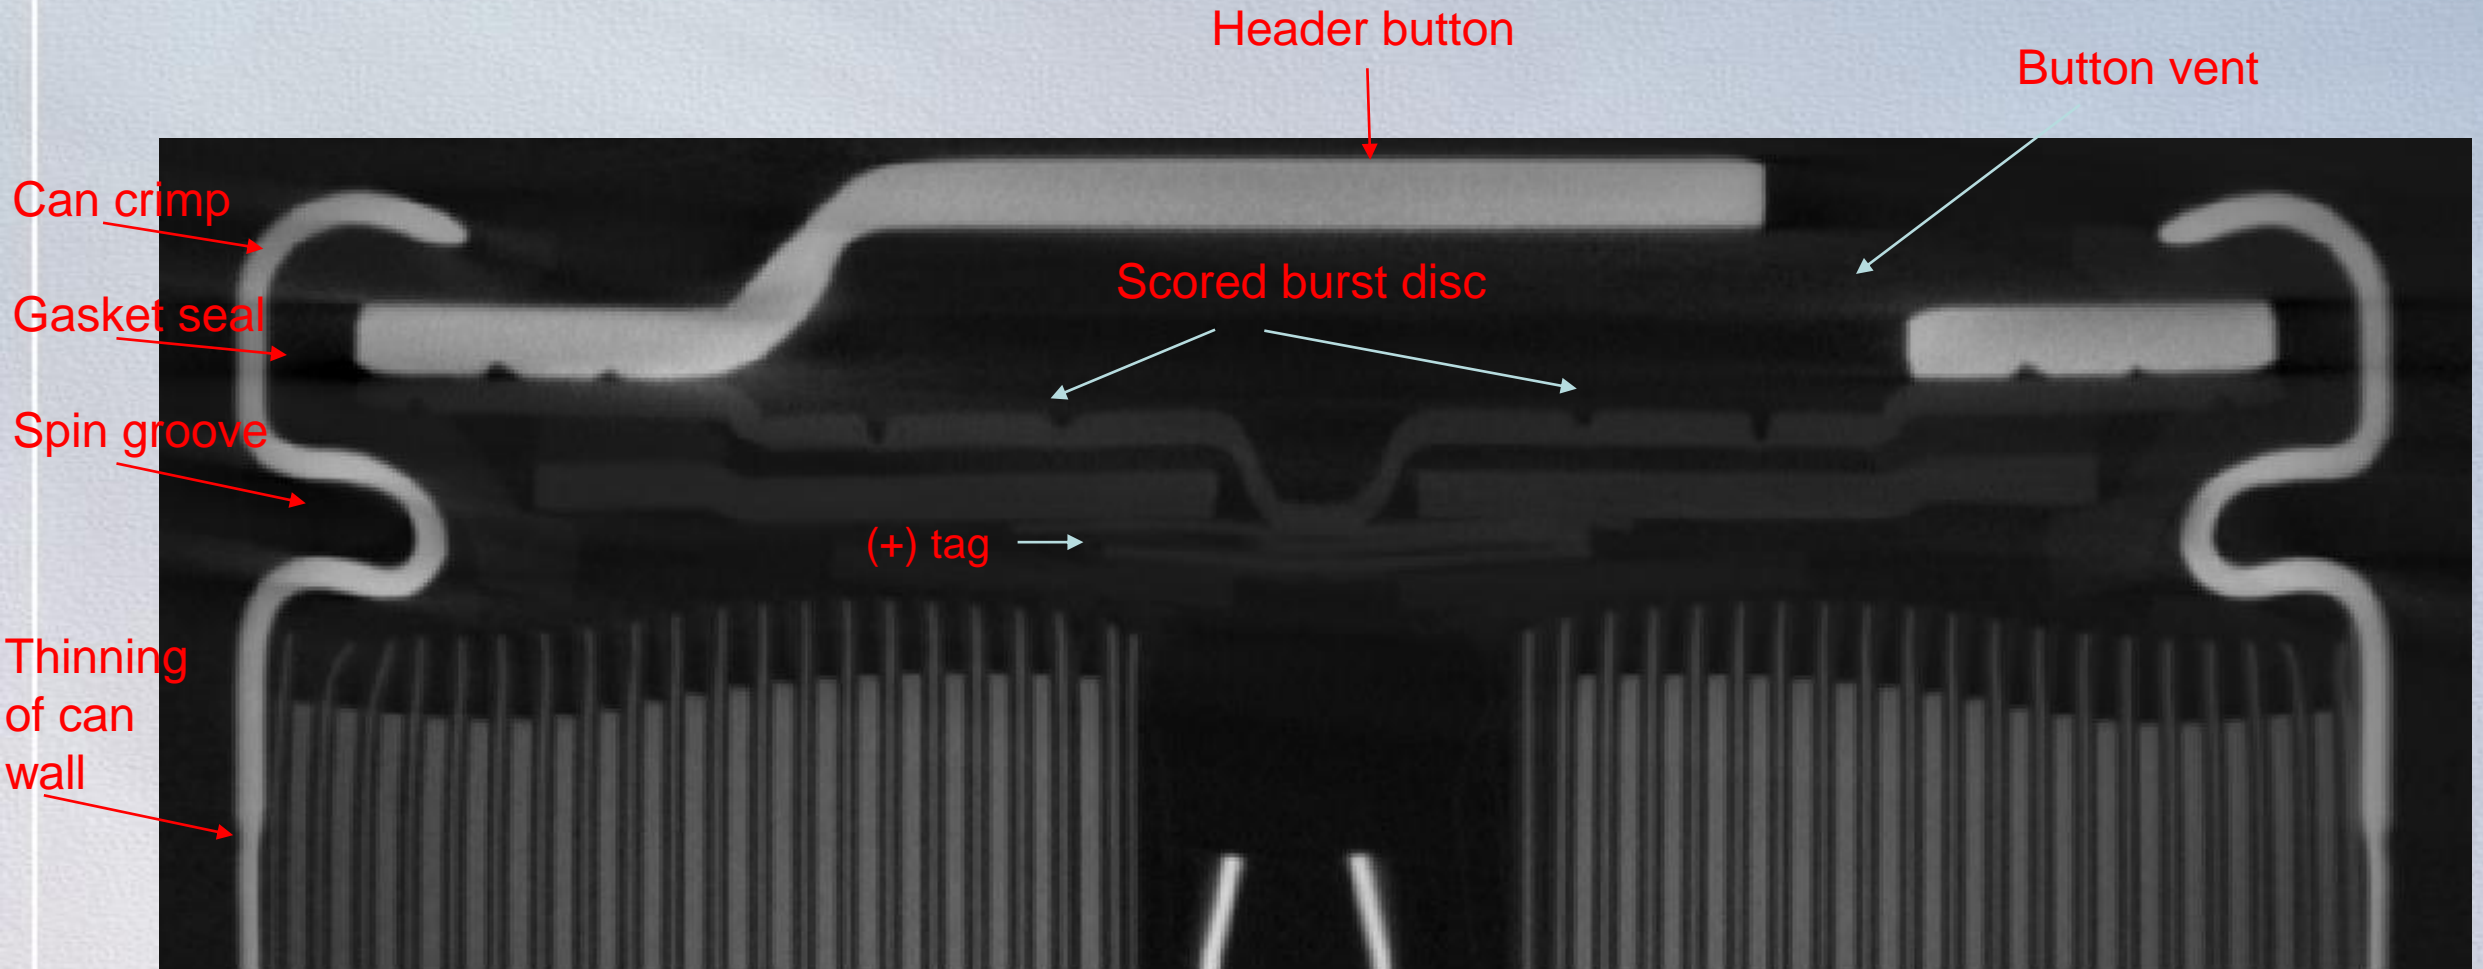



# CT Header of Sony VC7

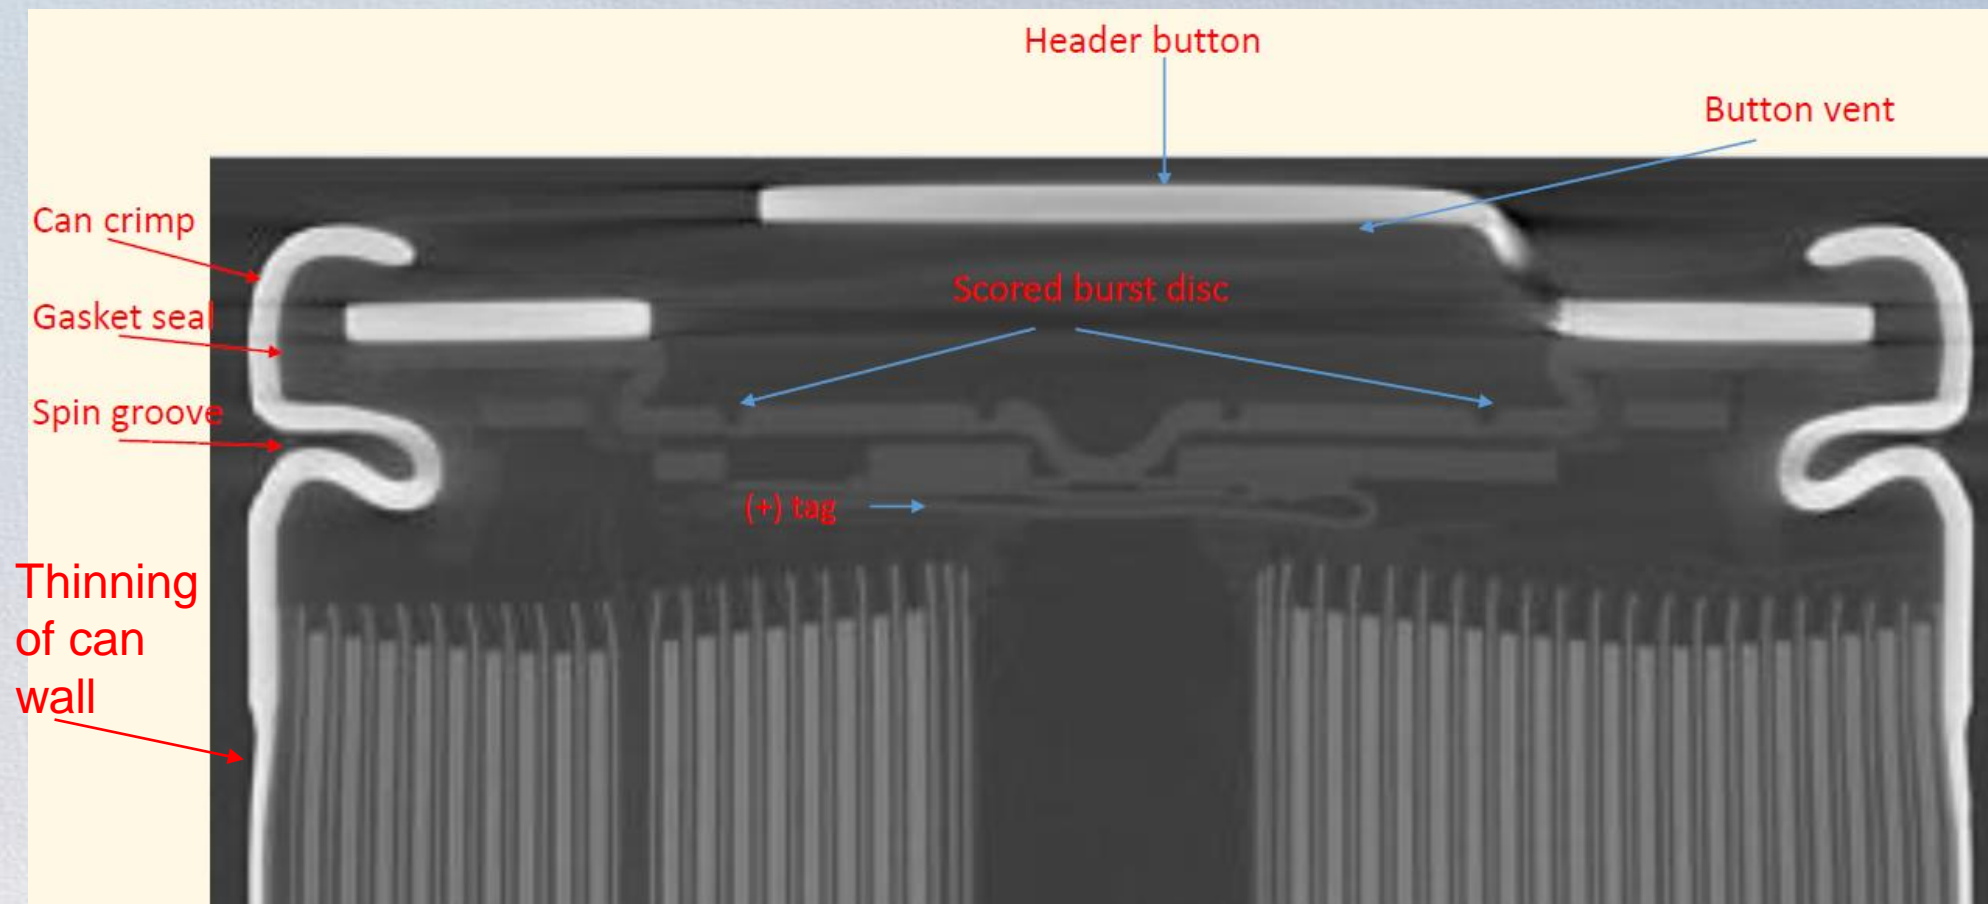

Sony VC-7  
Average Wall Thickness: 6.9 mil  
(Measurements taken at 200x magnification)



Avg can wall  
Thickness 0.0069"  
(175  $\mu\text{m}$ )



# 5 Design Driving Factors for Reducing Hazard Severity from a Single Cell TR

- **Reduce risk of cell can side wall ruptures**
  - Without structural support most high energy density ( $>660$  Wh/L) designs are very likely to experience side wall ruptures during TR
  - Battery should minimize constrictions on cell TR pressure relief
- **Provide adequate cell spacing and heat rejection**
  - Direct contact between cells nearly assures propagation
  - Spacing required is inversely proportional to effectiveness of heat dissipation path
- **Individually fuse parallel cells**
  - TR cell becomes an external short to adjacent parallel cells and heats them up
- **Protect the adjacent cells from the hot TR cell ejecta (solids, liquids, and gases)**
  - TR ejecta is electrically conductive and can cause circulating currents
- **Prevent flames and sparks from exiting the battery enclosure**
  - Provide tortuous path for the TR ejecta before hitting battery vent ports equipped flame arresting screens






# Current Spacesuit Battery Design



Solid Al side panels  
block cell vents


## Design Features

- 80 Li-ion cells (16p-5s)
- ICR-18650J from E-one Moli Energy (2.4Ah)

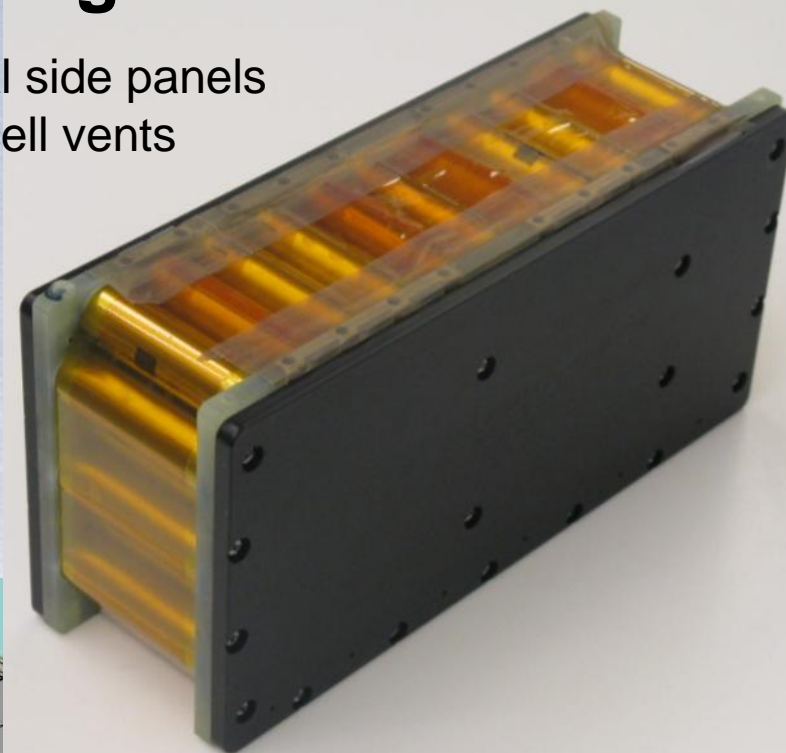

## Compliance with the 5 rules

- Minimize side wall ruptures ✓
- No direct cell-cell contact ✓
- Individually fusing cell in parallel X
- Protecting adjacent cells from TR ejecta X
- Include flame arresting vent ports X

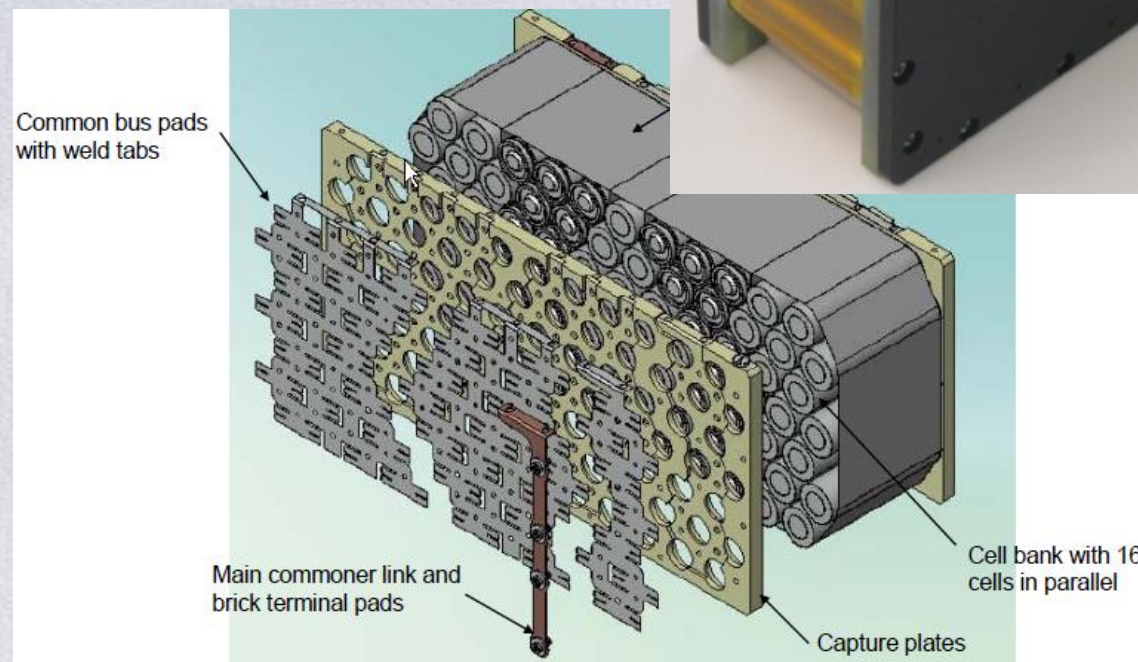



# Design Propagates TR – Catastrophic Hazard




**Battery external surfaces reach 350°C  
Vented some sparks and much smoke for >  
15 min**






Pre-Test

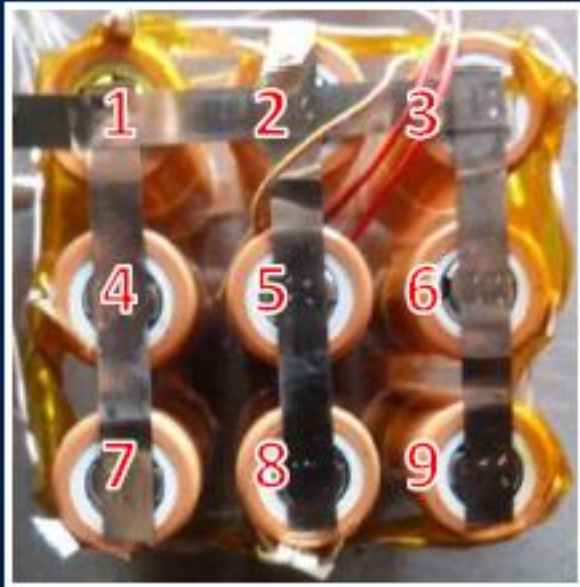

Jeevarajan et al. from 2014 Workshop showed that without any heat dissipation path except through electrical parallel connections, adjacent cells get damaged (shorted) with even 4 mm spacing

9P LGC2 4mm

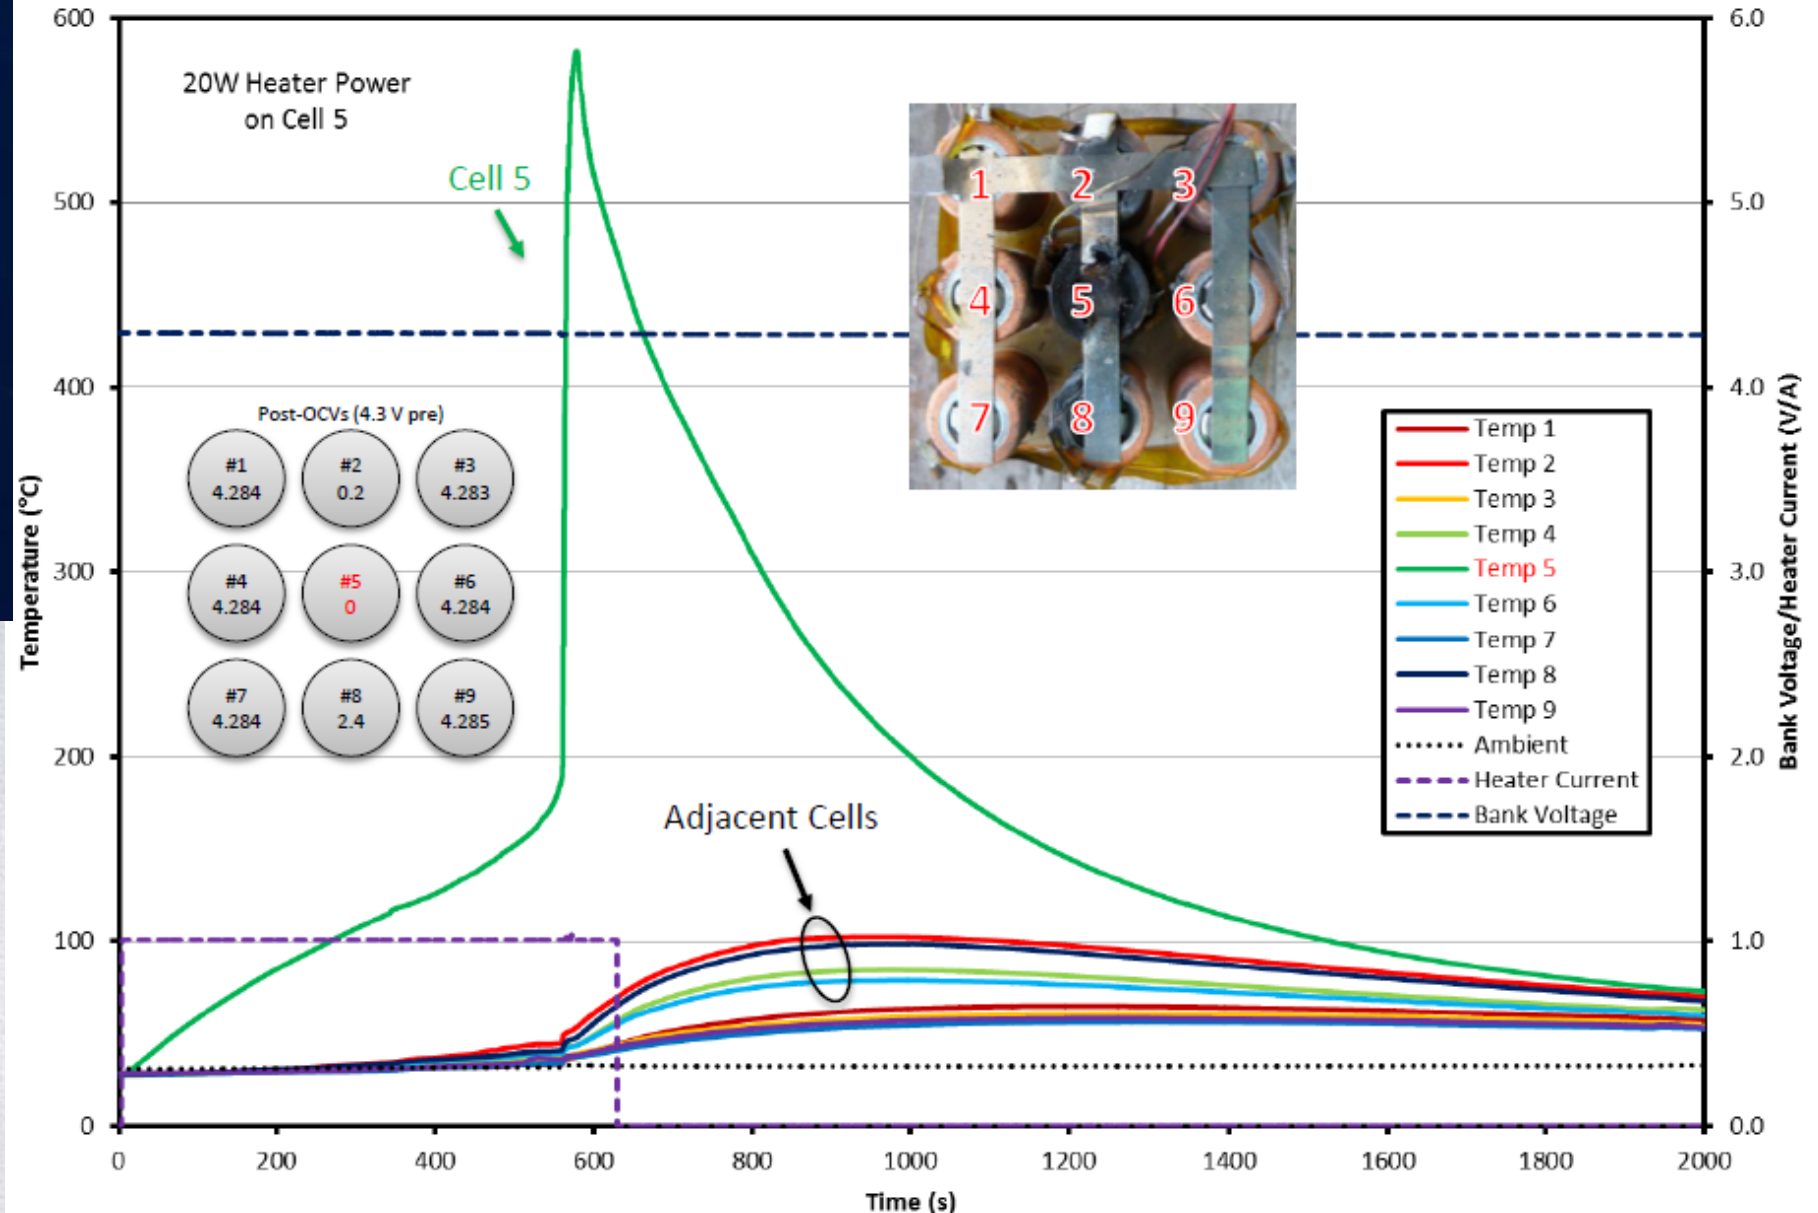



# VHS TR Test with Panasonic NCR18650B Cells




Side wall ruptures will even defeat very high flux heat rejection paths!

- Vaporizing Heat Sink (VHS) leaves 10mm of cell can wall bottoms exposed
- 2mm spacing between cells
- Trigger cell had side wall rupture in circumferential heater area which impinged TR ejecta into adjacent cell
- Resulted in propagation to two additional cells and damaged several others





# Orion Battery 14-cell Block

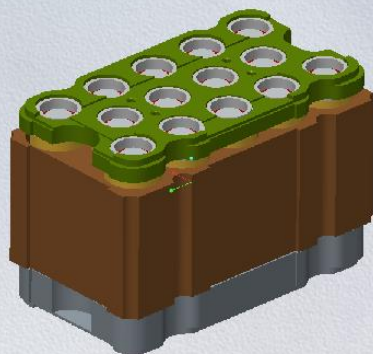

UPPER CAPTURE PLATE  
G10 FR4 FIBERGLASS  
COMP



MACOR VENT  
TUBES




18650 CELL



SYNTACTIC  
FOAM LINER




304 Stainless  
Steel Sleeve –  
9 mil wall  
thickness



LOWER HEAT-SINK  
CAPTURE PLATE  
6061-T651 ALUM



## Orion 14P-8S Superbrick


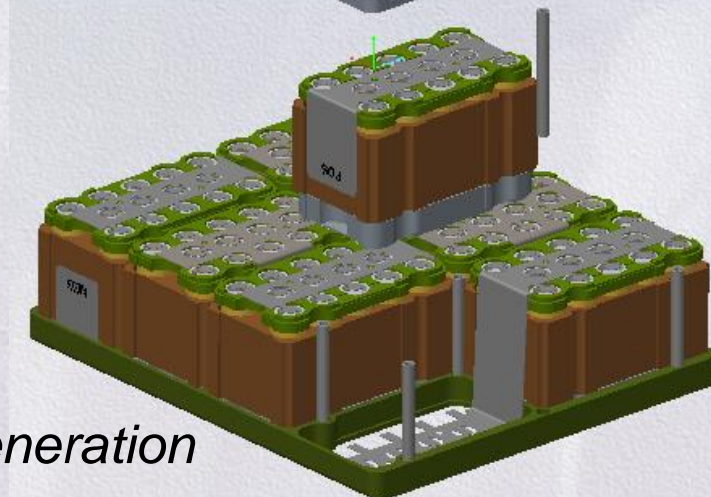


*Draw cell heat generation  
through cell bottom*



# Isolating vs Providing a heat path

- If you thermally isolate cells (air)
  - Adjacent cell  $\Delta T$  rise 80-100°C
  - ***Limited to cell designs with little risk of side wall ruptures***
  - Achieves 160-170 Wh/kg
- Orion - Partially conductive (Draw heat from cell bottom)
  - Conduct heat to divider plate
  - Adjacent cell  $\Delta T$  rise 60-70°C and shorter exposure
  - 14P-8S superbrick with SS sleeves achieves 150-160 Wh/kg

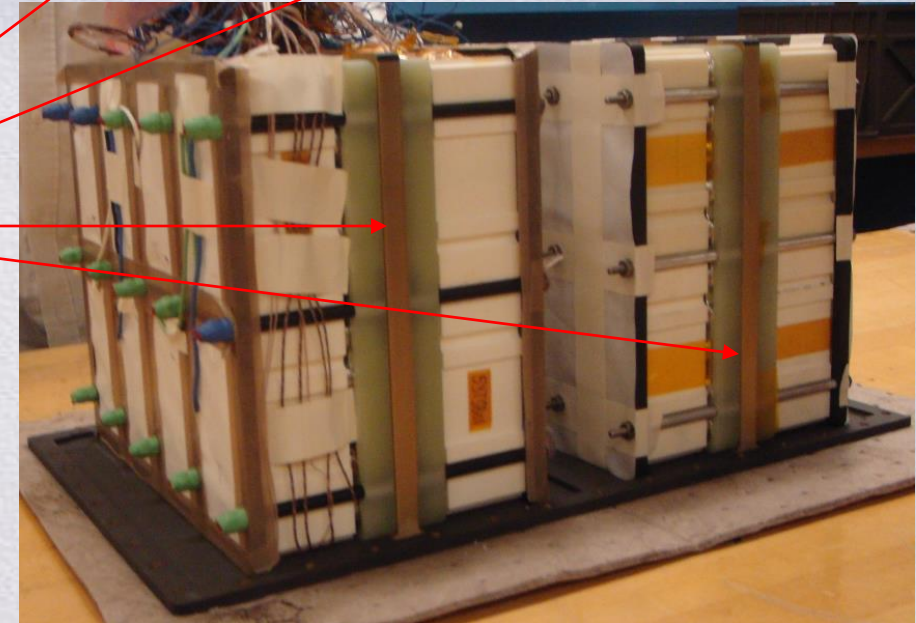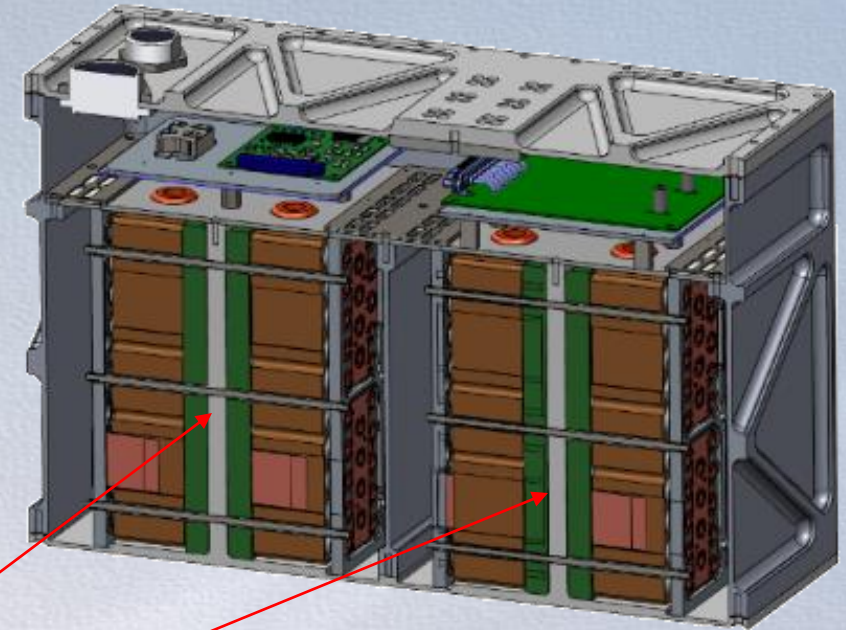






# Safer, Higher Performing Battery Design

## Compliance with the 5 rules

- **Minimize side wall ruptures** ✓
  - Al interstitial heat sink
- **No direct cell-cell contact** ✓
  - 0.5mm cell spacing, mica paper sleeves on each cell
- **Individually fusing cell in parallel** ✓
  - 12A fusible link
- **Protecting adjacent cells from TR ejecta** ✓
  - Ceramic bushing lining cell vent opening in G10 capture plate
- **Include flame arresting vent ports** ✓
  - Tortious path with flame arresting screens
  - Battery vent ports lined with steel screens

## Features

- 65 High Specific Energy Cell Design 3.4Ah (13P-5S)
- 37Ah and 686 Wh at BOL (in 16-20.5V window)
- Cell design likely to side wall rupture, but supported

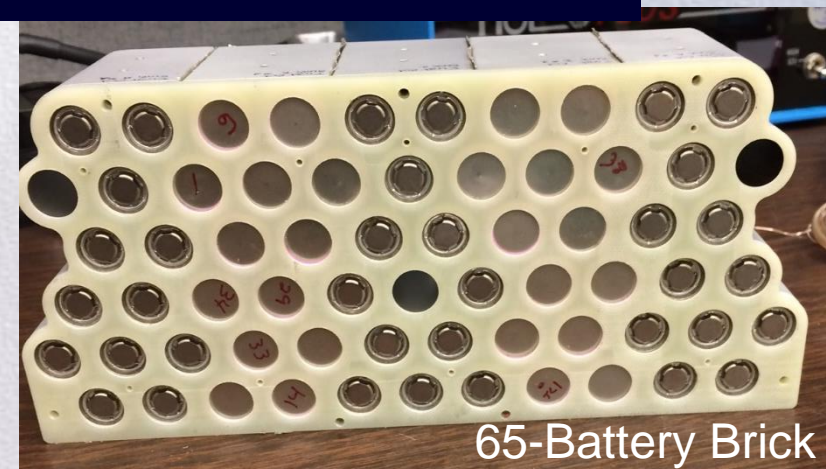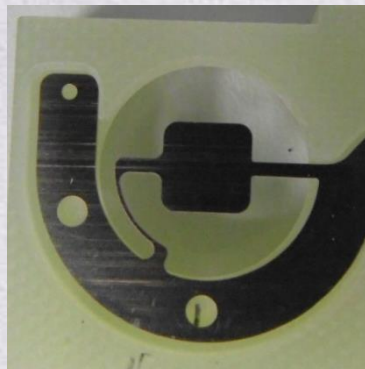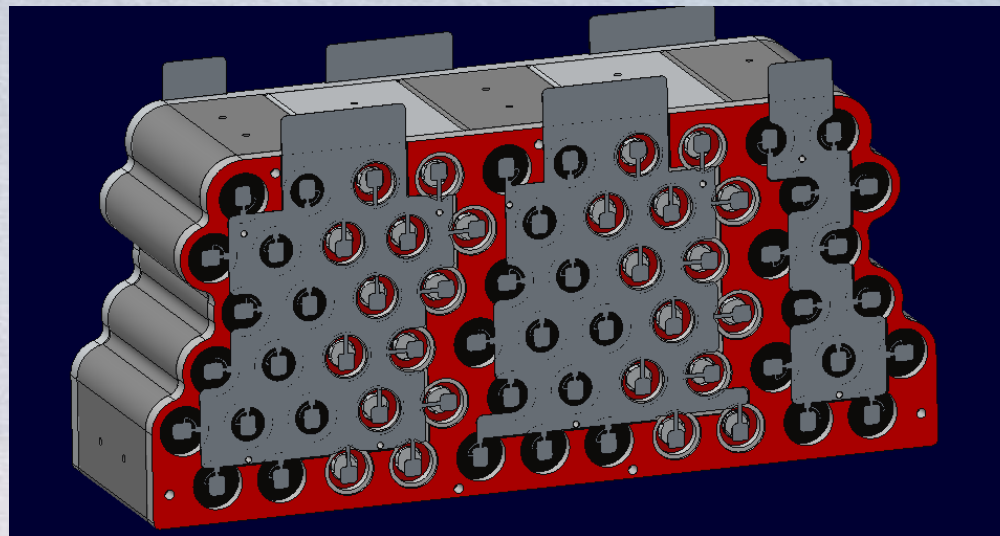


65-Battery Brick



# LLB2 Heat Sinks

No corner cells - Every cell has at least 3 adjacent cells

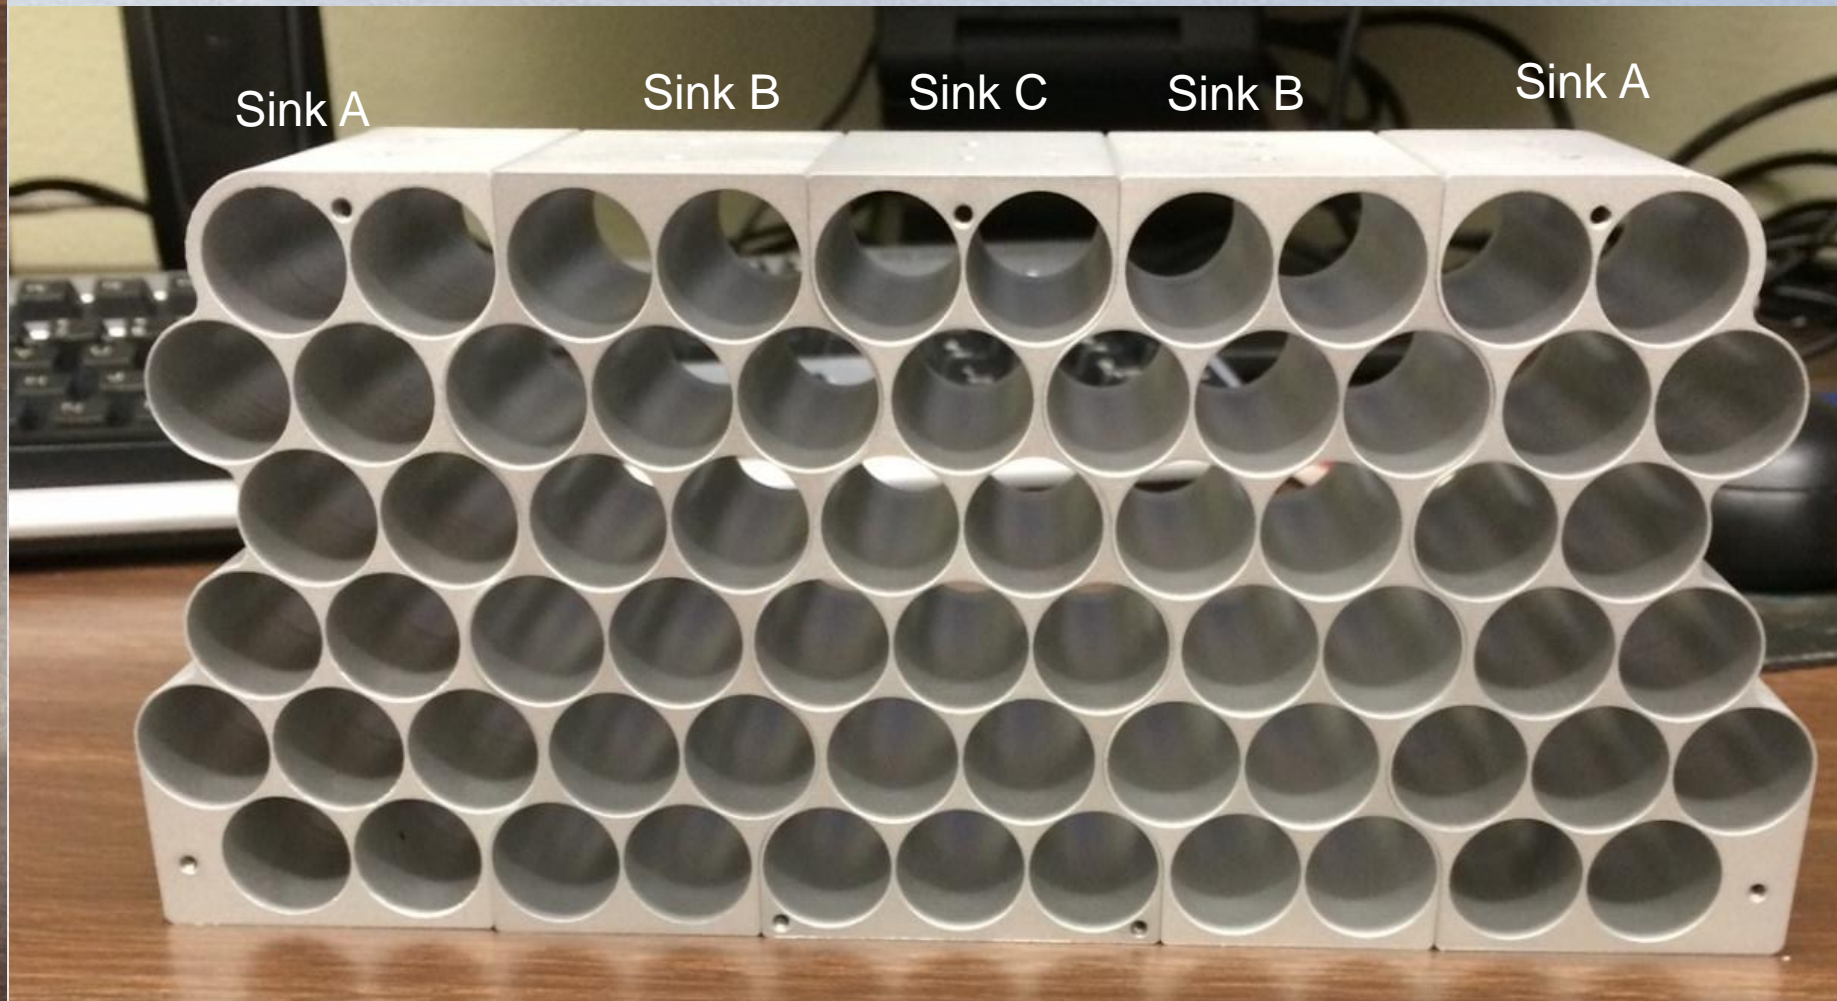


0.5mm cell spacing, Al 6061T6






- 13P-5S Configuration with 3.4 Ah LG cell design yielding 37 Ah at 3.8 A mission rate.
- Aluminum interstitial heat sink, 0.5 mm spacing between cells
- Mica sleeves around shrink wrap, 2 FT
- The G10 capture plate houses the + and - ends of the cells and prevents the Ni bussing from shorting to the heat sinks.
- The ceramic Macor bushing acts as a chimney to direct ejecta outwards and protect the G10/FR4 capture plate

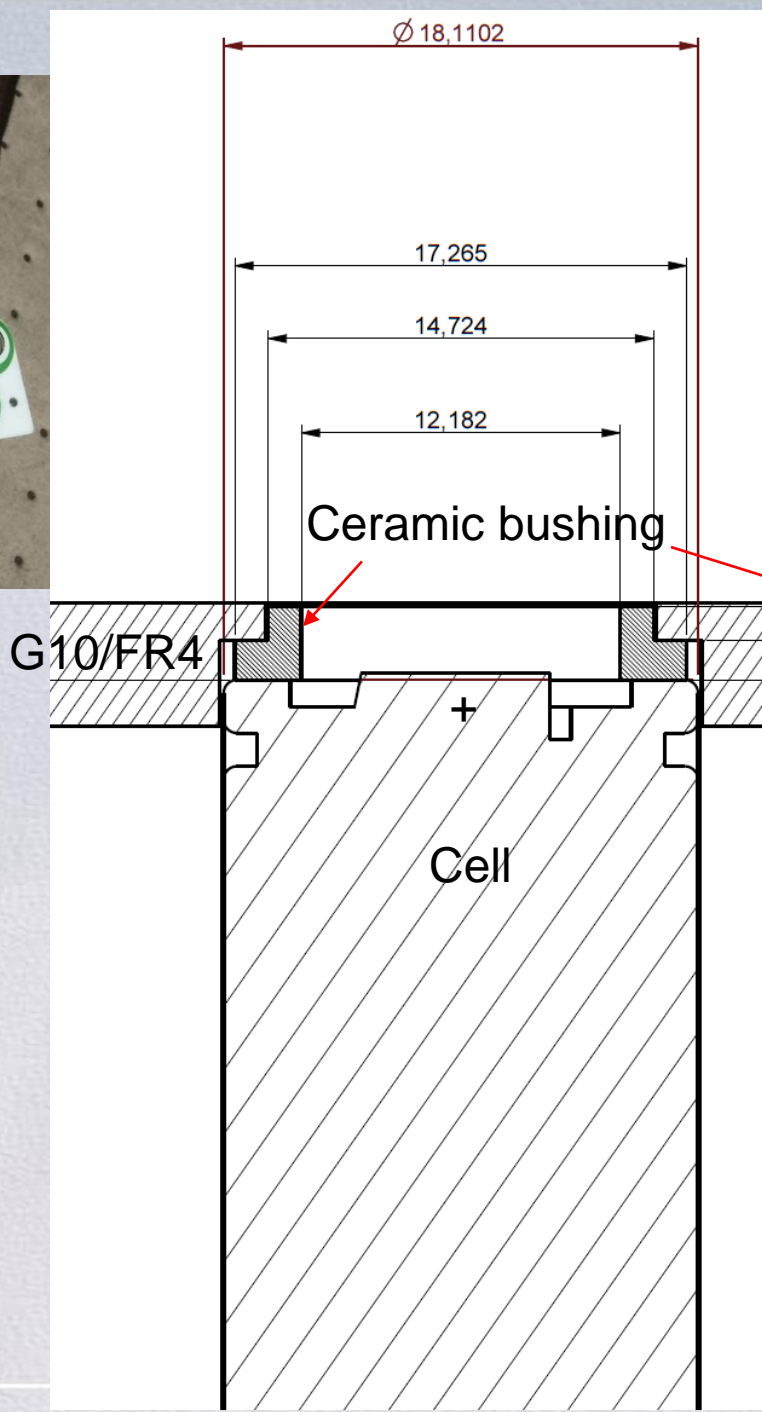




# Cell Brick Assembly > 180 Wh/kg

Mass Categories	g	%
3.4Ah 18650 Cells	3012.75	71.3%
Heat sinks	824.95	19.5%
Mica sleeves	182.31	4.3%
Capture plates	115.81	2.7%
Ceramic bushings	60.15	1.4%
Ni-201 bussing	29.71	0.7%
Total	4225.7	

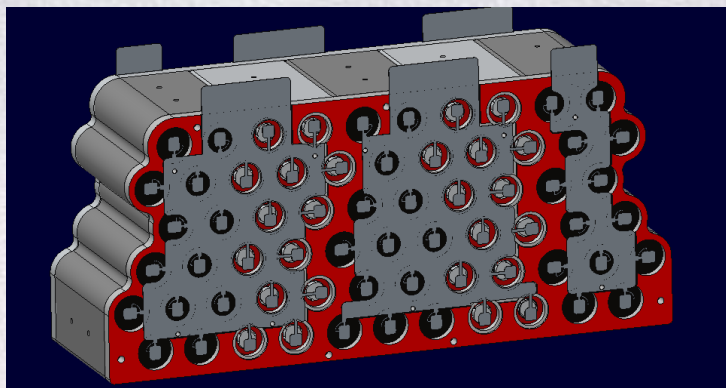


- With 12.41 Wh/cell, cell brick assembly achieves **191 Wh/kg**
  - Assuming 12.41Wh per cell
- Design has 1.4 parasitic mass factor
  - Cell mass x 1.4 = Brick mass

Mass Distribution

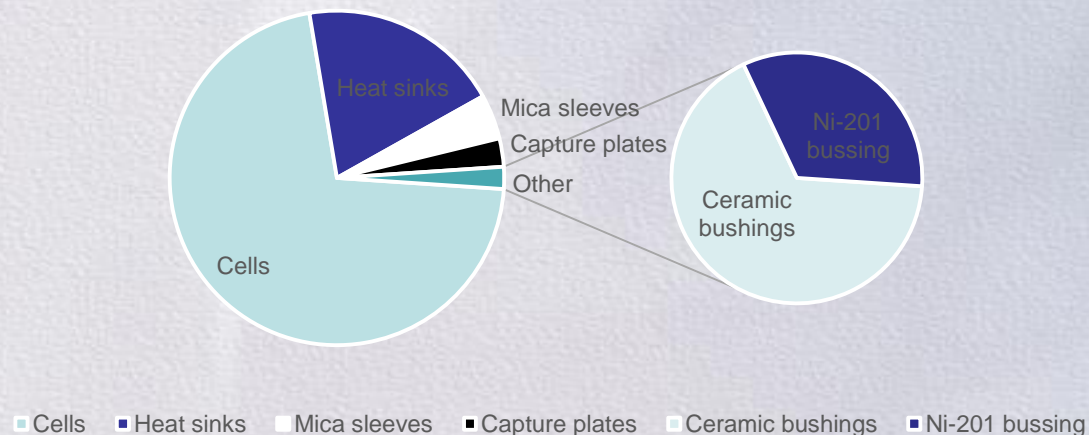




# Attempts to Drive TR with Cell Bottom Heater Fails

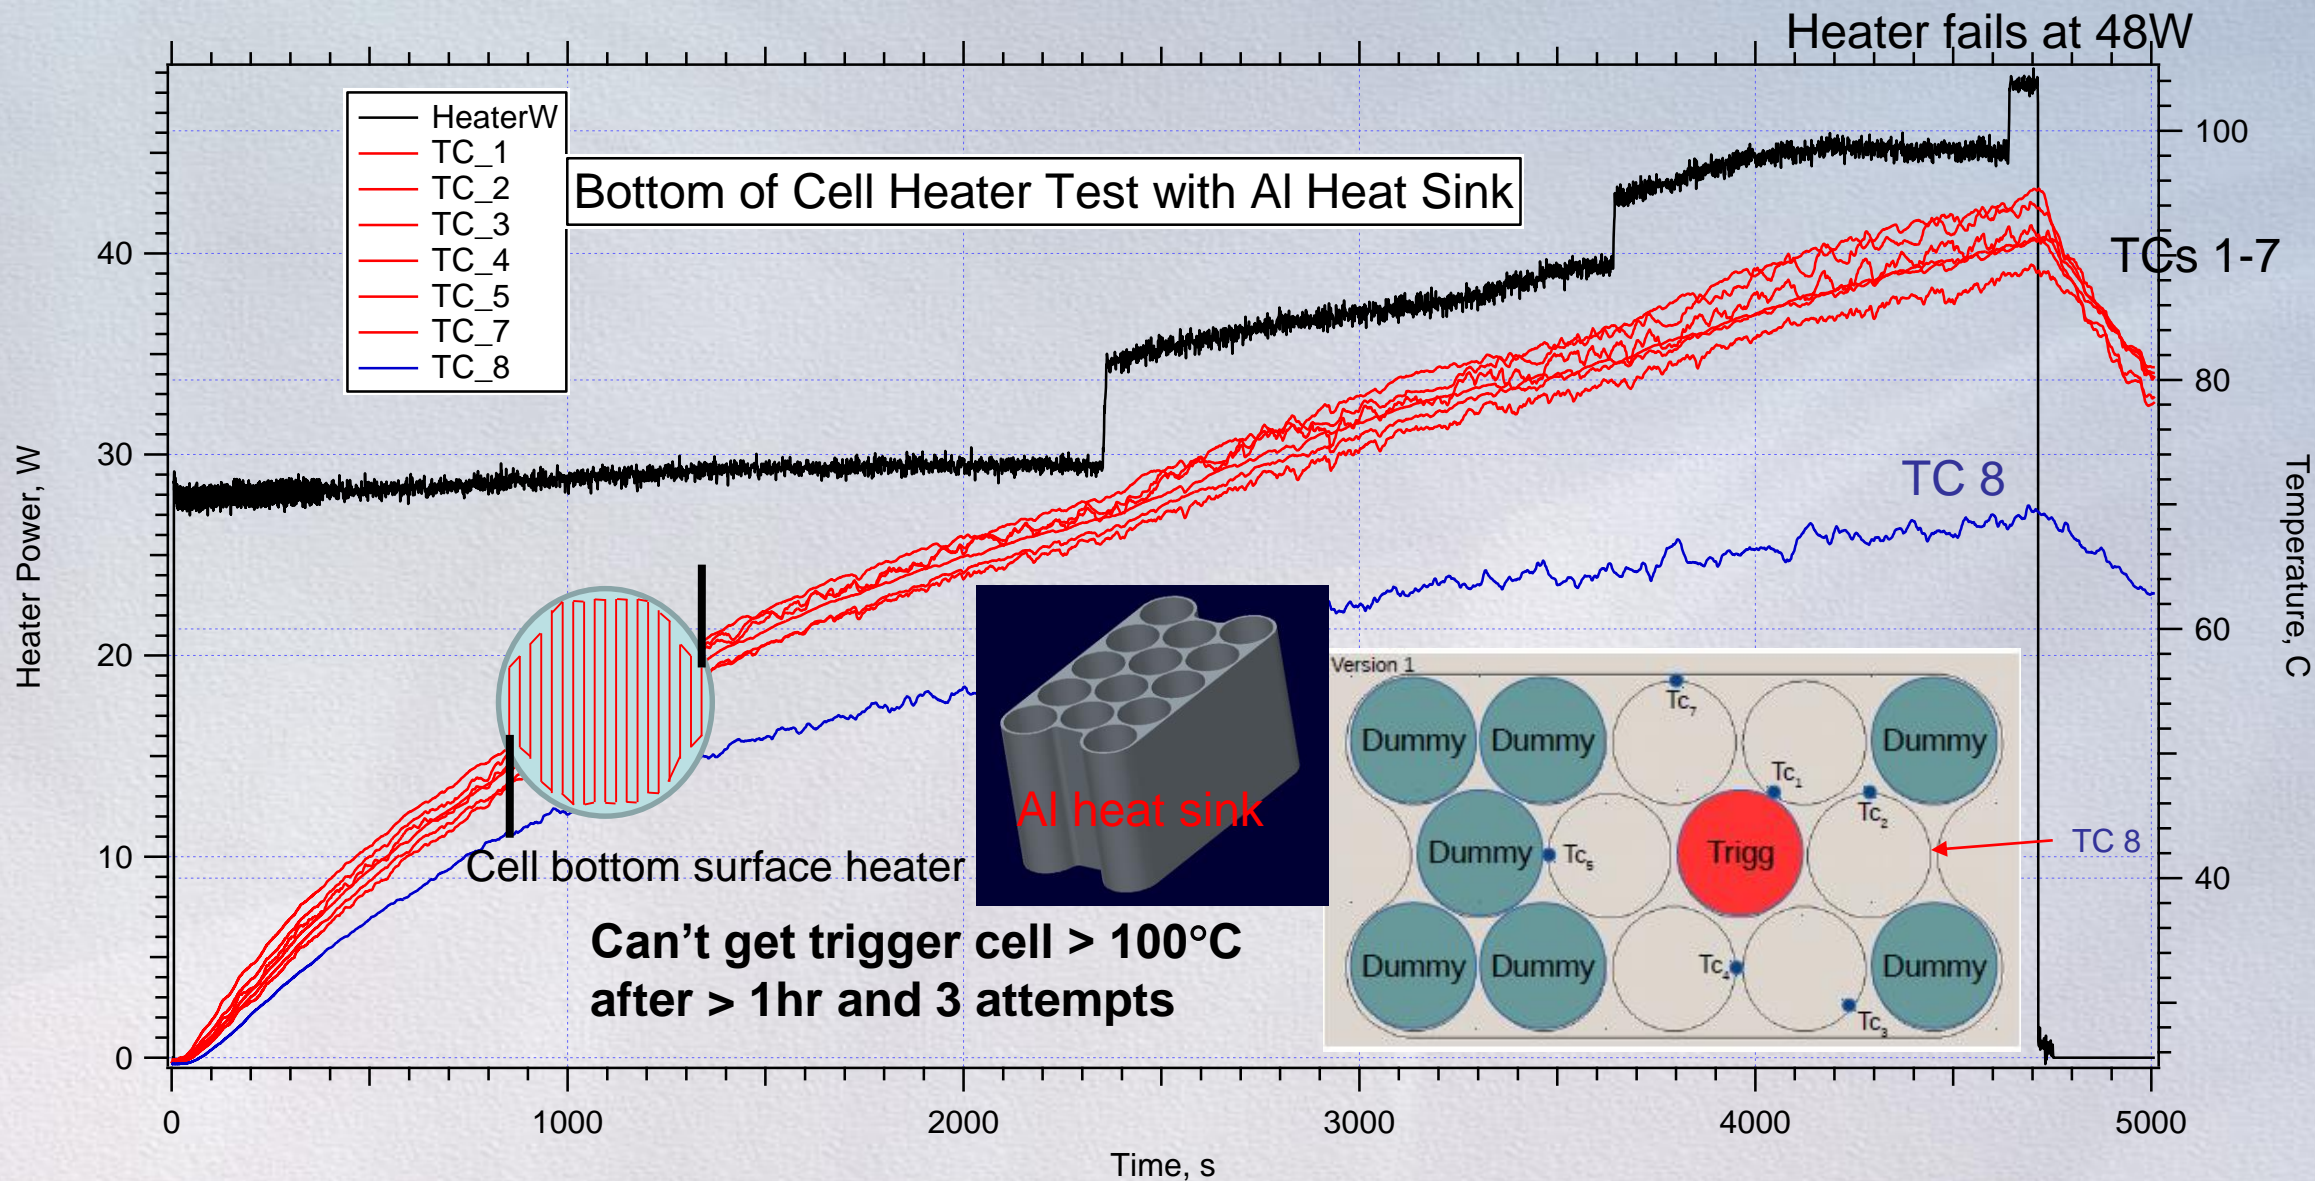



# Metallic Interstitial Heat Sink is Effective

- Cell can isolated with mica paper sleeves and very small air gap
- Heat sink spreads heat more quickly through multiple layers than through mica and onto cells
- Heat from trigger cell is quickly dispersed and shared among more cells


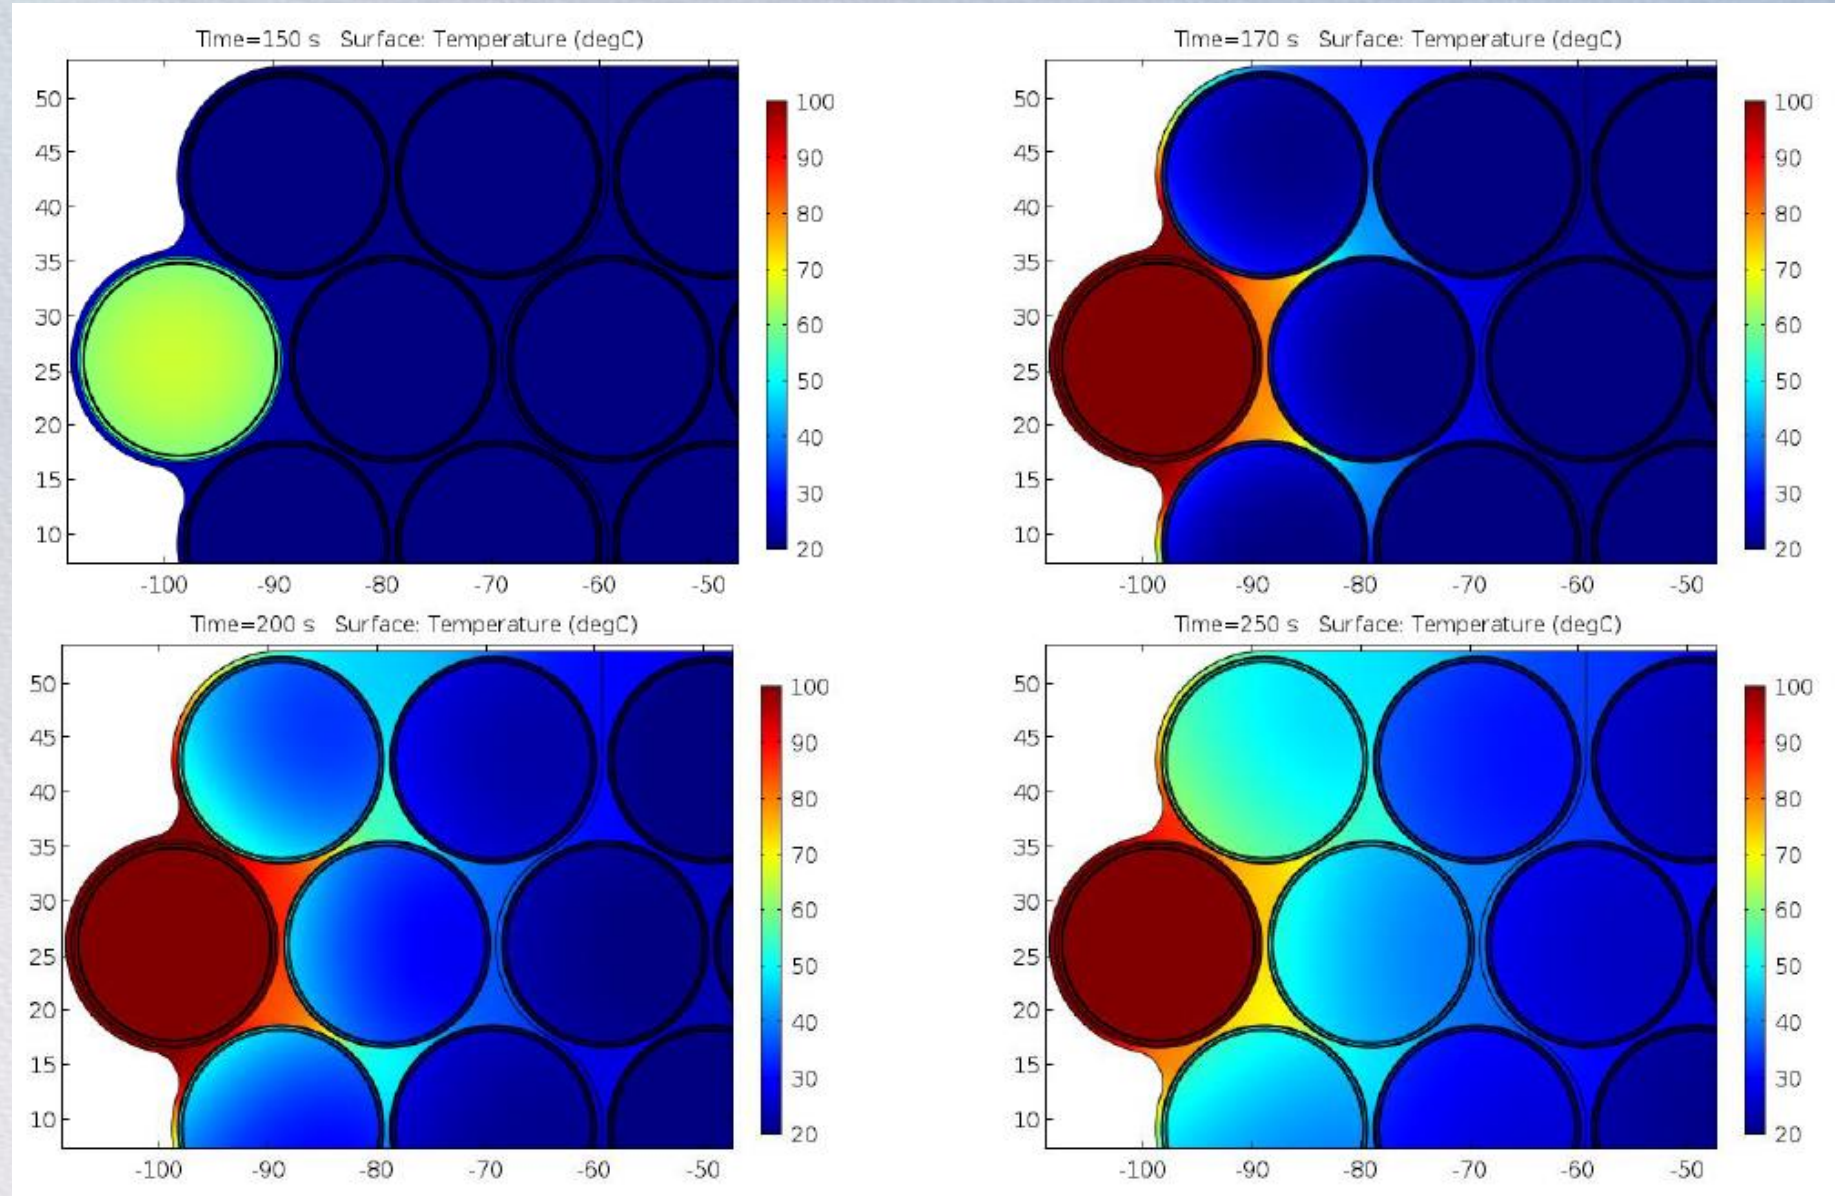


Graphic and analysis courtesy of Paul Coman



# NREL/NASA ISC Device Design

25

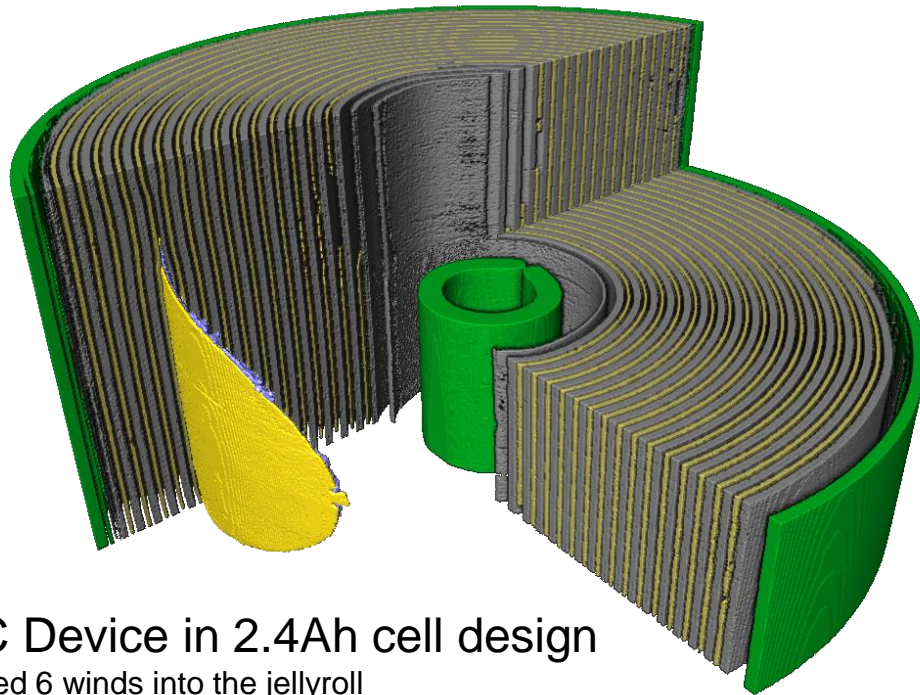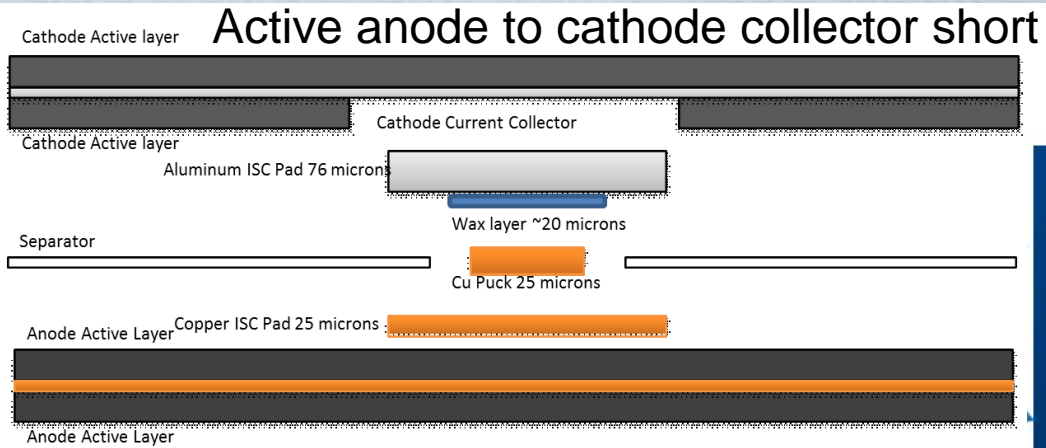


ISC Device in 2.4Ah cell design

Placed 6 winds into the jellyroll

5 mm

Tomography credits: University College of London

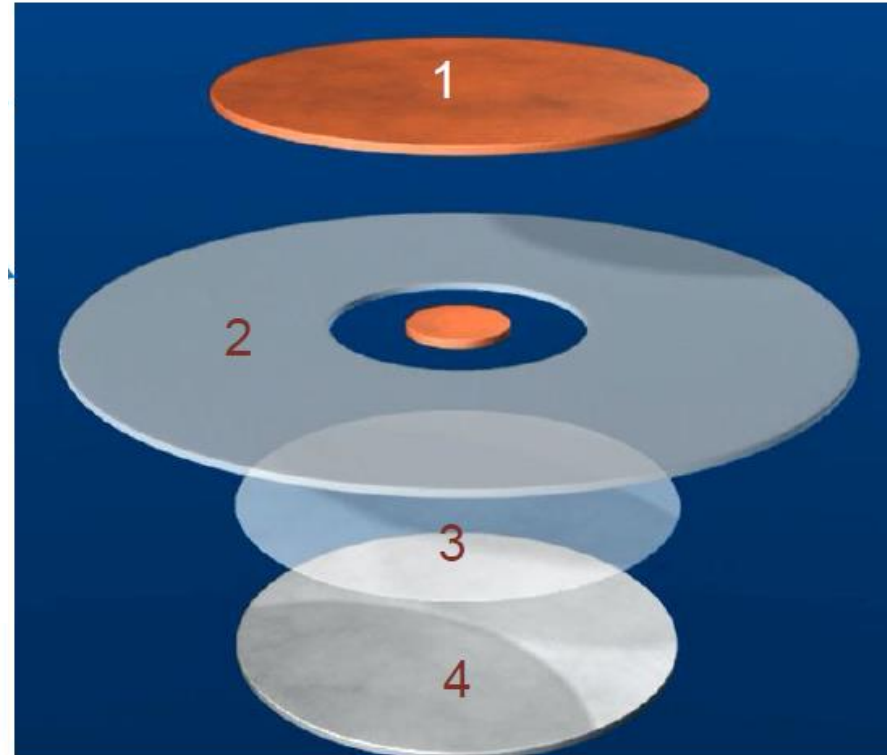

Graphic credits: NREL

Top to Bottom:

1. Copper Pad
2. Battery Separator with Copper Puck
3. Wax – Phase Change Material
4. Aluminum Pad

2010 Inventors:

- Matthew Keyser, Dirk Long, and Ahmad Pesaran at NREL
- Eric Darcy at NASA

US Patent # 9,142,829  
awarded in 2015

Wax formulation used  
melts ~57°C


Thin (10-20  $\mu\text{m}$ ) wax  
layer is spin coated  
on Al foil pad



2016 Award Winner




# Single Cell TR – Moli 2.4Ah with ISC Device

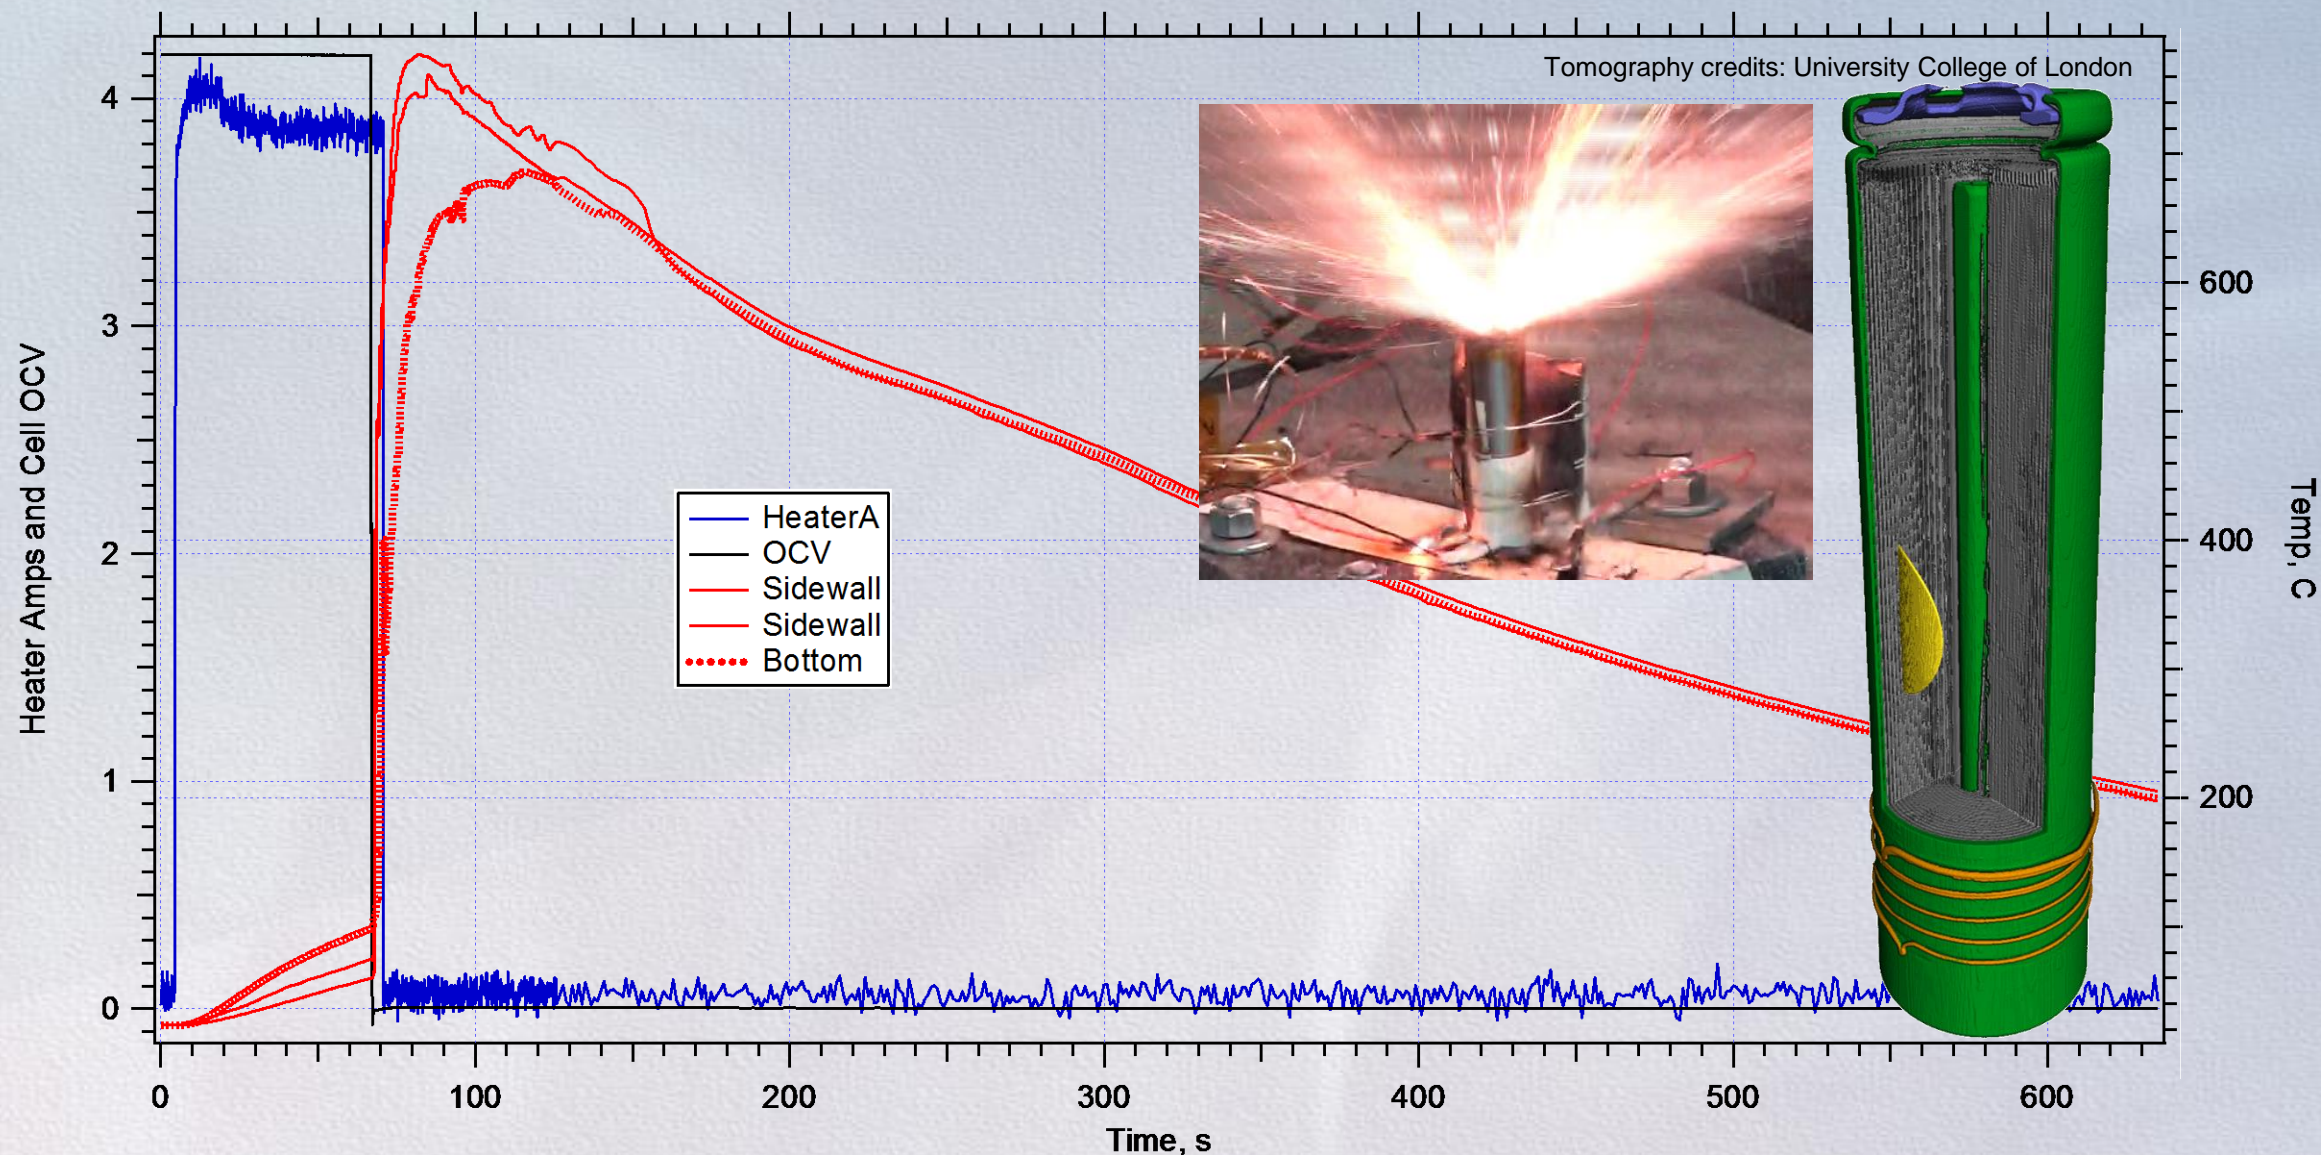


Open air test with cell charged to 4.2V and with TCs welded to cell side wall (2) and bottom (1)



# CT Images of ISC Device

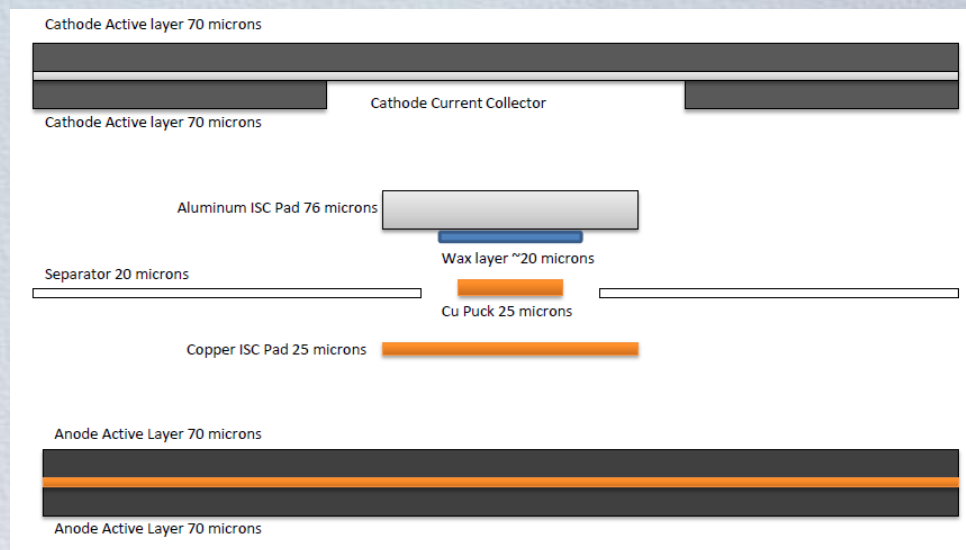

Clearly shows that active material hole boundaries are much wider than the device

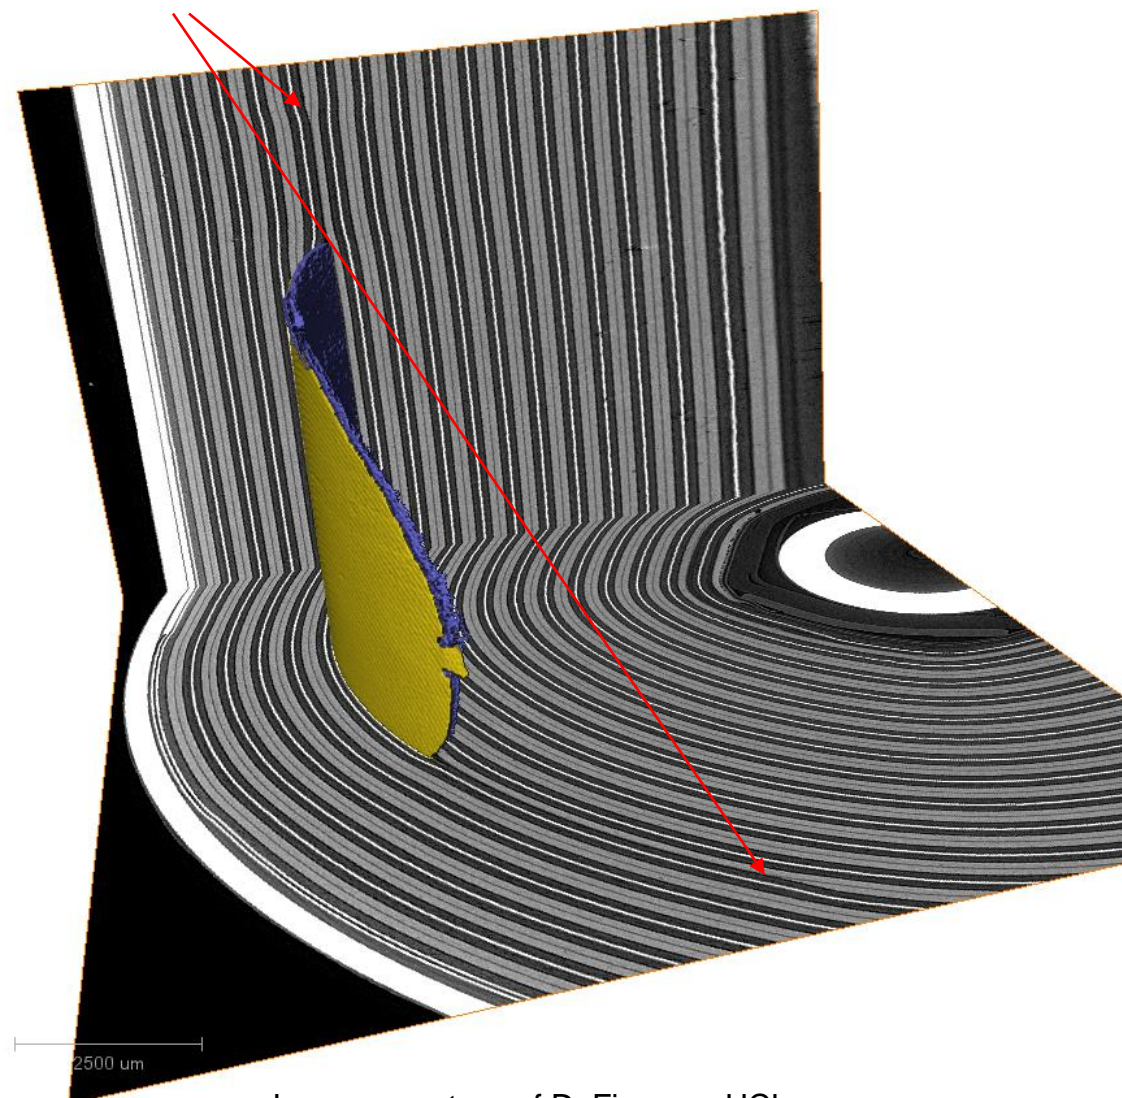

Cu puck  
Al pad removed for clarity


Images courtesy of D. Finegan, UCL



# CT images (cont.)

Misalignment of Cu and Al pads creates stress zones on the separator and could explain the damage initiation at the ISC device edge in some videos


Image picks up tweezer marks during fabrication on the Cu puck

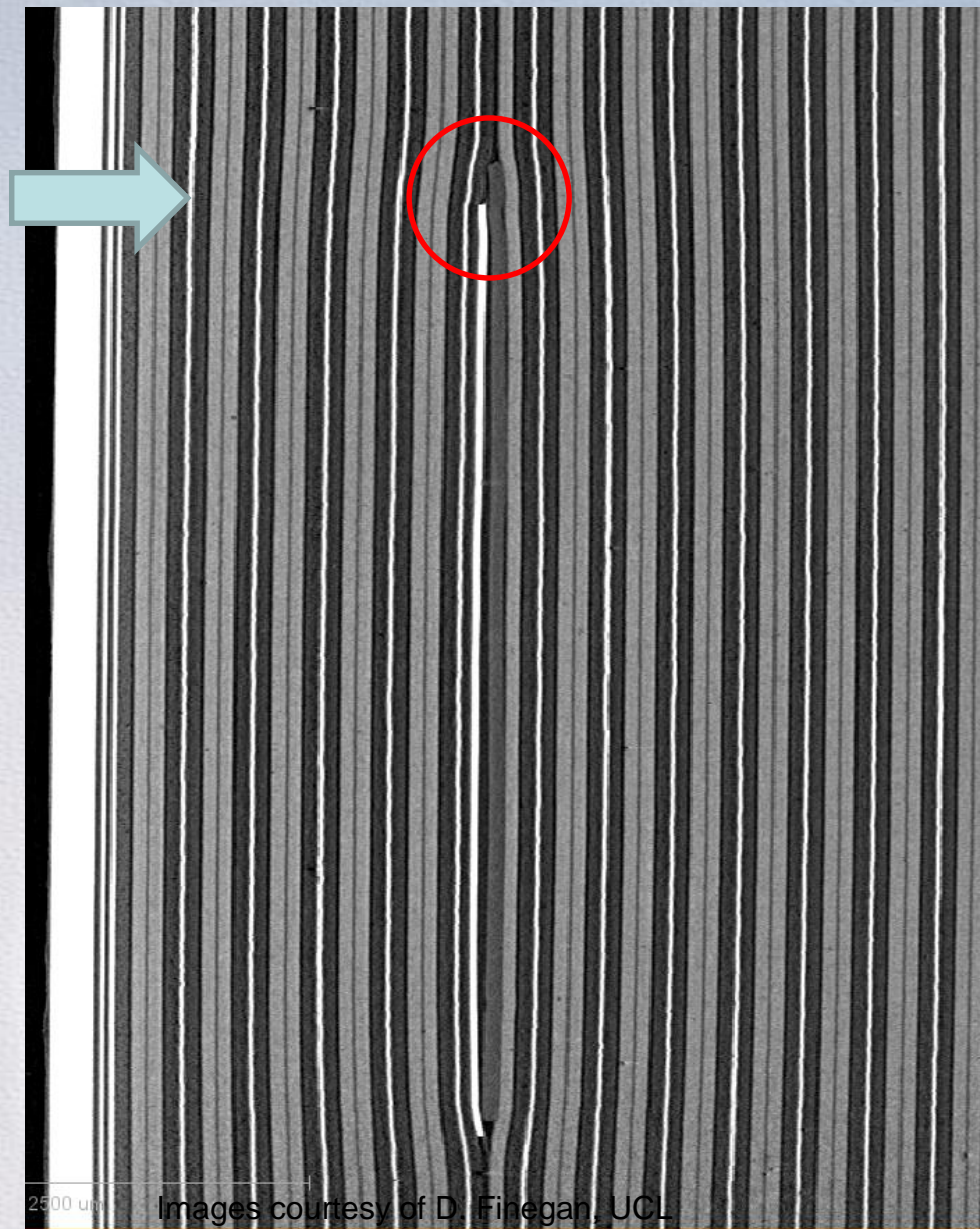

Images courtesy of D. Finegan, UCL




## 2.4Ah 18650 with ISC device

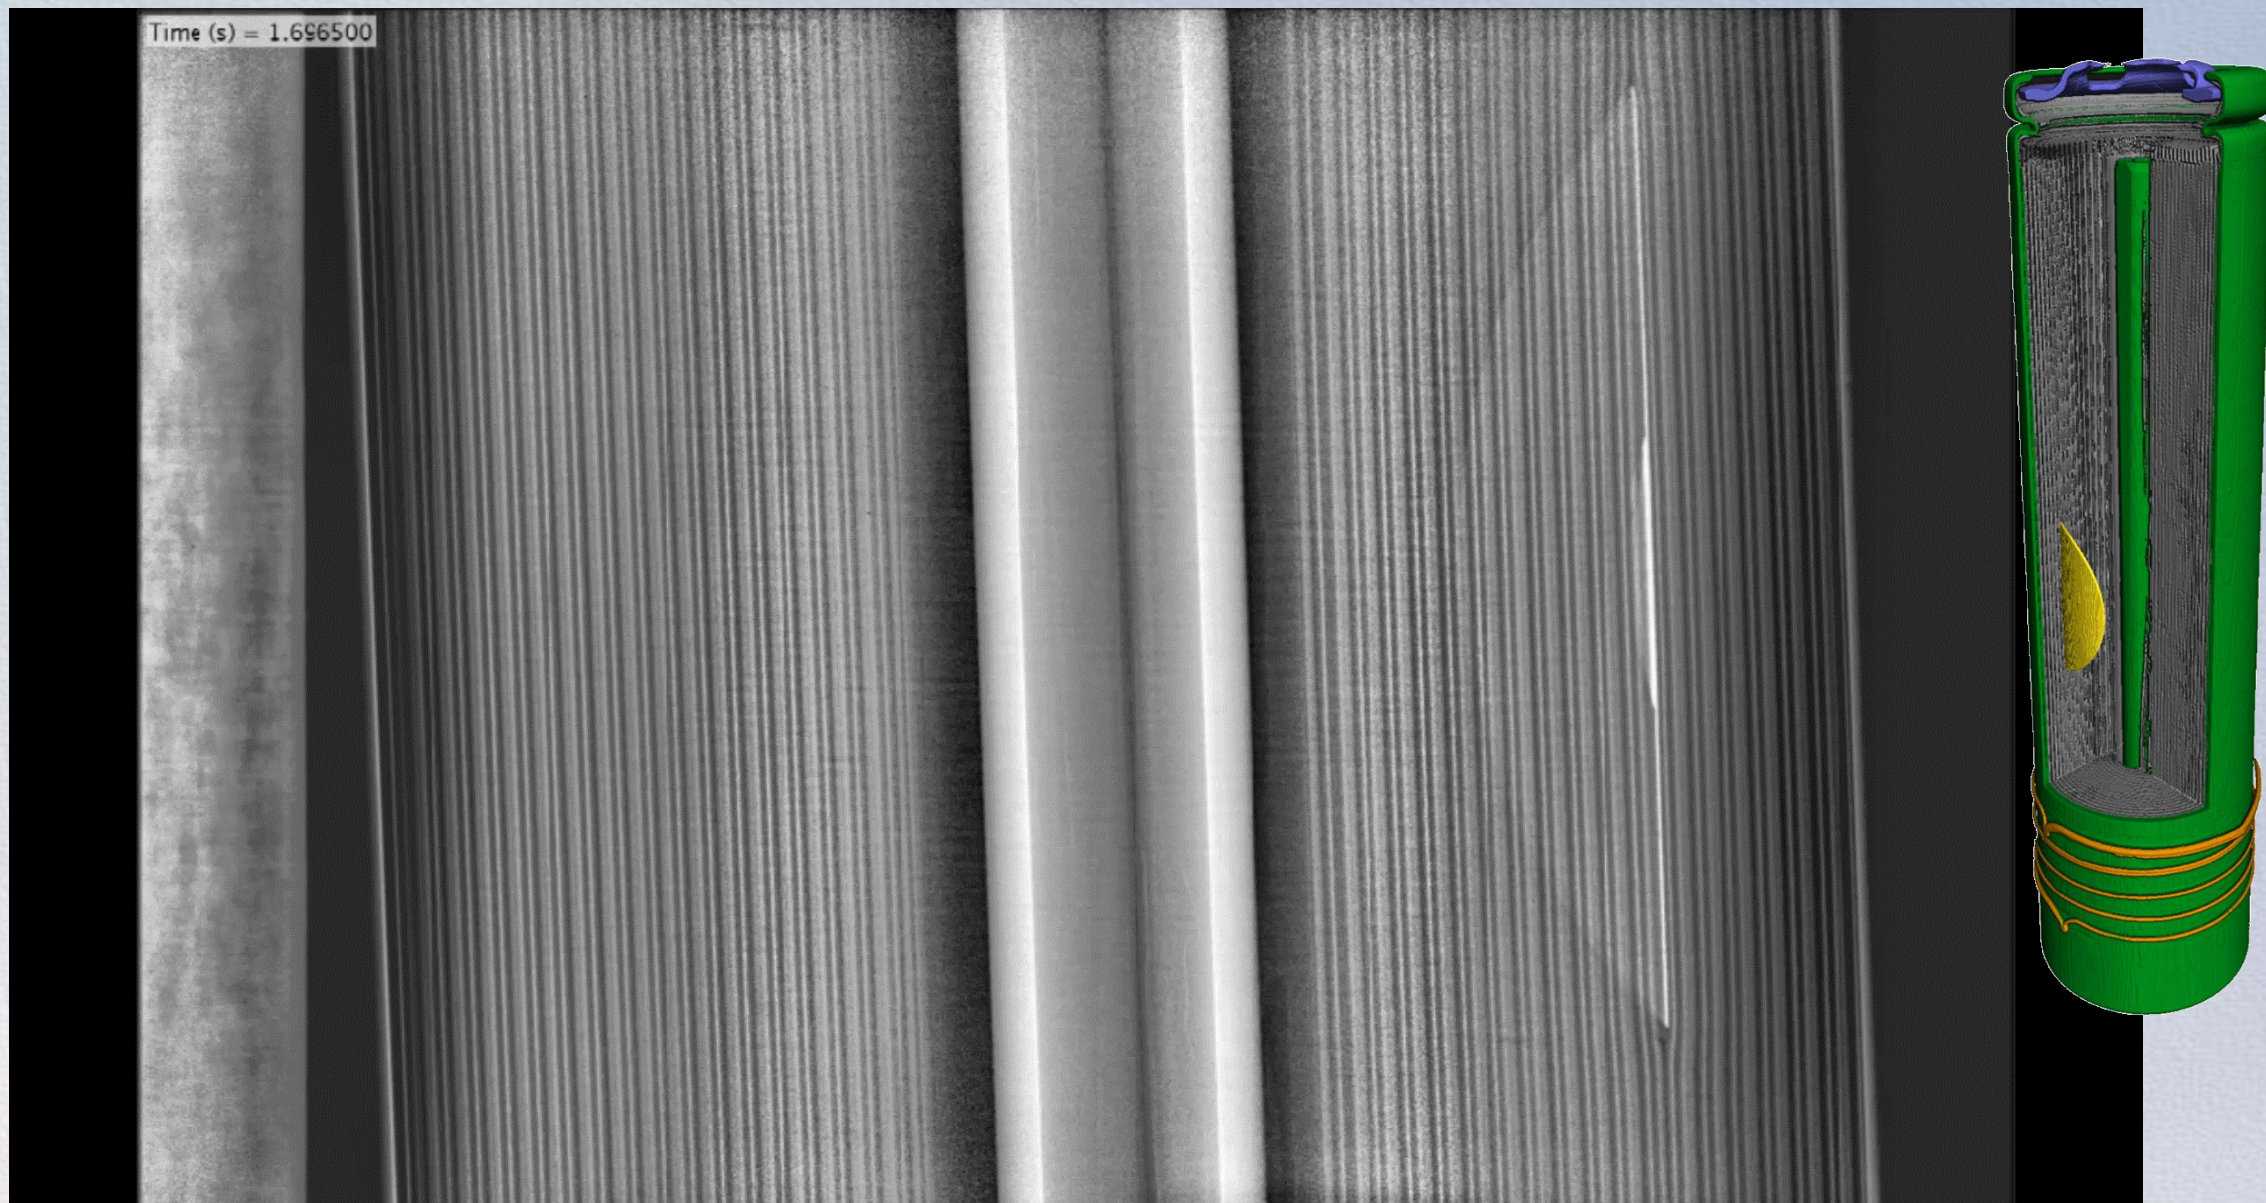




## 2.4Ah Cell with ISC Device – JR Ejection

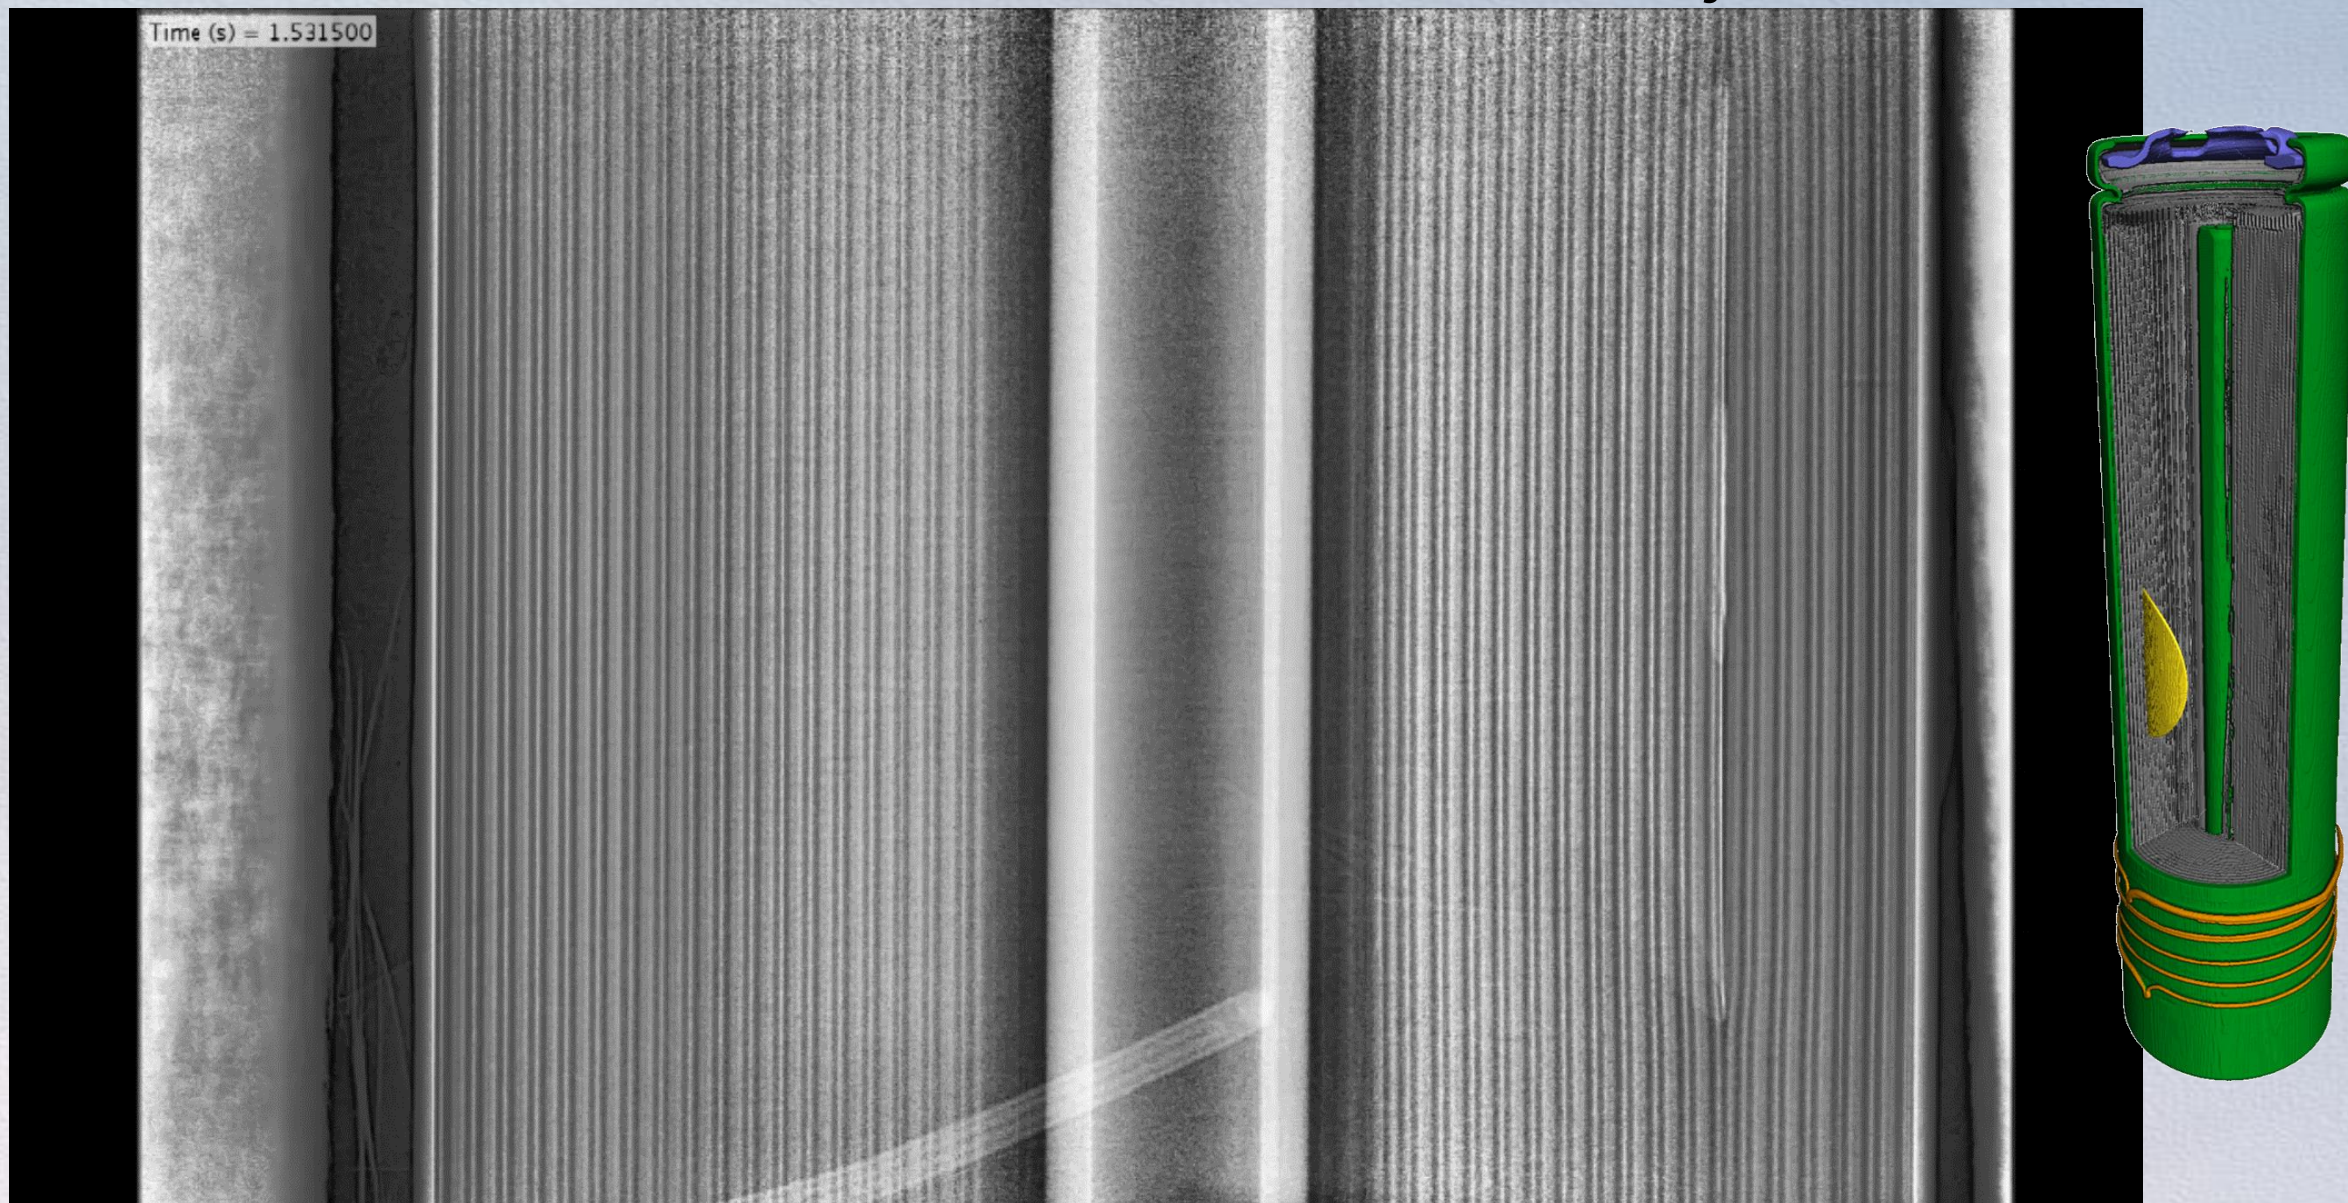





# Full Scale Battery TR Test – MoliJ ISC Cell

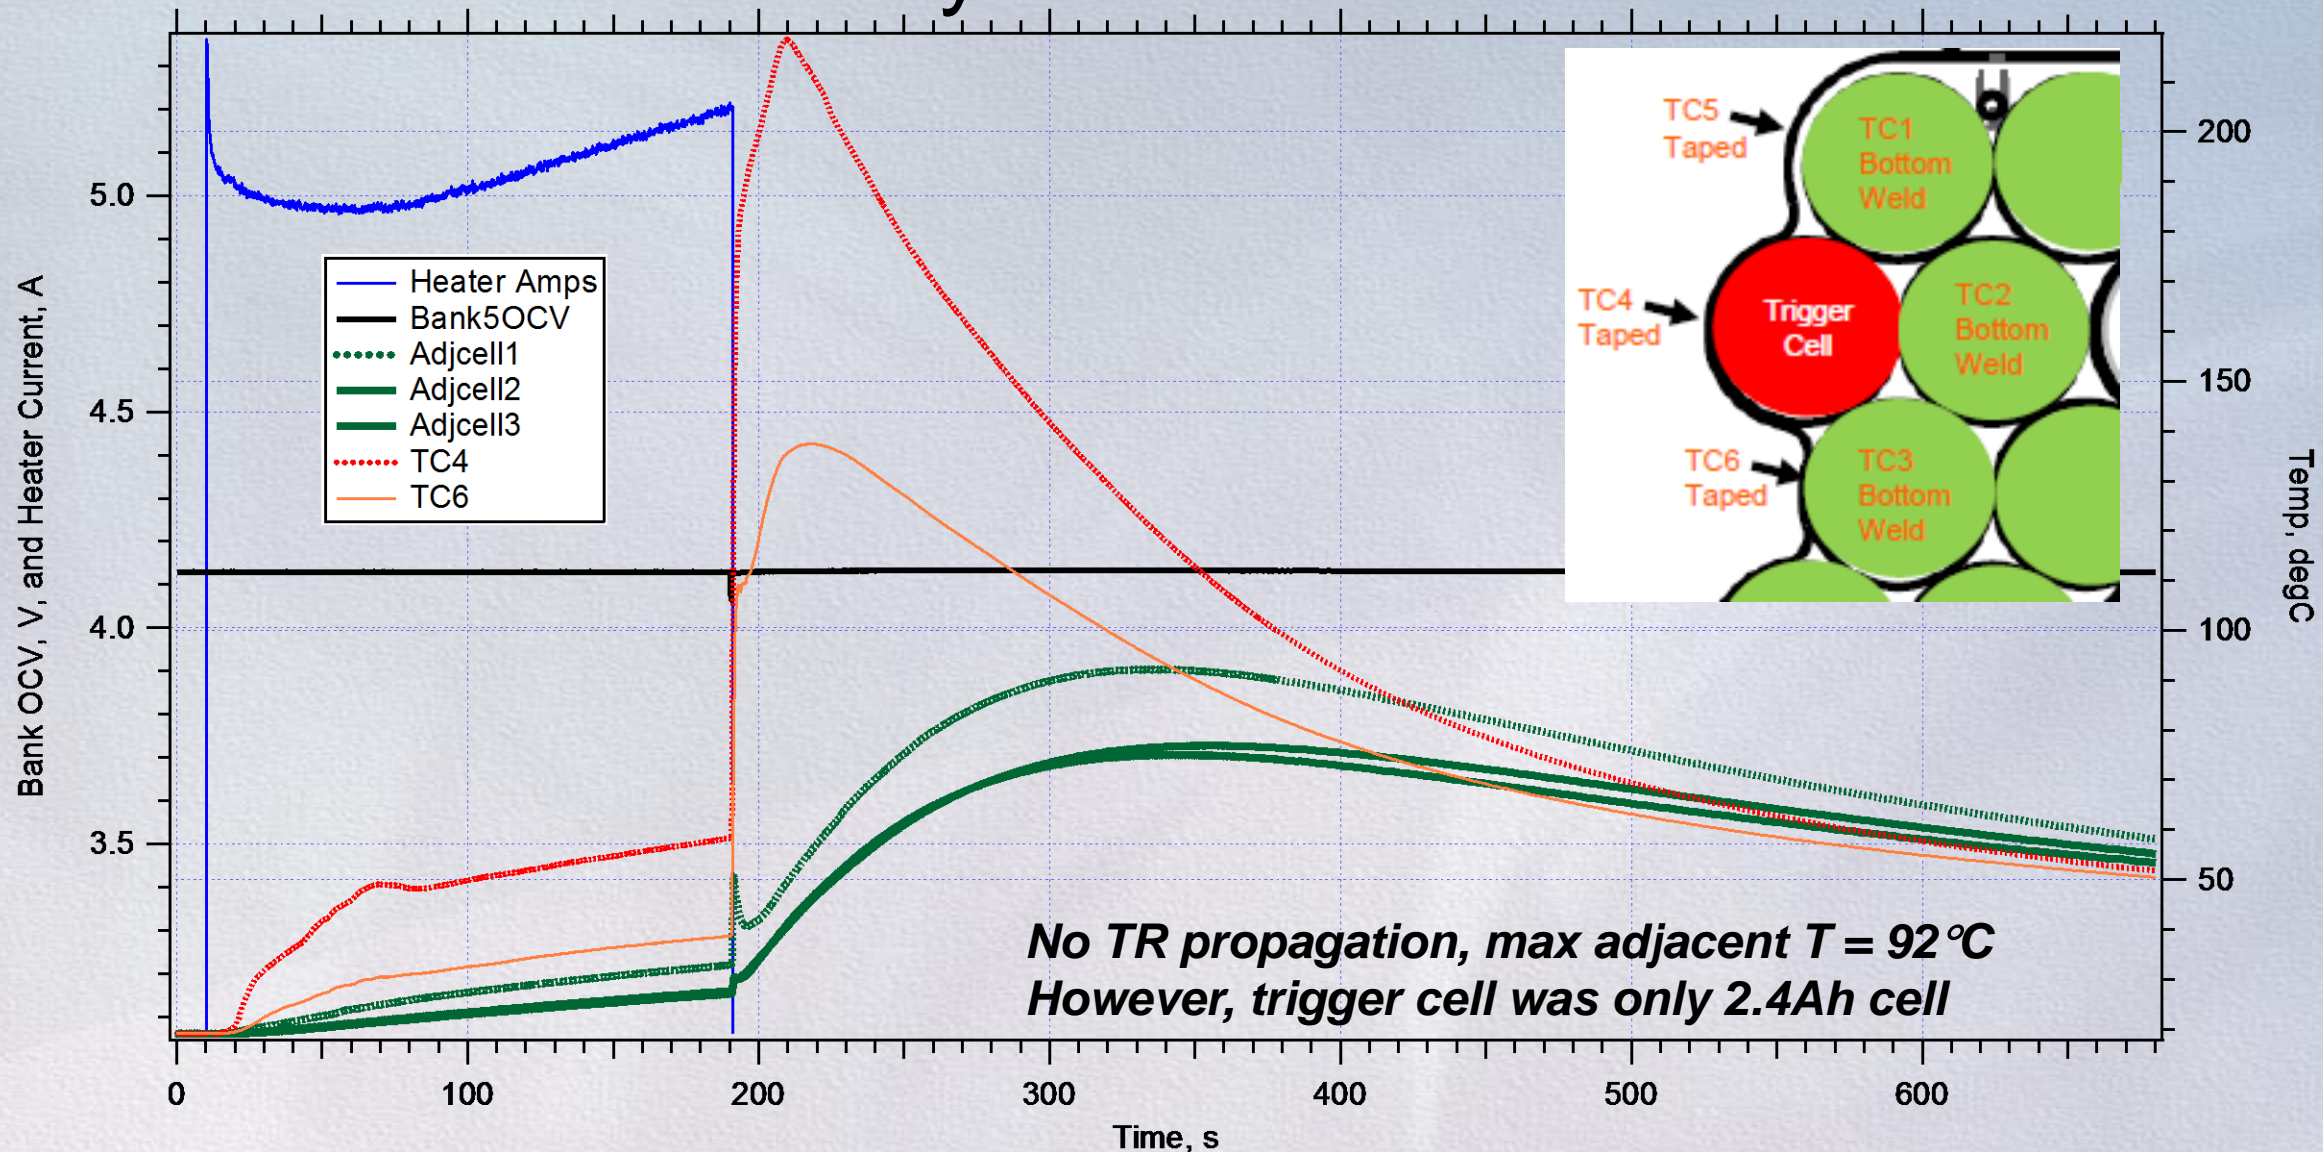


Heater power  $\sim 42\text{W}$  for 180s. Onset of TR (OTR) occurs 180s after power on and coincides with trigger bank OCV dip. Adjacent cell1 has  $\Delta T = 58.9^{\circ}\text{C}$  to max of  $92.0^{\circ}\text{C}$ , while adjacent cells 2 & 3 have  $\Delta T = 48^{\circ}\text{C}$  to max of  $76.0^{\circ}\text{C}$




# No TR Propagation, Only Smoke Exits Battery

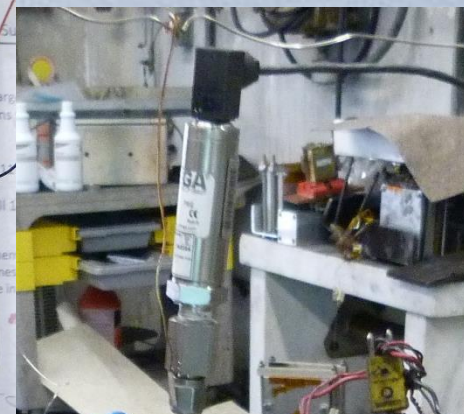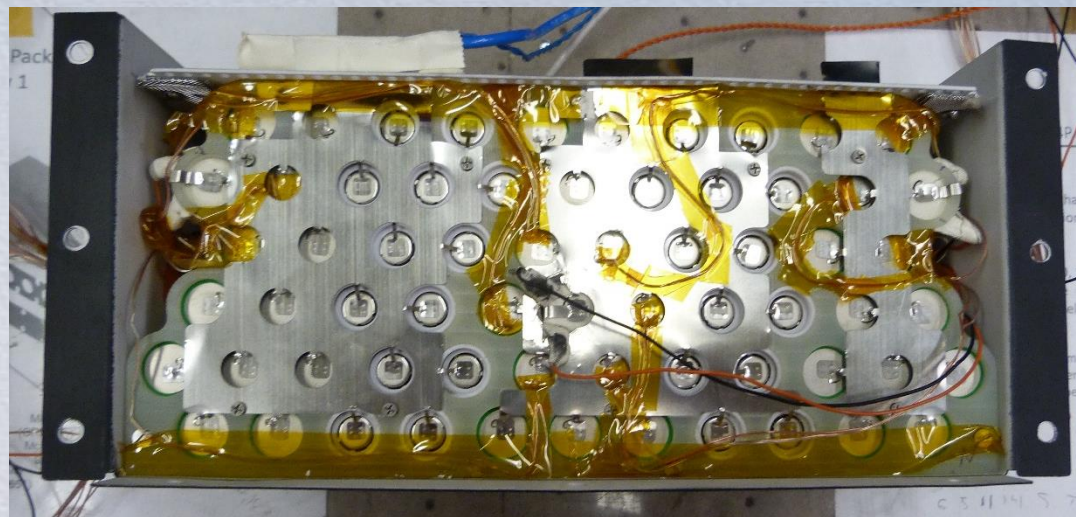

Mesh 40 & 30 steel screens arrest flames and sparks

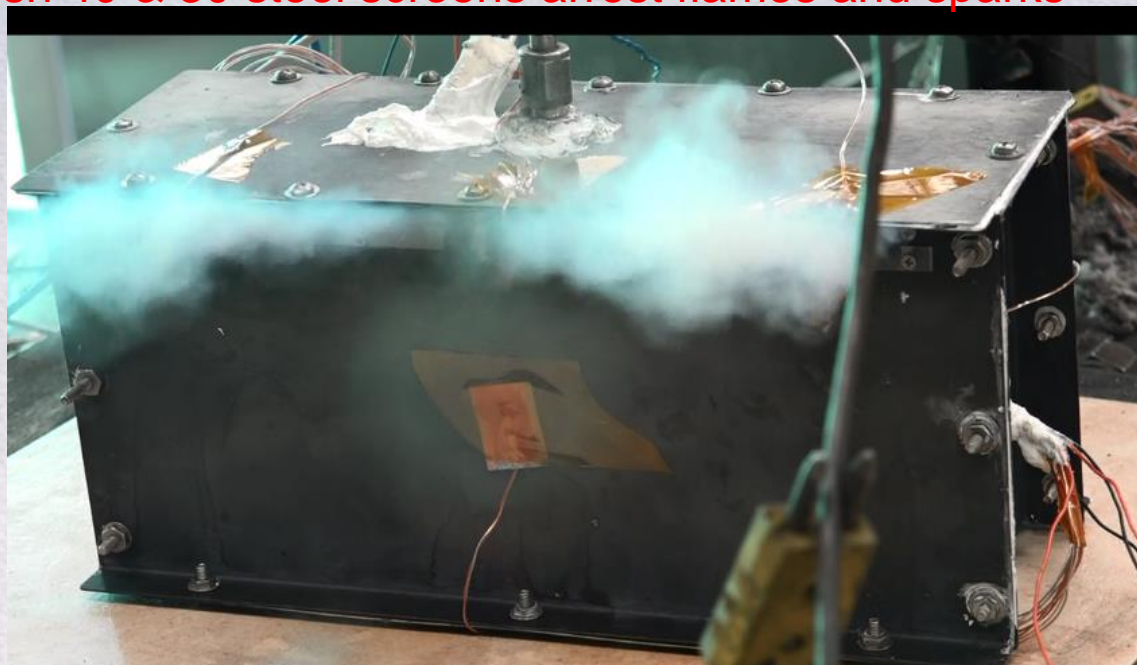


*However, trigger cell was only 2.4Ah cell*

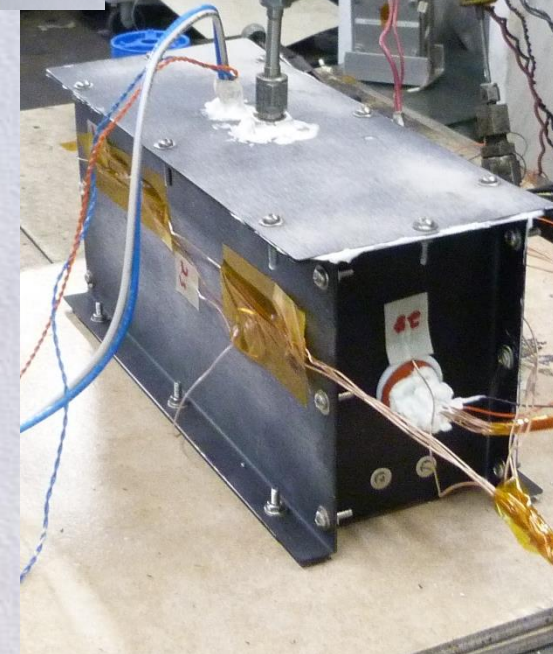



# 1<sup>st</sup> Test with 3.4Ah ISC Device Trigger Cell

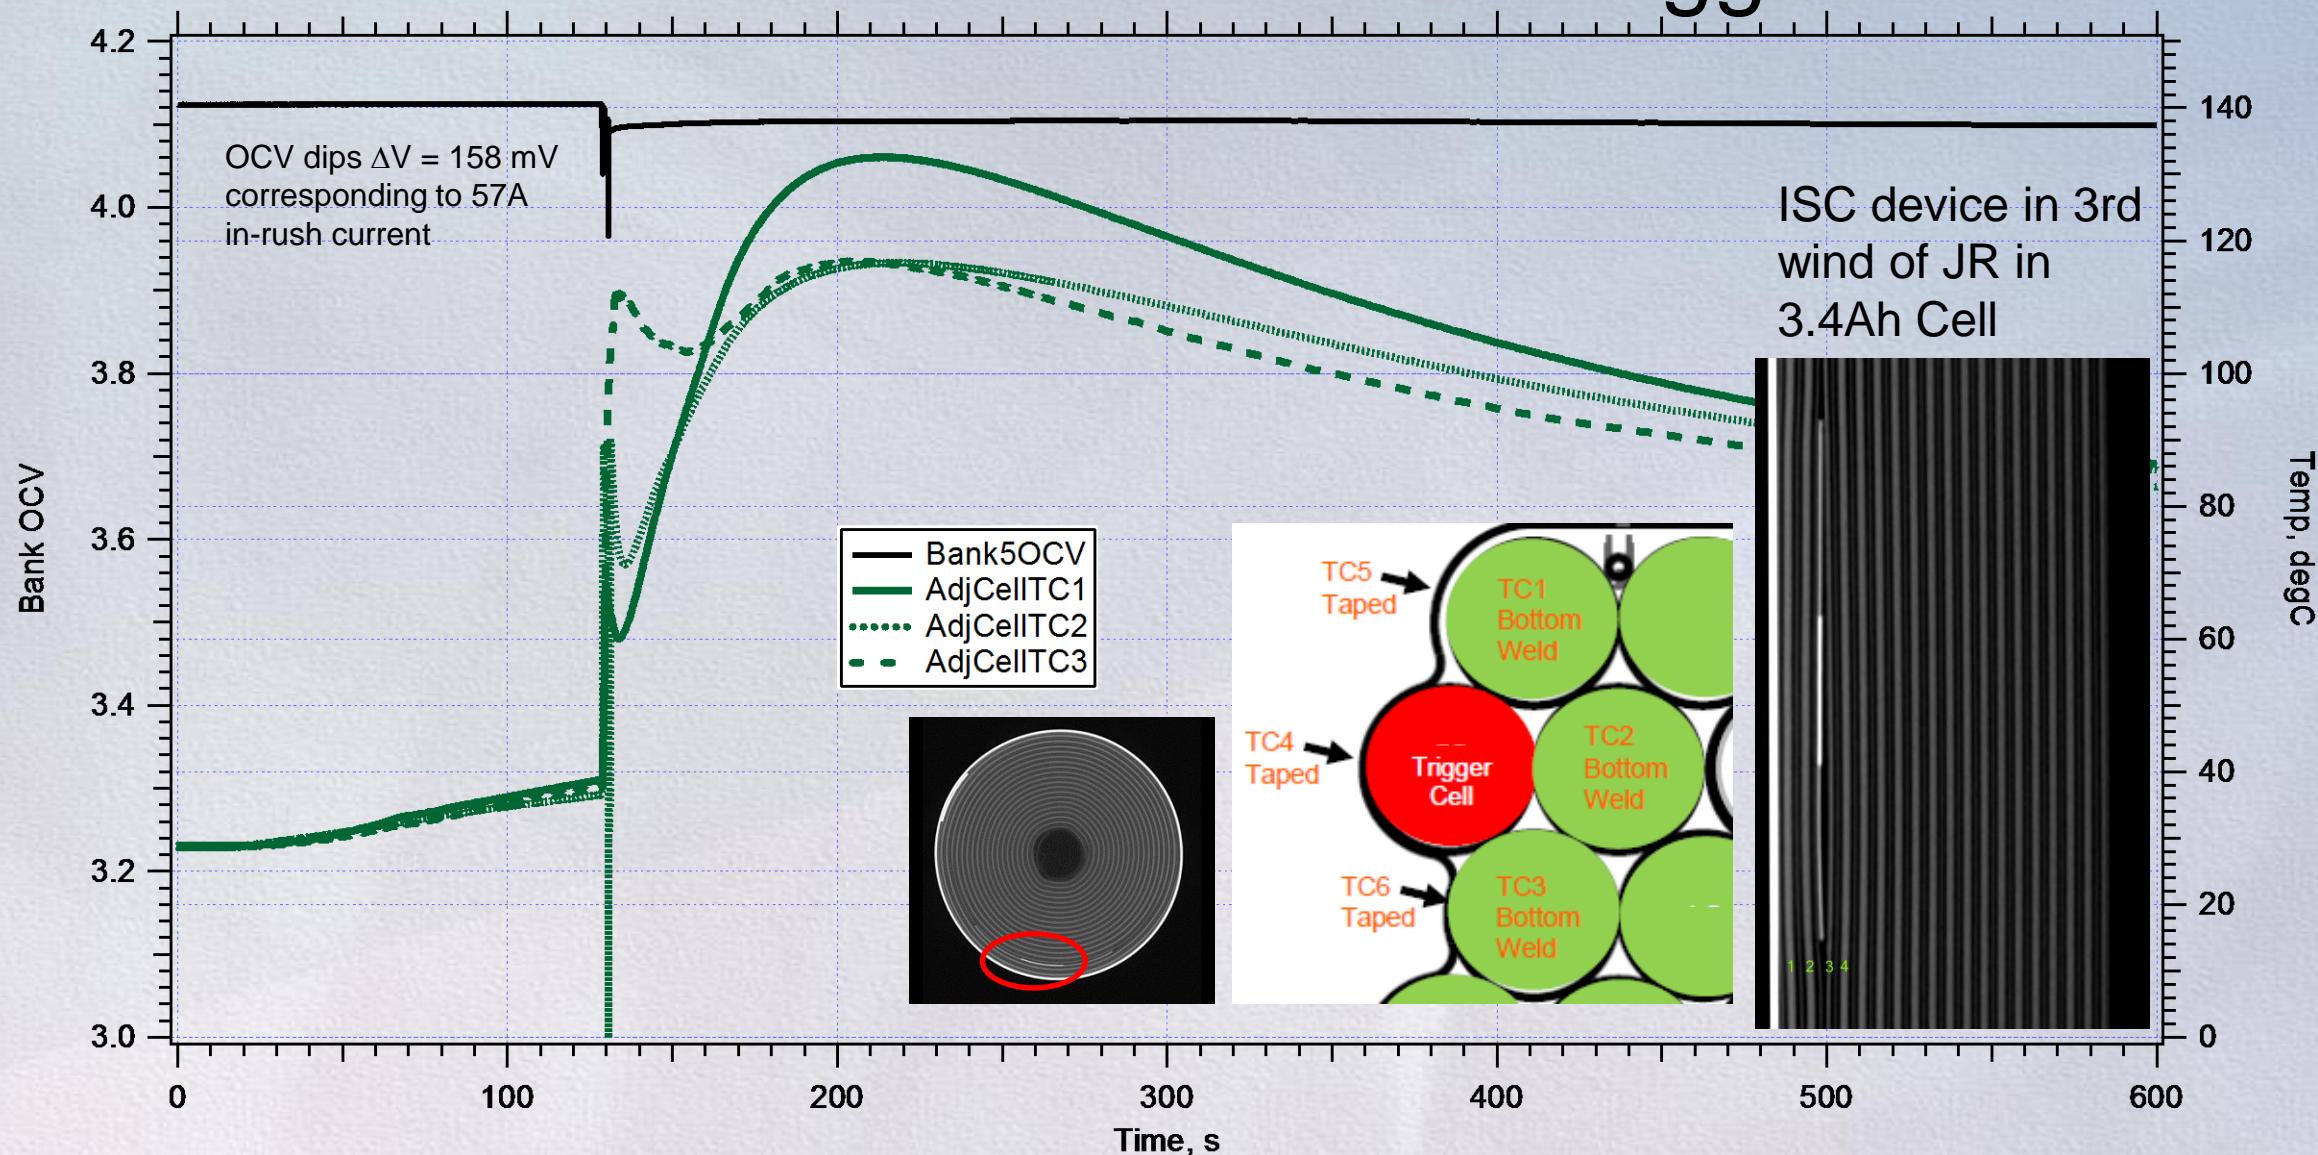



Adjacent cell temperatures TC1, TC2, and TC3 peak at **133°C**, 117°C, and 117°C in 77-87s from onset temperatures of 39°C, 37°C, and 38°C for  $\Delta T =$  **94°C**, 77°C, and 78°C, respectively.



# No TR Propagation – Only Clean Smoke Exits Gore Vent

Flame arresting steel screens

**3.4Ah Cell with ISC device trigger location**

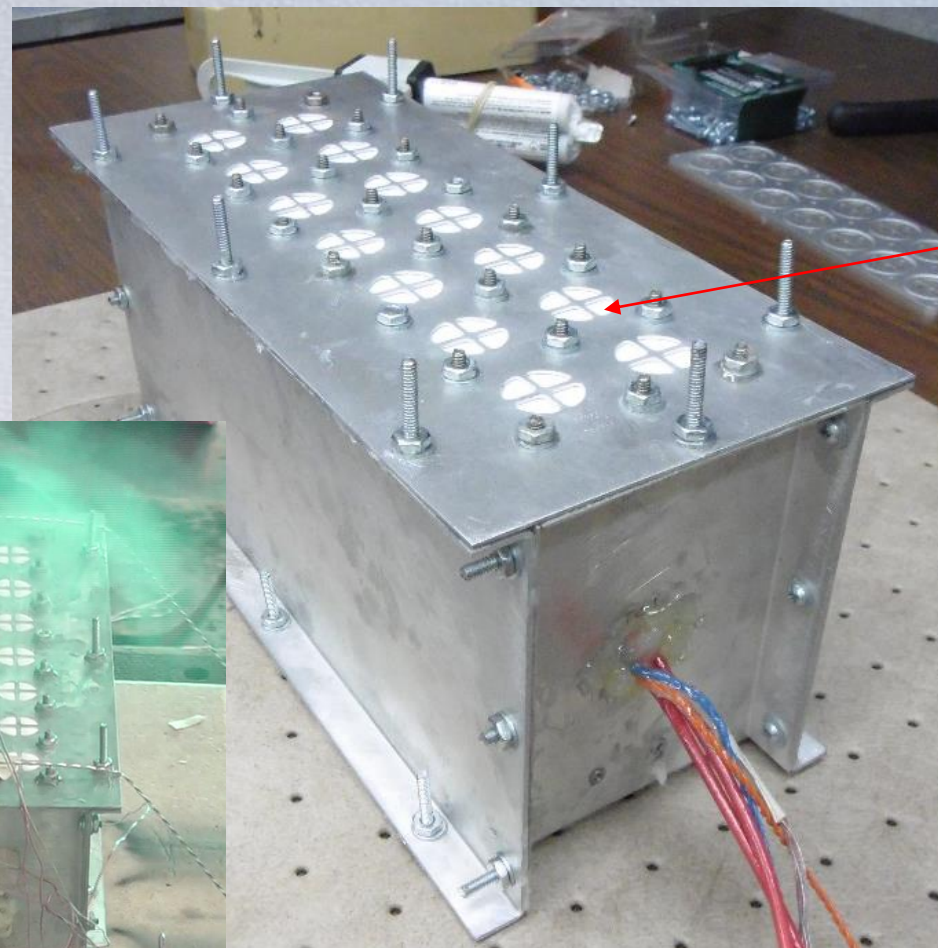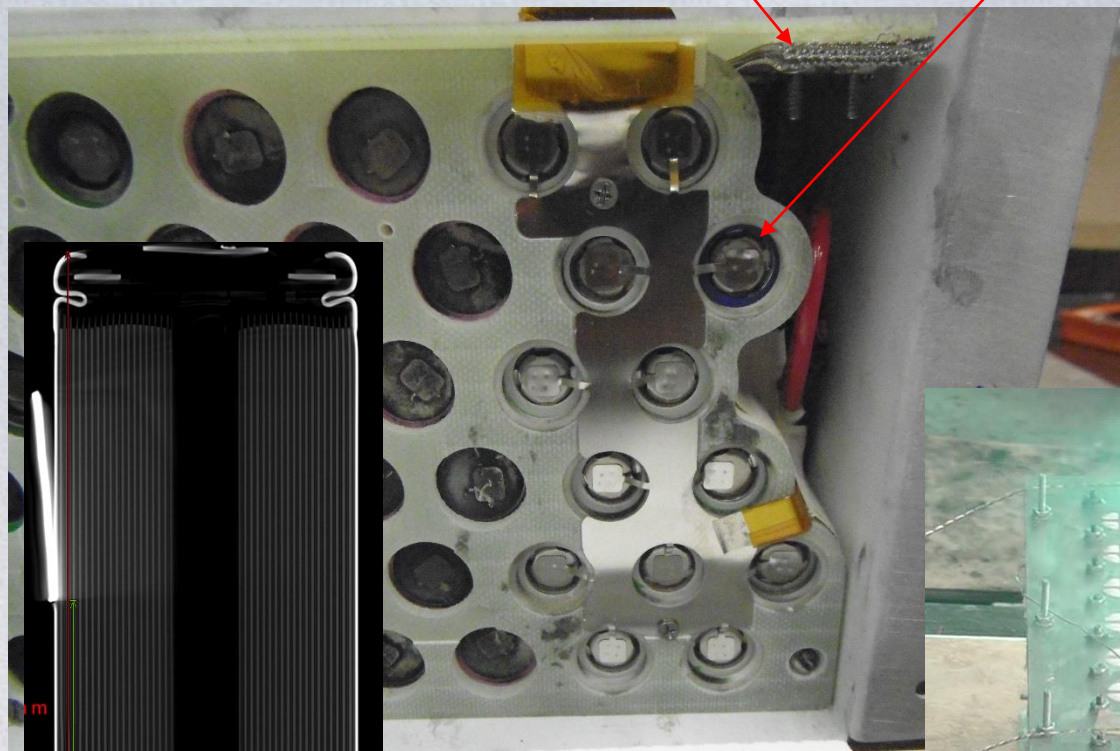

Gore fabric  
Vent design

3.4Ah cell with  
ISC device in 3<sup>rd</sup>  
JR wind

Battery bottom edge seal fails and relieves  
internal pressure at ~11.4 psig (0.77 bar)




# 3.4 Ah Trigger Cell Experienced a Side Wall Rupture

Trigger cell was a struggle to extract from heat sink.


The mica insulation was severely damaged adjacent to rupture

Cell	OCV (V)	Mass (g)
Trigger	0	17.161
1	3.474	46.801
2	0.336	46.691
3	0	46.671

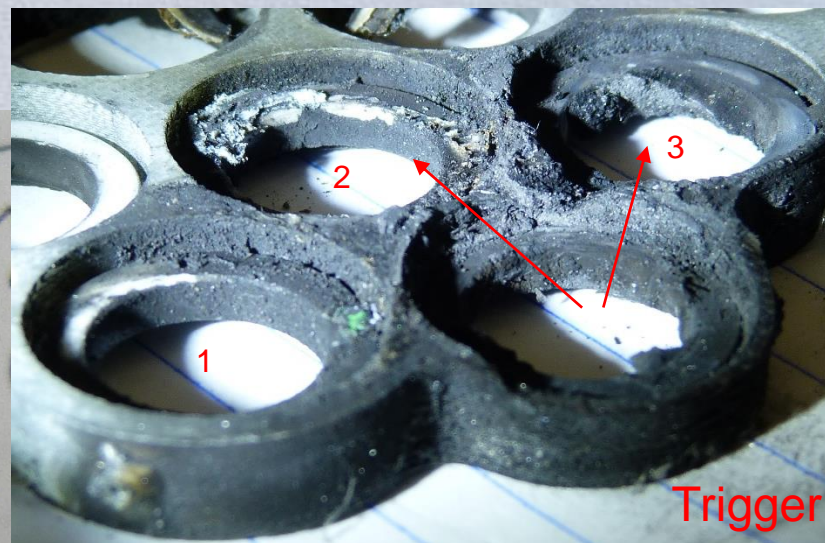





## 2<sup>nd</sup> Test with 3.4Ah ISC Trigger

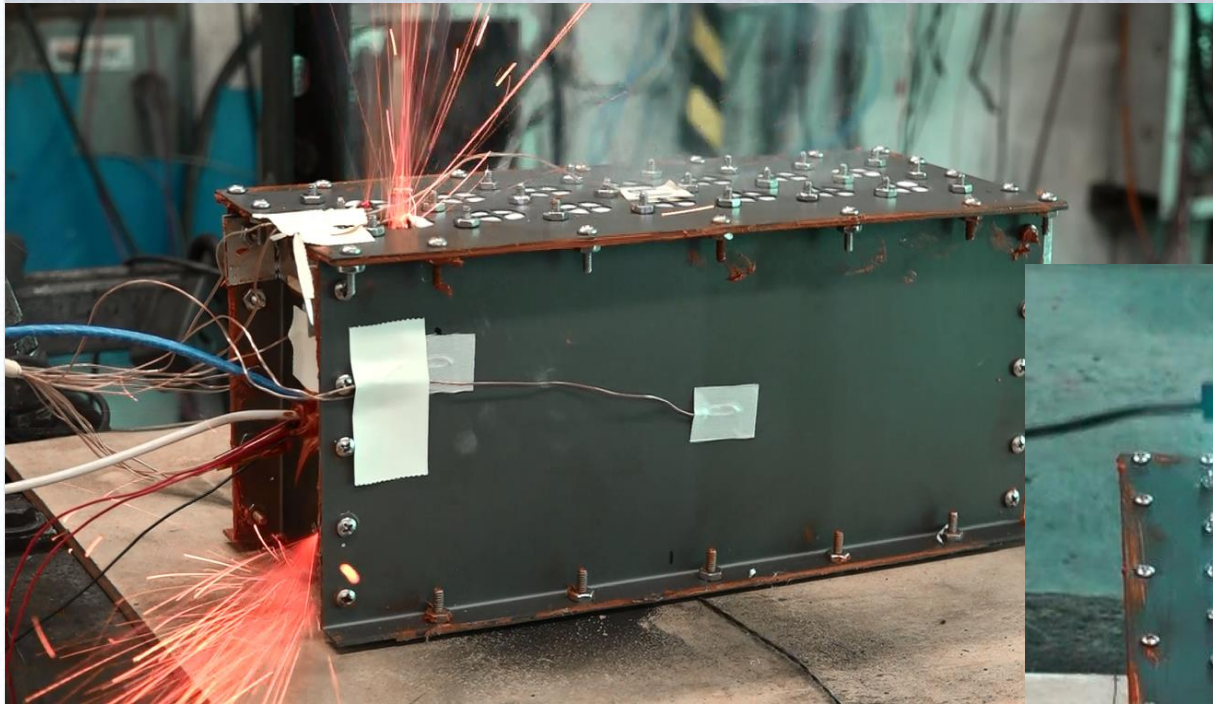

Flames exiting from top and sides of box, less than 1 second

Cell flame path was insufficiently tortuous and sparks burn through 2 Gore vents

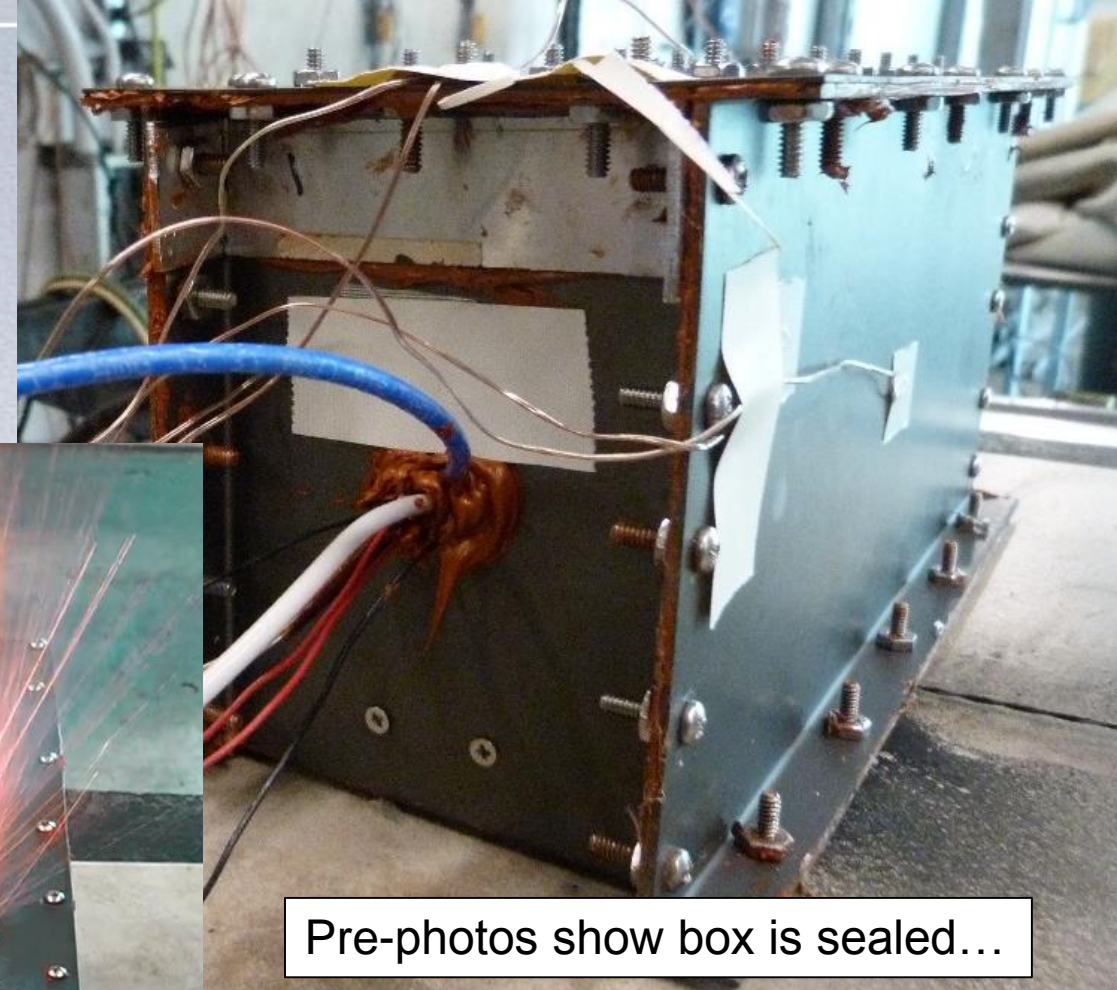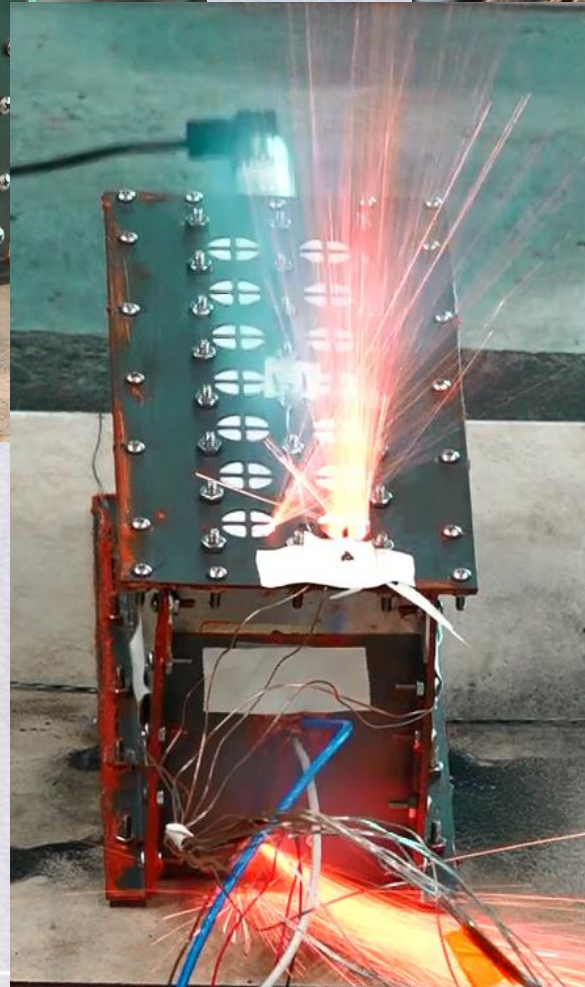


Pre-photos show box is sealed...

Not enough sealant on screw and hole



# 2<sup>nd</sup> Test 3.4Ah ISC Trigger Cell – OCV, Heaters, & Interior Temps

37

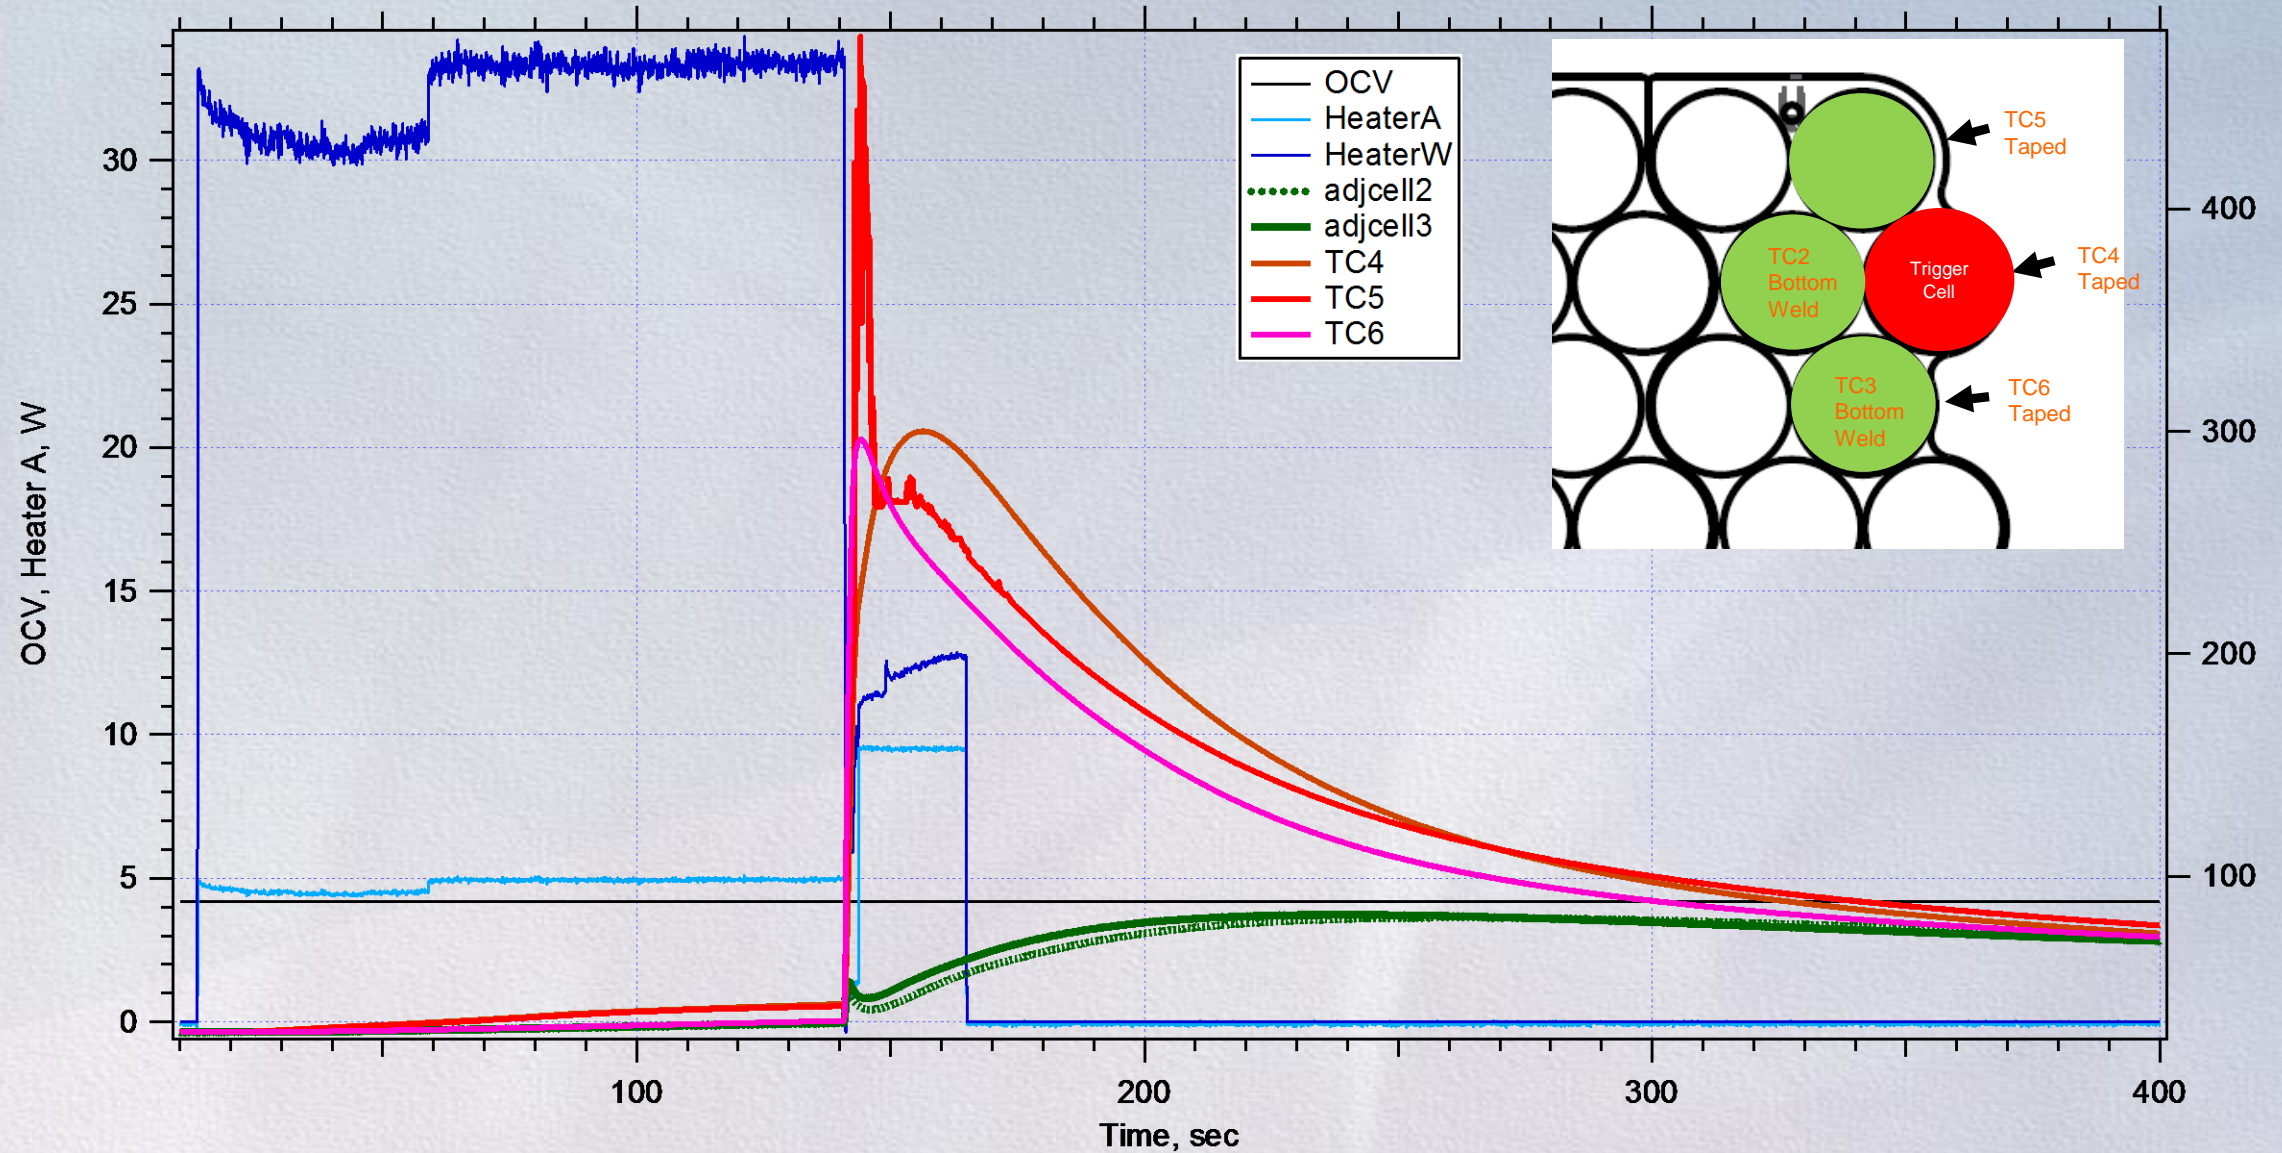

Adjacent cell max temperatures < 83°C



# Post-Test Photos – Trigger Cell



Post-Test Mass: 25.3g

Bottom breach

Spin groove is stretched



# Findings from 2<sup>nd</sup> Test with 3.4Ah ISC Trigger Cell


- ISC device in 3.4Ah 18650 cell triggered in 127 seconds with bottom heater at 32W average
  - Very similar initiation time (1<sup>st</sup> run was in 119s)
  - Very similar biasing of adjacent cells (34-35°C) at onset of TR (1<sup>st</sup> run at 37-39°C)
- No propagation of TR
  - Despite bottom rupture of trigger cell, which damaged the G10/FR4 negative capture plate
  - Reusing the same heat sinks from the first test – undamaged after both tests
- Max adjacent cell temperatures < 83°C
  - Adjacent cell temperature rise was 46-47°C, significantly lower than 1<sup>st</sup> run (77-94°C)
  - Bottom rupture yields a much less severe impact than side wall rupture



# Spacesuit Prototype Battery Test Summary

40

- Al Heat Sink Tests
  - 4 attempts to drive > 250Wh/kg cell into TR – All failures
    - 2 with Panasonic, 2 with LGs, all with home made bottom heaters
  - 5 attempts with 2.4Ah ISC device cells – No propagation of TR
    - 1 dud and 4 success with the 2.4Ah ISC cell driven into TR
  - 2 heat to vent tests with 5 fully charged 3.4Ah cells each
    - No side wall ruptures in areas supported by the sink
- LLB2 brick tests (All six 2.4Ah ISC cells successfully driven to TR)
  - 3 no-Ni bussing brick tests
    - No TR propagation and no OCV changes to adjacent cells with excellent temp margins
      - Interior cell trigger  $\Delta T \sim 19^{\circ}\text{C}$  (one run)
      - Edge cell trigger  $\Delta T \sim 42^{\circ}\text{C}$  (two runs)
    - Interior cell trigger are less vulnerable than edge cells based on temperature rise (max-onset T) on adjacent cells
  - 3 Ni bussing (13P5S)
    - No propagation of TR, no impact on adjacent cell OCVs
    - Very good temperature margins (vs onset of TR temperature)
      - Interior cell trigger:  $\Delta T \sim 30^{\circ}\text{C}$  (one run)
      - Edge cell trigger  $\Delta T \sim 48^{\circ}\text{C}$  (one valid run)
- LLB2 full scale tests (4 runs – 2 w/ 2.4Ah, 2 with 3.4Ah ISC device implanted cells)
  - No propagation of TR (even with side wall rupture of trigger cell in 1<sup>st</sup> test w/ 3.4Ah trigger cell)
  - Maximum adjacent cell temperature rise with 2.4Ah trigger cell was 55-58°C
  - Maximum adjacent cell temperature rise with 3.4Ah trigger cell was 94°C w/ side wall rupture and 46°C with bottom rupture
  - Gore vent design needs more flame arresting protection to handle 3.4Ah cell TR output
  - Screened vents were demonstrated as a successful flame arresting solution

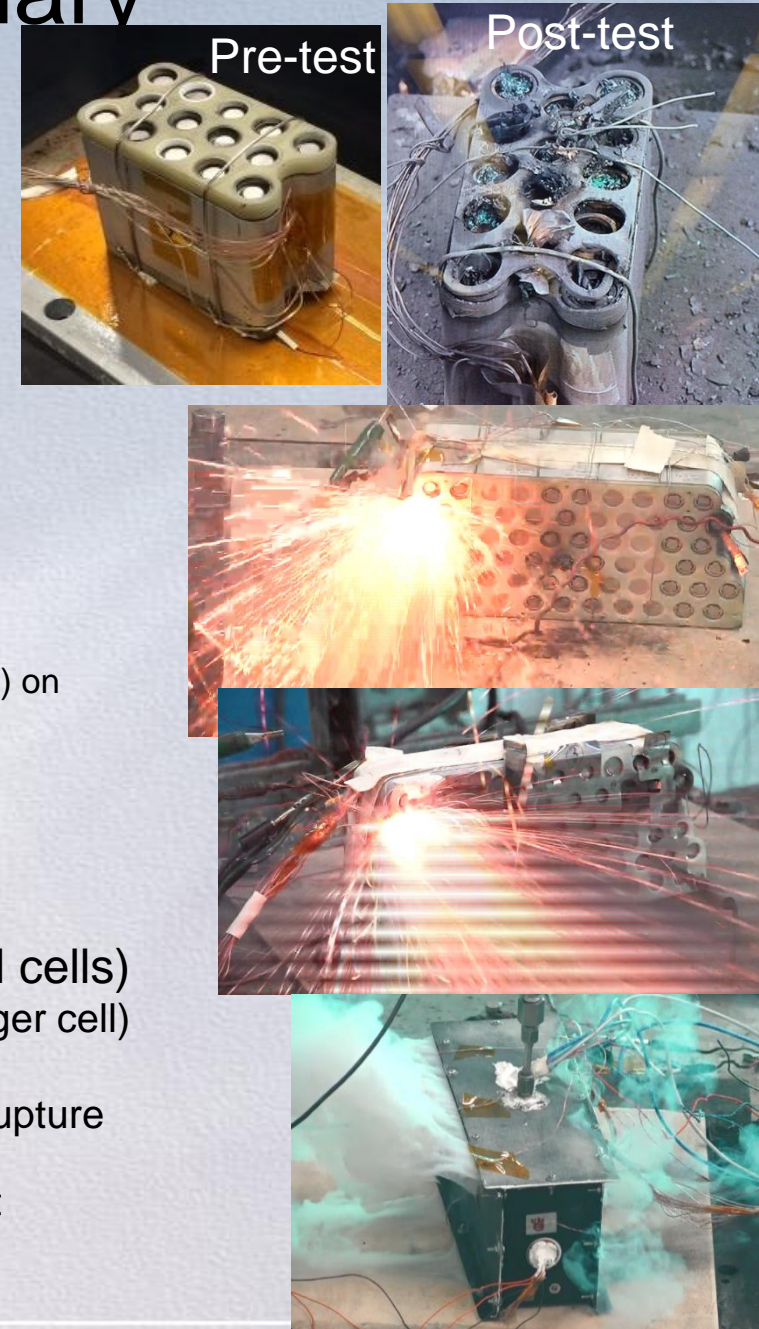



# ISC Device Location Reveals Side Wall Rupture Risk

- 3.4Ah cell can thickness
  - 165 microns
  - No bottom vent
- Unsupported oven heating test
  - **No** side wall ruptures (30 cells)
  - Slow external heating to TR
- Unsupported circumferential heater test
  - **No** side wall ruptures (5 cells) at ~30W
  - 1 of 3 side wall rupture at ~60W
- With ISC device (11 tested so far)
  - 8 sidewall ruptures
    - 5 unsupported
    - 3 supported by Al interstitial heat sink
  - 1 bottom rupture
    - Supported by Al interstitial heat sink
  - 2 vented through header
    - Supported by Fe tubes



ISC device in 3<sup>rd</sup> wind




Circumferential heater  
near bottom of can wall



# How Effective Are Steel Tubes?


Corner cell 1

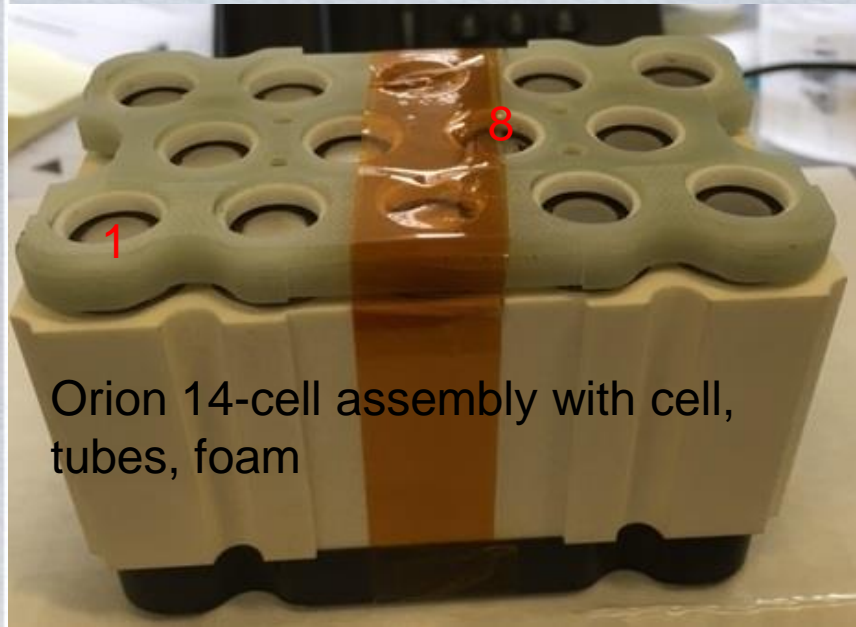

Orion 14-cell assembly with cell tubes, foam



- Fully charged 3.4Ah ISC device cells in positions 1 (corner) and 8 (interior) clocked towards adjacent cells
- Block heated to  $> 60^{\circ}\text{C}$  to activate ISC devices
- Corner cell wrapped with 0.015" (381  $\mu\text{m}$ ) SS tube experienced side wall rupture outside of tube
  - Dissection of tube found no cell can side wall ruptures inside tube area
- Interior cell wrapped with 0.009" (229  $\mu\text{m}$ )
  - No side wall ruptures outside or inside tube

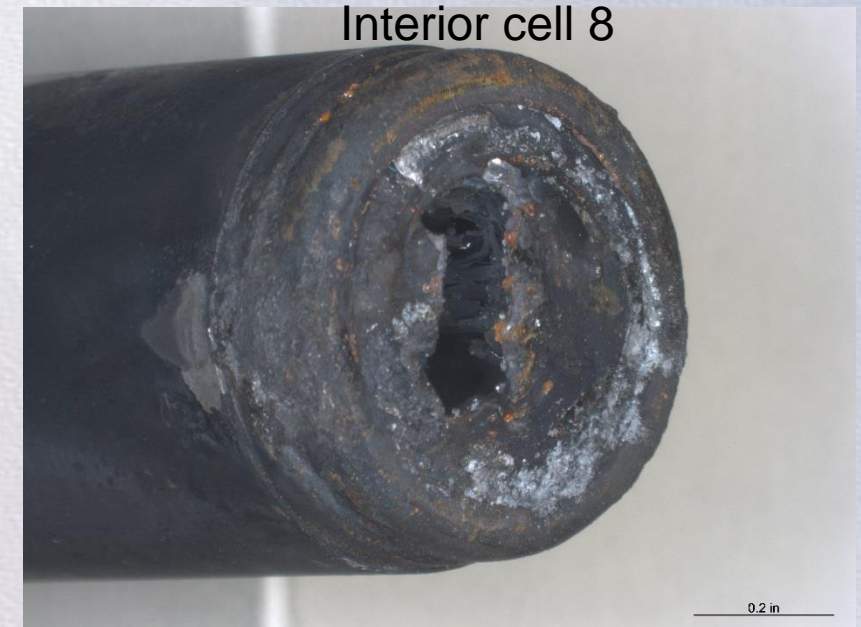




# Sony US18650VC7

43

Nominal Capacity at 0.2C	3530mAh 12.7Wh	discharge 2.0V cut off at 23°C
Rated Capacity at 0.2C	3400mAh 12.2Wh	discharge 2.0V cut off at 23°C
Capacity at 1C	3320mAh 12.0Wh	discharge 2.5V cut off at 23°C
Capacity at 6A	3300mAh 11.9Wh	discharge 2.5V cut off at 23°C
Nominal Voltage	3.6V	
Internal Impedance	22.6mΩ Typ.	measured by AC1kHz
Cycle Performance	60% Min. of Initial capacity at 500 cycles	1.5A charge 100mA cut 4A discharge 2.5V cut off at 23°C

## \* Standard Charge Condition


Charge Method : constant current constant voltage  
 Charge Up Voltage :  $4.2 \pm 0.05V$   
 Charge Current : 1.7A  
 Charge Time : 3.5h  
 Ambient Temperature: 23°C

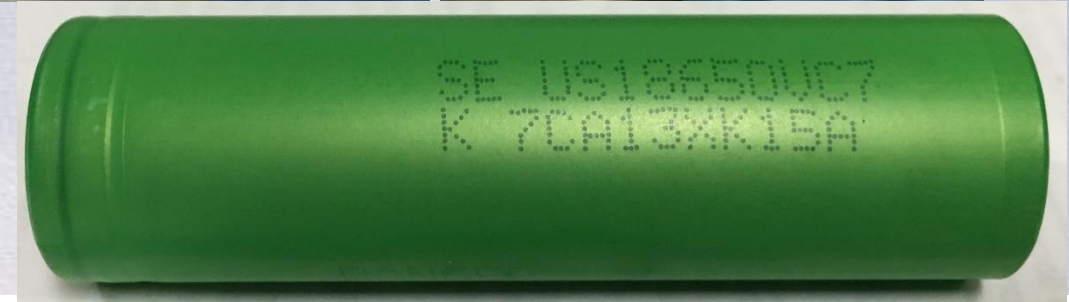


Venting area  
(Engraved)



a) Top view

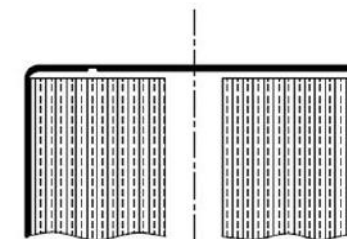

Before rupture

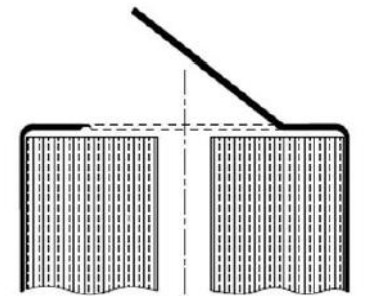

After rupture

b) X-section view




# Investigation of Bottom Vent Cell Designs

## Sony US18650VC7 Cell Design

Venting area  
(Engraved)





a) Top view

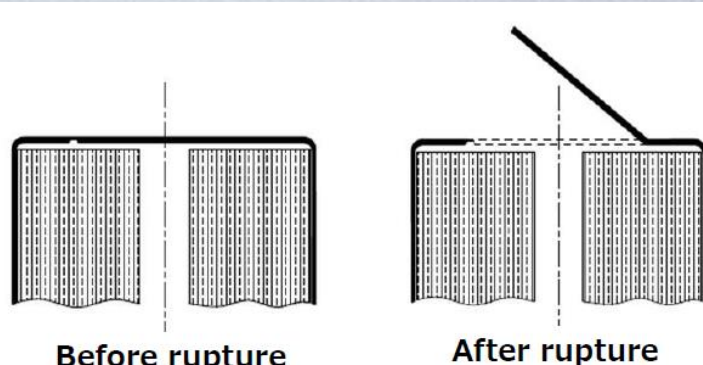


Before rupture

After rupture

b) X-section view

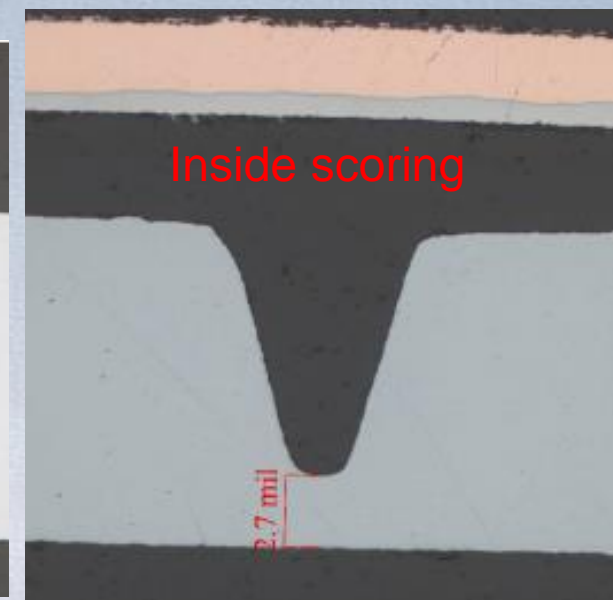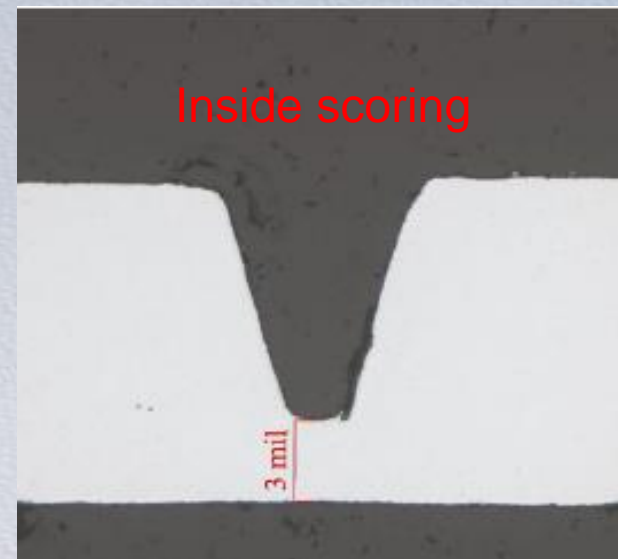

Sony VC-7 Cap Thickness  
Measurements taken at 100x mag

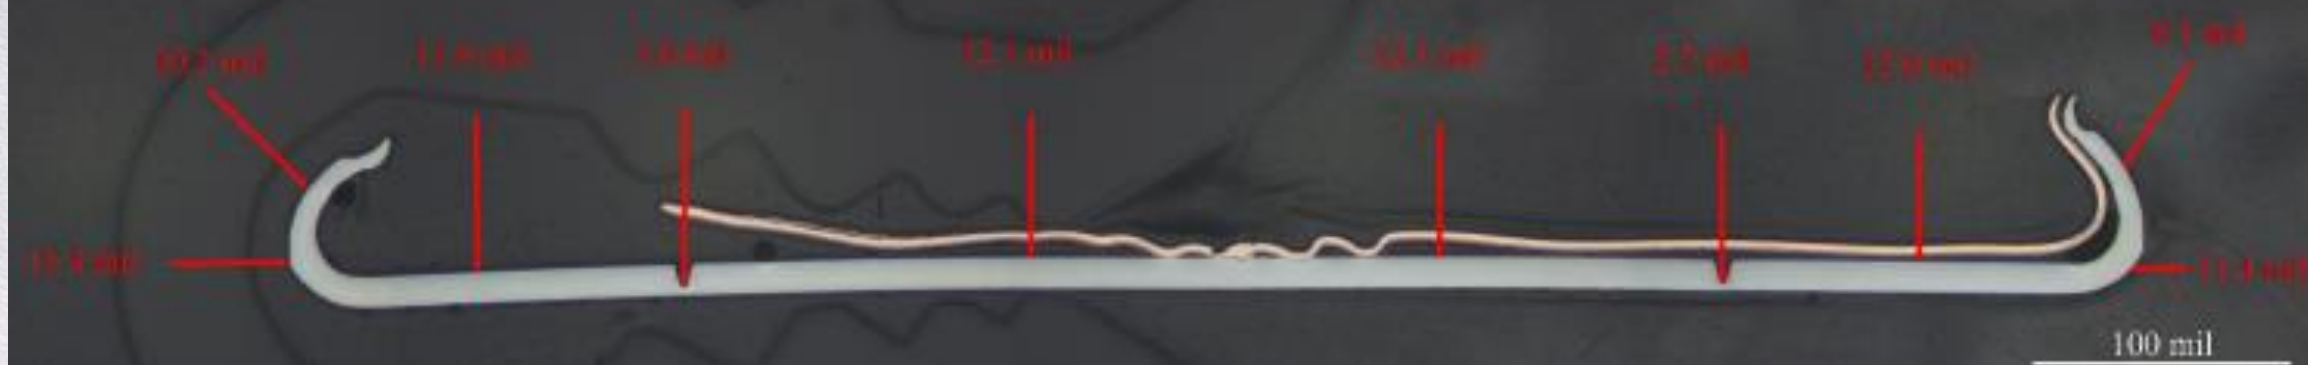


This feature could greatly reduce the risk of side wall rupture during thermal runaway




# Sony US18650VC7

45

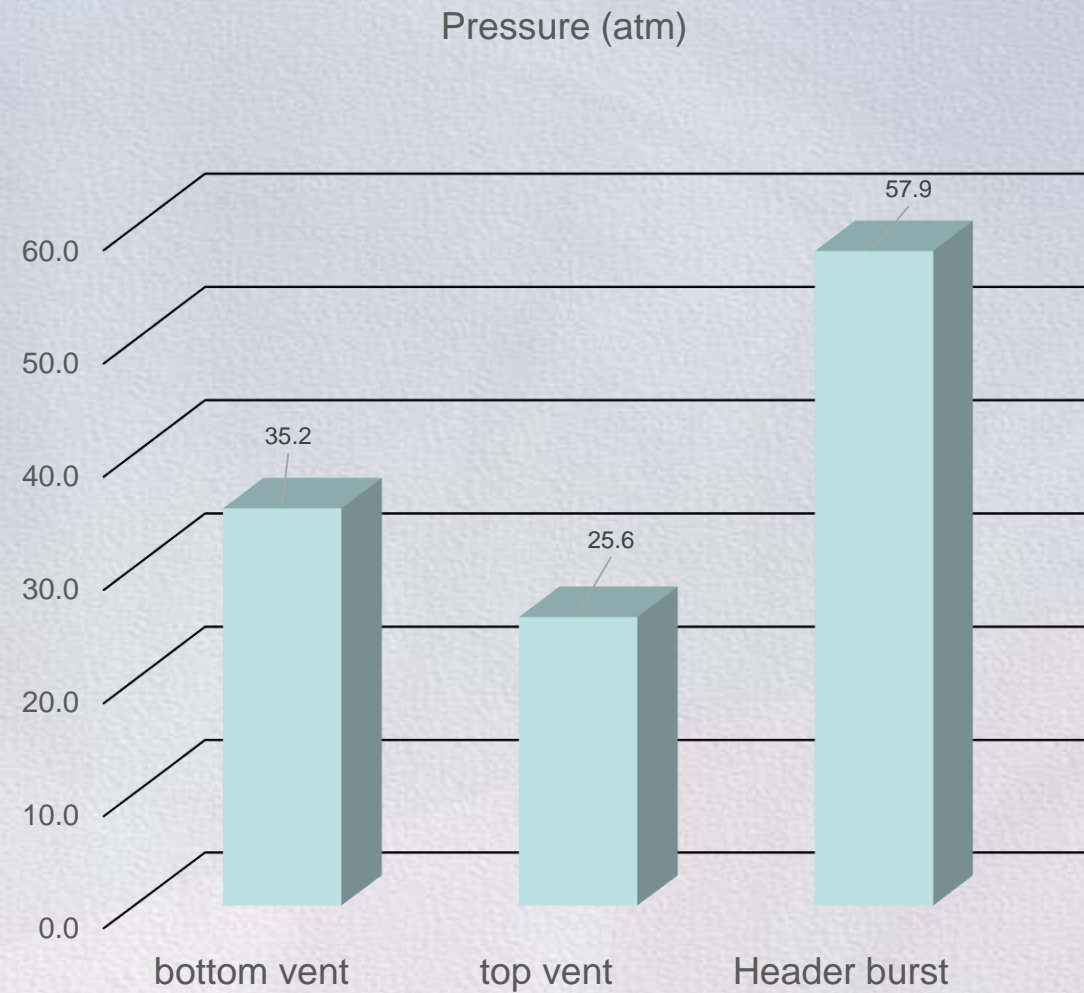

Bottom burst disc operates ~517 psia (35.2 bars)

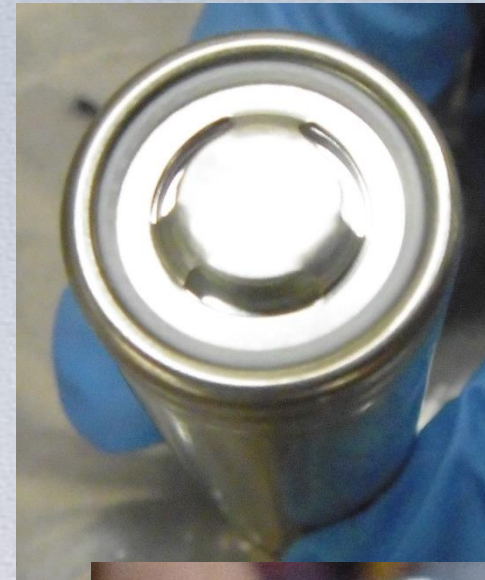




LG INR18650 M36-BV



MJ1 (3.5 Ah)	M36 (3.4 Ah)
max. 18.65	max. 18.45
max. 65.3	max. 65.6
0.15	0.22
47.0 g	47.5 g
3.5Ah	3.4 Ah
12.7wh	12.3 Wh
2.5~4.2	2.5~4.2
10A	10A
30	23


Pre-production cell design (not yet commercially available)

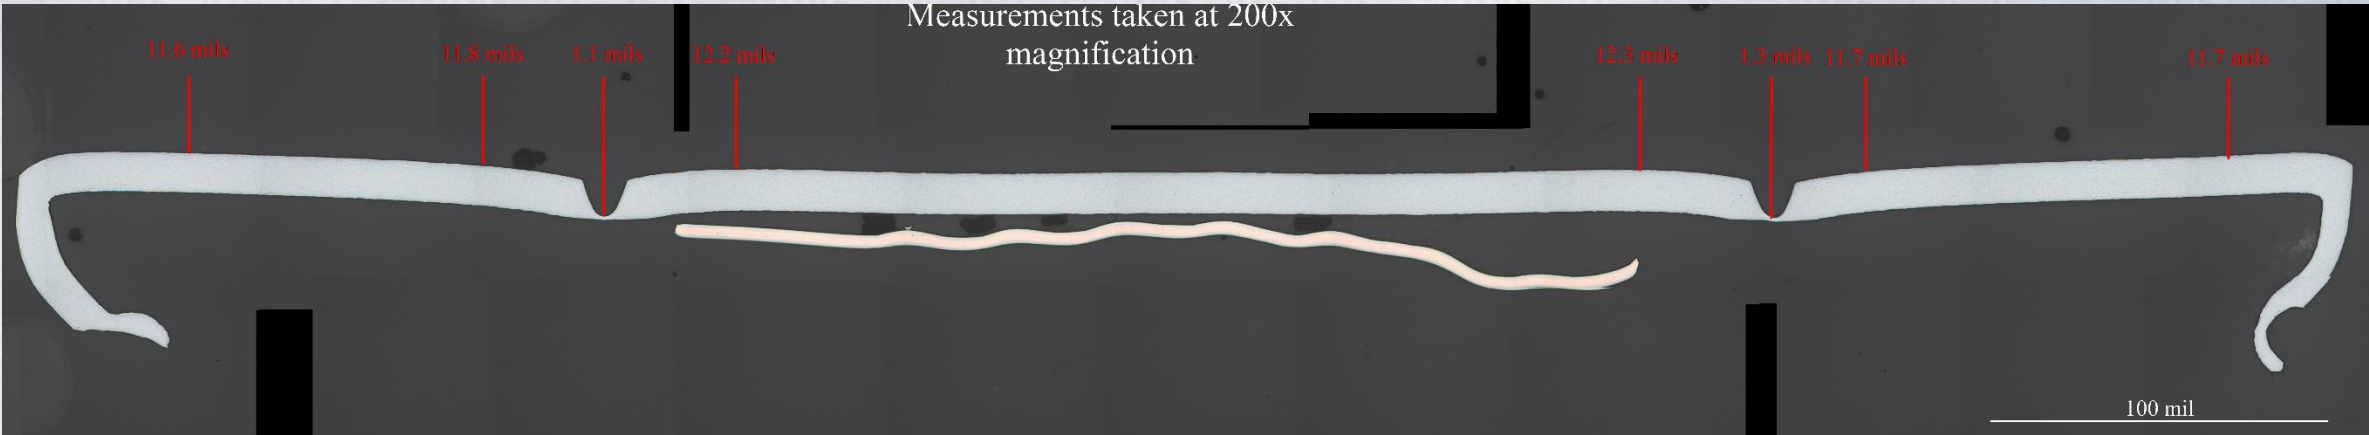



# Vent/Burst Pressure Stats


ID #	Pressure (Psia)		
	Bottom Vent	Top Vent	Header Burst
1	362.6	382.4	
2	359.8	365	
3	347.8	377.5	
4	359.1		826.2
5	356.6		860.1
6	364		825.1
Avg	358.3	375.0	837.1
StDev	5.28	7.33	16.25

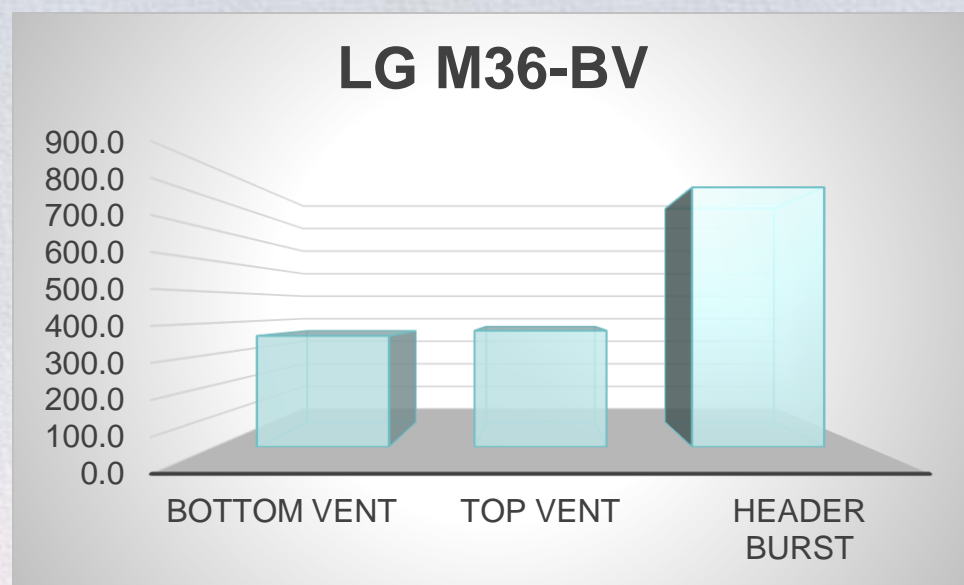

Bottom burst disc operates ~358 psia (24.4 bars)



# C-rate Capacity Performance Comparison

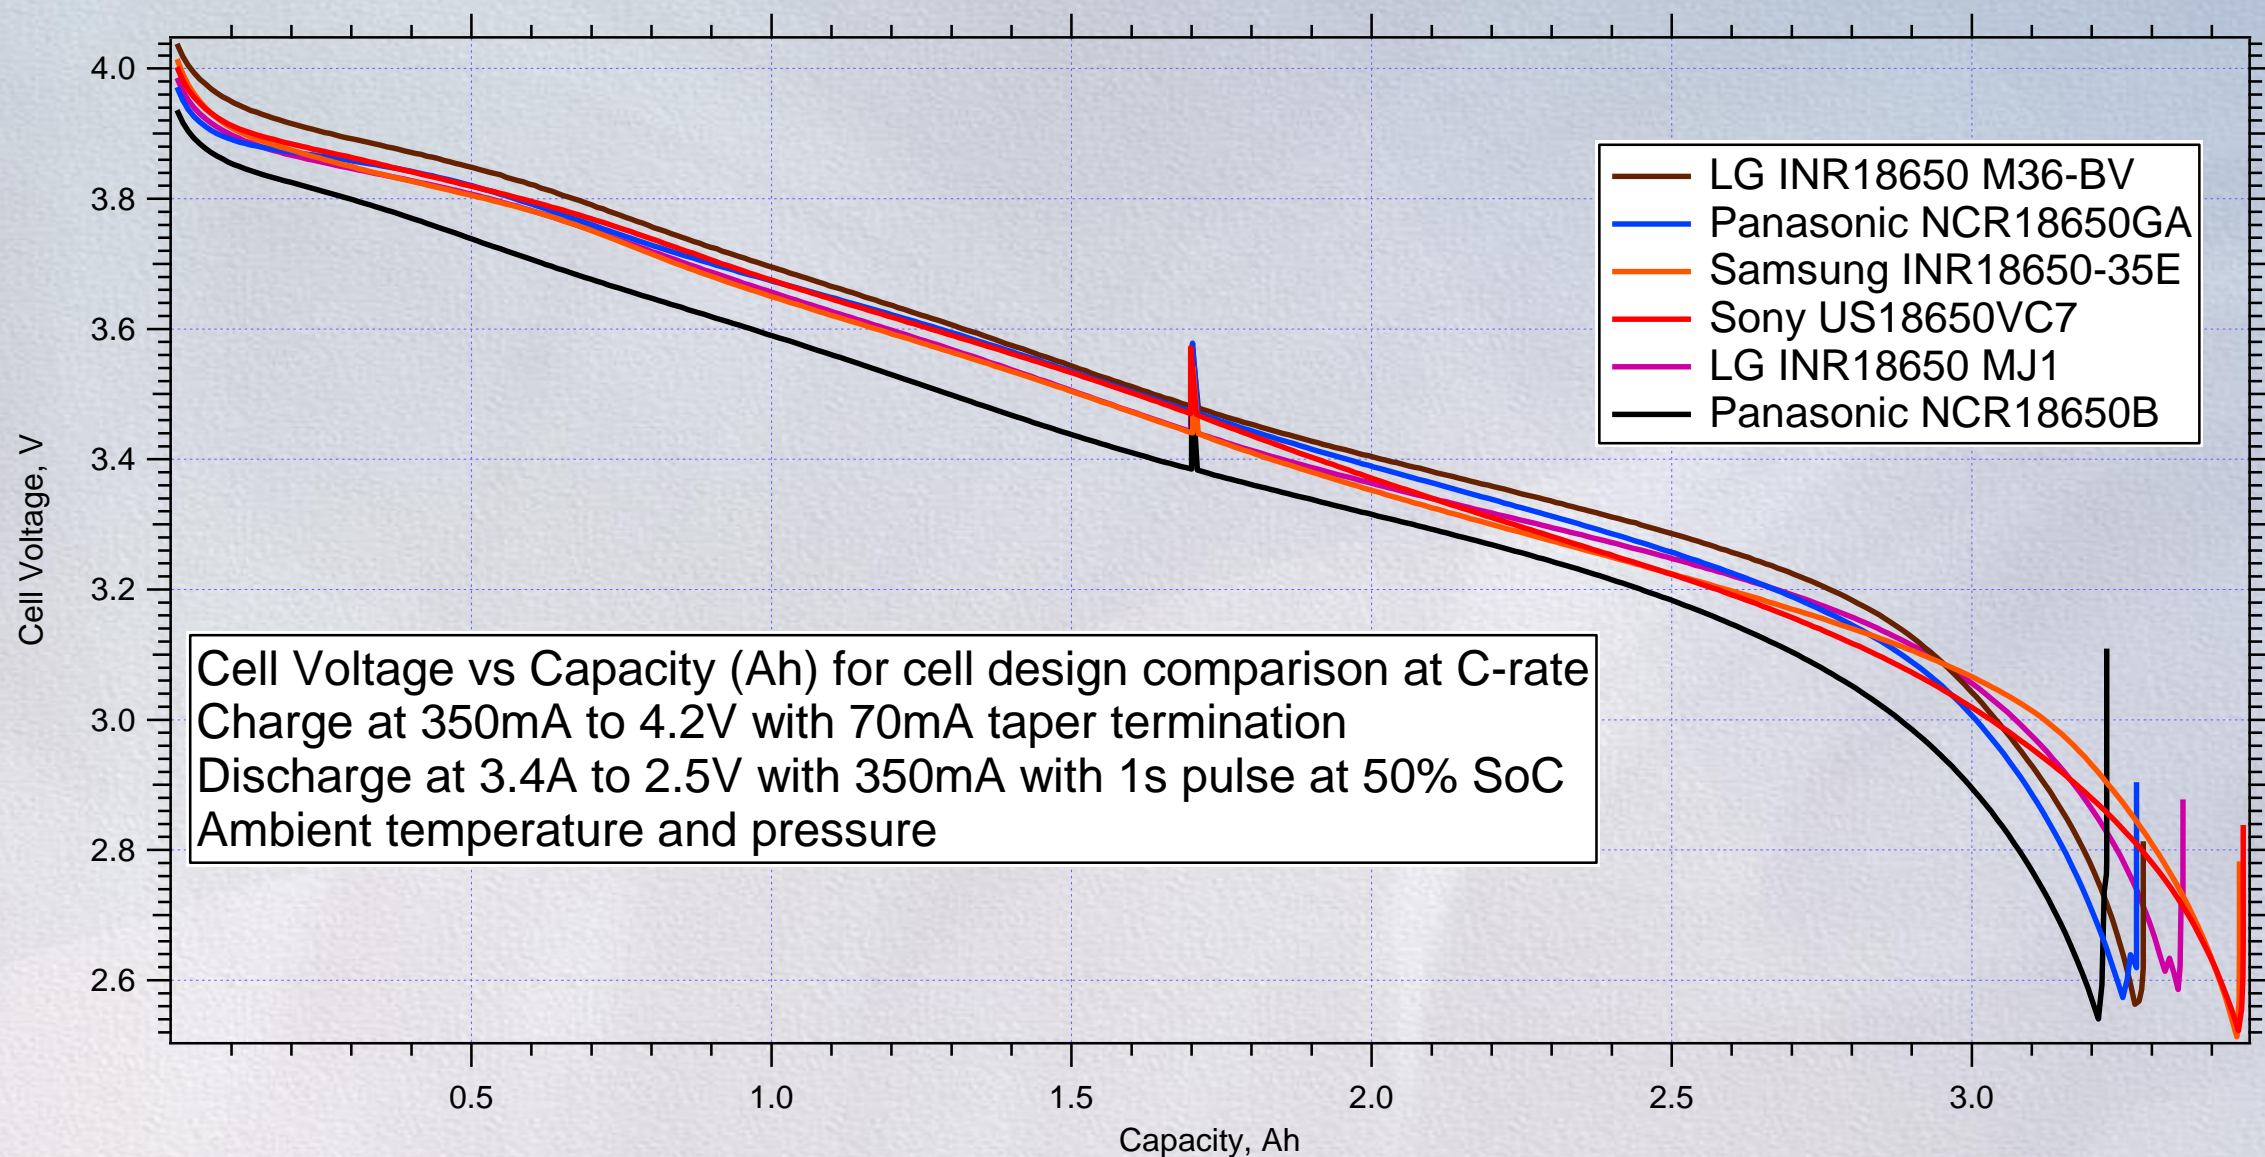



# Typical TR Performance of Bottom Vents

Sony VC7



LG M36-BV



Patch heater applied to bottom half of cell can



# Post TR Test Photos

Sony VC7



LG M36-BV



Ten cells driven into TR for each design



# Sony VC7 Driven into TR with Patch Heater



Two views showing 4 of the 10 cells that vented through the bottom and experienced side wall ruptures in area exposed to heater



# LG M36-BV Driven into TR with Patch Heater

Bottom vent works but 3 of 10 cells experienced side wall ruptures in area exposed to heater

## Big Caveat:

- This test weakens the cell can. NCR18650B cell design without bottom vent experiences much higher rate of side wall rupture





# Summary Findings

- ISC device enables critical battery safety verification
  - With the aluminum interstitial heat sink between the cells, normal trigger cells can't be driven into TR without excessive temperature bias of adjacent cells
  - With an implantable, on-demand ISC device, TR tests show that the conductive heat sinks very effectively protected adjacent cells from propagation
    - Even with >700 Wh/L cell design experiencing side wall or bottom rupture (4 test runs)
  - 3.4Ah 18650 cell design shown susceptible to side and bottom rupture with ISC device
    - Note that no side wall ruptures occurred during slow heat to TR testing (unsupported, 30 cells tested)
- High heat dissipation and structural support of Al heat sinks show high promise for safer, higher performing batteries
  - Battery brick design achieving > 190Wh/kg demonstrated to be safe
- Preliminary results on bottom vents are inconclusive
  - TR testing with ISC device is needed

## Future work

- Will examine impact of the location of the ISC device in the JR
- Will examine merits of cell designs with bottom burst disk vent feature to reduce side wall rupture risk
  - Is it a better solution than thicker can and/or lower header burst pressure?

## Acknowledgements

- M. Keyser, National Renewable Energy Labs, for making the ISC devices
- M. Shoesmith, E-one Moli Energy, for successfully implanting the ISC device in their 2.4Ah cell design
- D. Finegan, University College of London, for tomography and high speed X-ray videos
- P. Coman, University of South Denmark, for battery design guidance through thermal analysis

